

Mineralogy and geochemical features of Fouban clay deposits (west Cameroon): genesis and potential applications

A. NKALIH MEFIRE^{1,2}, R. YONGUE FOUATEU^{2,*}, A. NJOYA³, J.R. MACHE⁴,
P. PILATE⁵, F. HATERT⁶ AND N. FAGEL¹

¹Laboratory of Clays, Geochemistry and Sedimentary Environments (AGEs), Department of Geology, University of Liège, Quartier Agora, 14 Allée du 6 Août, Bât. B18, Sart Tilman – 4000, Liège, Belgium

²Laboratory of Applied Geology Metallogeny, Department of Earth Sciences, University of Yaoundé I, PO Box 812, Yaoundé, Cameroon

³Fine Arts Institute of Fouban (IBAF), University of Dschang, PO Box 31, Fouban, Cameroon

⁴Local Material Promotion Authority, PO Box 2396, Yaoundé, Cameroon

⁵Belgian Ceramic Research Center (INISMa-CRIBC) 4, Avenue Gouverneur Cornez, B-7000 Mons, Belgium

⁶Laboratory of Mineralogy, Department of Geology, University of Liège, Quartier Agora, 14 Allée du 6 Août, Bât. B18, Sart Tilman – 4000, Liège, Belgium

(Received 14 October 2017; revised 4 May 2018; Guest Associate Editor: Lachen Daoudi)

ABSTRACT: Five clay deposits in Fouban, west Cameroon, were studied for their morphological, mineralogical and geochemical properties to determine their suitability for ceramics. The clays were examined with X-ray diffraction, X-ray fluorescence, thermal gravimetric analysis and Fourier-transform infrared spectroscopy. Field studies showed that a homogeneous clayey layer occurs at the upper part of the laterite cover of the interfluvial, while the valleys are occupied by a clayey heterogeneous hydromorphic material. The clays are composed of kaolinite, illite, smectite and chlorite, associated with quartz, K-feldspars, plagioclase, goethite, traces of rutile and hematite. Geochemical analyses of these samples show a relatively large amount of SiO₂ (45–71%), Al₂O₃ (14–31%) and relatively little Fe₂O₃ (up to 11%), suggesting weathering of mainly granitic and rhyolitic parent rocks. The majority of these clays may be used in the production of structural ceramics such as bricks (refractory or not) and tiles. The relatively high proportion of the alkalis (K₂O + Na₂O; 6–8%) in some samples from Marom and Njindare areas might be responsible for the low firing temperatures. The abundance of smectite limits the application of some Koutaba and Marom clays for structural ceramics, while the high Fe₂O₃ contents (>8%) in some Bangourain clays indicate that some pre-treatment might be necessary prior to use.

KEYWORDS: common clays, mineralogy, geochemistry, ceramic, Fouban, Cameroon.

Natural clays used in the manufacture of structural ceramics are weathered products from rocks that crop out

at the earth's surface (Vieira & Sanchez Monteiro, 2008; Daoudi *et al.*, 2014). They may remain *in situ* as residual clays or may be transported and deposited in sedimentary basins as secondary clay deposits (Manning, 1995; Christidis, 2011) and valleys, resulting in alluvial clays (*e.g.* Ngon Ngon *et al.*, 2012; Fadil-Djenabou *et al.*, 2014; Ndjigui *et al.*, 2016). Optimum conditions necessary for the accumulation of thick, argillaceous sediments occur in warm, humid climates, where slowly

This paper was presented during the session 'CZ-01: Clays for ceramics' of the International Clay Conference 2017.

*E-mail: rfyongue@yahoo.fr

<https://doi.org/10.1180/clm.2018.31>

rising shield areas bordering basins are drained by rivers at the maturity stage (Ridgeway, 1982). Some common clays (alluvial clays) provided the cohesion and workability needed for manufacturing whiteware and earthenware (Wilson, 1998; Reeves *et al.*, 2006). Their optimal exploitation and valorization for use in ceramics require detailed assessment, beginning with the determination of their mineralogical compositions and geochemical properties.

Due to its geographical location and geological context, Cameroon (Central Africa) has widespread clay deposits (Elimbi *et al.*, 2003; Nkoumbou *et al.*, 2008, 2009; Ngon Ngon *et al.*, 2009; Ekosse, 2010; Nzeukou *et al.*, 2013; Fadi-Djenabou *et al.*, 2014; Tassongwa *et al.*, 2014; Ndjigui *et al.*, 2016). The potential uses of these clay materials include ceramic products such as bricks, tiles, refractories and fine porcelain (Elimbi *et al.*, 2002; Kamseu *et al.*, 2007; Djangang *et al.*, 2007, 2008a,b; Pialy *et al.*, 2009; Diko *et al.*, 2011; Nzeukou *et al.*, 2014; Ndjigui *et al.*, 2015). Nevertheless, there are few industrial units in the country; some local producers exist, but their hand-made products are generally of poor quality. In fact, raw materials are not always used efficiently in ceramic production. For example, in Foumban (west Cameroon), clay materials were exploited for traditional production in small-scale ceramic factories (pottery, brickworks) and used to build the Foumban Royal Palace in the twentieth century. However, these traditional methods of ceramic production do not take into account the properties of the raw materials. This may explain why parts of the Foumban Palace became damaged and needed restoration. The purposes of this study are to locate common clay occurrences in the broader area of Foumban and to determine their mineralogical compositions and geochemical properties in relation to their suitability for ceramic products.

GEOLOGICAL SETTING

Foumban is part of the Bamoun plateau (average altitude: 1200 m) in western Cameroon, in the central area of the continental part of the Cameroon volcanic line (CVL), which includes plutonic and volcanic rocks (Njonfang *et al.*, 2011). The studied area is made up of a Precambrian–Panafrican basement underlying Eocene basalts (Weecksteen, 1957). The main volcanic rocks are fissure-erupted mafic rocks, among which transitional basalts constitute the main lava flows, with some samples dated at 51.8 m.y., the oldest volcanic manifestation found in the CVL (Moundi *et al.*, 2009).

Various mantle sources participated in the formation of the Bamoun lavas (Moundi *et al.*, 2007), among which is a mantle source similar to that of Mt Cameroon (Okomo Atouba *et al.*, 2016). The Precambrian–Panafrican basement is made up of gneiss extruded by syntectonic plutonism and affected in the northern part by the Foumban shear zone (Njonfang *et al.*, 1998). The Precambrian granite–gneissic bedrock mainly outcrops in the north of the Bamoun plateau. Transitional basalts outcrop in the western part, near Bangourain and Foumban, while alkaline basalts are observed in the south-eastern part, around Foumban, Koutaba and Foubot (Wandji, 1995; Moundi *et al.*, 1996, 2009). A geological map (Weecksteen, 1957) illustrating the main rock types with locations of sampling points is shown in Fig. 1. The significant weathering of the bedrock has formed deep ferrallitic soils. The surface formations in the region are composed of red lateritic or ferrallitic soils in the uplands and hills and hydromorphic soils in the lowlands (Segalen, 1967).

MATERIALS AND METHODS

Field campaigns were conducted using classical methods of geological survey to locate and characterize clay materials found in valleys and/or foothills in Koutaba (S1), Bangourain (S2), Marom (S3), Njindare (S4) and Njimom (S5) (Fig. 1). Twenty-six samples of common clays (Table 1) from Koutaba (14), Marom (4), Bangourain (4), Njindare (2) and Njimom (2) were collected. The nature, size, thickness and distribution of the outcrops were determined. The colours of the various profile layers were determined with the Munsell code (Cailleux, 1992) and the samples were selected according to clay facies variation (texture, colour).

Bulk dried samples (40°C for 24 h) were ground using an agate mortar and sieved to obtain a homogeneous, fine, <250 µm powder used for X-ray diffraction (XRD), X-ray fluorescence (XRF), thermal gravimetric analysis (TGA) and Fourier-transform infrared spectroscopy (FTIR) analyses. Mineralogical analysis was done in the AGES (Argiles, Géochimie et Environnements Sédimentaires) laboratory at the University of Liege in Belgium. X-ray diffraction patterns were determined with a Bruker Advance D8 diffractometer using Cu-K α radiation, 40 kV and 30 mA. Bulk powders were analysed following the normal procedure as presented by Moore & Reynolds (1997). For clay fractions, oriented aggregates on glass slides were prepared from the <2 µm fraction obtained

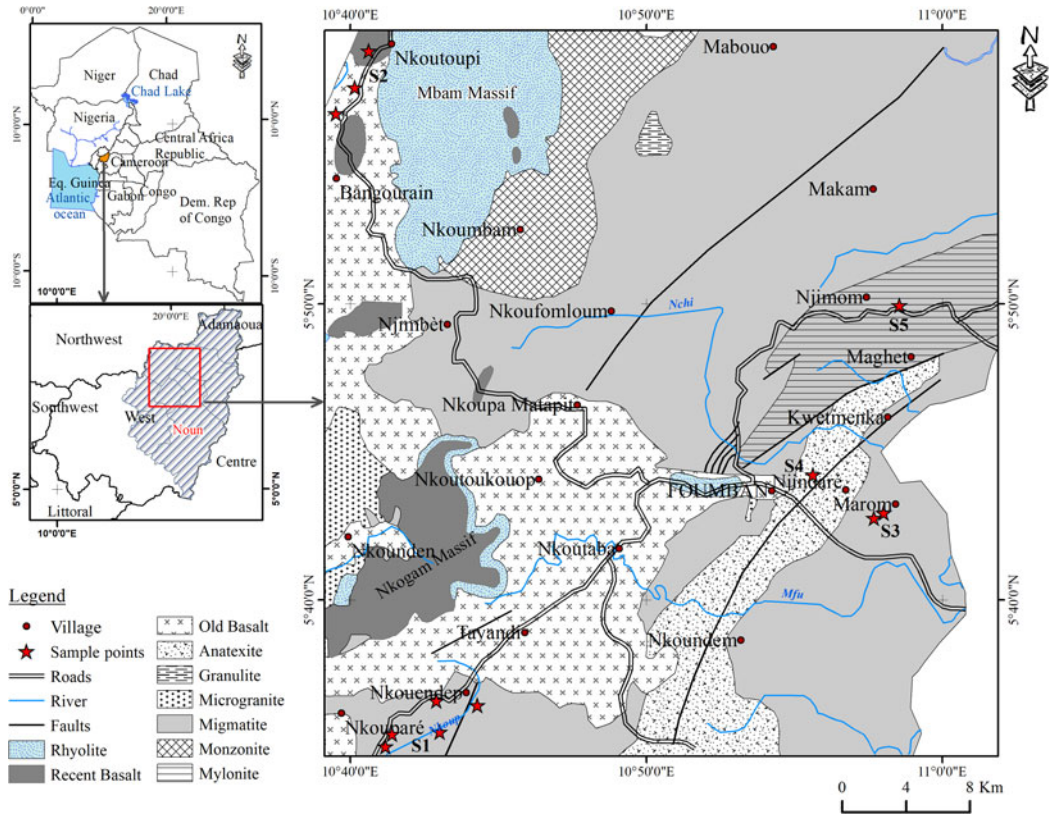


FIG. 1. Geological map of Foumban (after Weecksteen, 1957) with locations of sampling points.

by suspensions of 1–2 g of the dried bulk sample in distilled water. Three patterns were recorded, under natural conditions (N), after saturation with ethylene glycol (EG) for 22–24 h and after heating (H) at 500°C for 4 h. Minerals were identified using the *EVA* software. The semi-quantitative mineralogical composition of bulk powder was estimated from the intensity of a diagnostic peak multiplied by a correction factor (Cook *et al.*, 1975; Boski *et al.*, 1998). For the clay fractions, semi-quantitative estimation was done following the method described by Moore & Reynolds (1997).

Differential TGA was carried out with a SETARAM Cahn apparatus, operating under the following conditions: heating rate of 20°C/min, sample weight of 40 mg, in an air atmosphere from ambient temperature to 1200°C. Infrared spectra were collected on a Bruker FTIR Spectrometer between 4000 and 400 cm^{-1} to assess the structure and crystal order of the clay minerals. Geochemical analyses of major elements

were carried out by XRF spectrometry with an ARL PERFORM-X 4200 XRF spectrometer with a standard error <1% on samples fired at 1000°C. The abundance of major elements was compared with the average compositions of the source rocks.

RESULTS AND DISCUSSION

Location and description of clay materials

At Njimom (18 km north of Foumban) and at Koutaba (27 km south of Foumban; Fig. 1), a thick-layered lateritic cover is observed on dissymmetric hills (Fig. 2a). A vertical cross-section from the top to bottom shows: (1) an organic brown layer; (2) a sandy, pale brown-reddish clayey layer; and (3) a reddish, homogeneous, clayey layer with locally greyish, brownish and purplish varieties; homogeneous, fine and sandy weathering horizon brownish with locally whitish and/or yellowish varieties (Fig. 2b). They are

TABLE 1. Location of sampling points and lithology.

Localities	Samples	Thickness (m) and lithology	Coordinates	Localization in landscape
Koutaba (S1)	KB3c	2.2–3.2: fine, grey, light clay (7.5Y7/2)	N05°36'21"	Lower part in a margin of Nkoup River
	KB3f	4.5–5.0: fine, grey-brown clay (10Y7/4)	E010°44'16.3"	
	KC4b	2.0–3.4: fine, grey clay mottled with brown and yellow (5YR4/4)	N05°35' 30.0" E010°41'37.4'	
	KC4d	4.0–4.5: sandy, grey clay (5YR4/2)		
	KC4f	4.5–5.0: green clay (7.5Y4/6)		
	KF5c	2.4–3.0: fine, grey clay (5Y4/2)	N05°35'28.1"	
	KF5d	3.0–3.5: fine, light grey clay (7.5Y7/2)	E010°43'2.7"	
	KF5e	3.5–4.0: fine, dark greyish clay (10Y1/2)		
	KG2b	0.6–1.6: fine, grey-brown clay (10Y7/4) mottled with yellow (7.5YR7/12)	N05°35'20.8" E010°41'25.7"	
	KG2c	1.6–2.2: fine, grey-green dark clay (10Y3/4)		
	KG2f	3.4–4.5: fine, grey-brown clays (5YR4/8)		
	KG3c	1.5–1.8: fine, grey-greenish clay (10Y4/6)	N05°35'27.9"	
	KG3d	1.8–2.4: fine, grey-greenish clay (10Y5/6)	E010°43'0.50"	
KG3e	2.7–4.0: fine, grey-greenish clay (10Y4/6) with dark greenish garnish (10Y1/2)			
Bangourain (S2)	BA2a	0.8–2.6: fine, brown clay mottled with yellow (7.5 YR 6/8)	N05°56'17.3" E010°38'8.90"	Margin of Monoun River
	BA2b	2.6–4.0: fine to sandy, brown clay (5YR4/8)		Lower part of landscape
	KP11	0.2–1.8: fine, brown clay (5YR4/8)	N05°58'24.2"	
	KP12	1.8–3.2: fine, grey-brown clay (10YR6/2)	E010°44'36.8"	
Marom (S3)	MA1e	2.0–3.6: sandy, dark grey (10Y1/2) mottled with white clay (10Y9/4)	N05°42'53.4" E010°56'14"	Narrow valley and the bottom of hill
	MA2d	4.2–4.8: fine, sandy grey clay mottled with green (10Y5/6)		
	MA3b	1.4–2.4: sandy, grey clay (5YR4/2)		
	MA3c	2.4–3.2: sandy, grey-brown clay (10Y7/4)		
Njindare (S4)	NJAb	0.1–2.0: fine, grey-brown clay (10YR6/2), sandy, brown clay (10 YR 8/3)		Narrow valley
	NJAc	2.0–3.2: sandy, dark grey clay (10Y1/2)		
Njimom (S5)	NJJ	≈1.0: fine, purple clay (5YR1/4)	N05°49'7.63"	Lower part of landscape
	NJR	≈2.0: yellow-brown, sandy clay (7.5YR7/12)	E010°55'9.51"	

residual primary clays resulting from the weathering of the Panafrican granite–gneiss basement (Nkalih *et al.*, 2015). Close to the study area, Njoya *et al.* (2006) described a kaolin deposit overlain by rolling stones from the mylonitic cliff and by a <1 m thick grey, powdery soil, which is distinct from the red lateritic soil of the surrounding area.

In the lower part of the landscape, the clay materials occur in small and narrow valleys at Marom (5 km east of Foumban) and Njindare (2 km north of Foumban; Fig. 1). They are widespread in the swampy valleys along both margins of the Nkoup river at Koutaba (Fig. 2c), and along the Monoun river at Bangourain (~30 km northwest of Foumban; Fig. 1). The clay profiles are heterogeneous with several clayey and

sandy layers of grey, grey-mottled brown and dark brown colours (Fig. 2d). This heterogeneity in colour, texture and thickness characterizes alluvial clays (Ngon Ngon *et al.*, 2009), with similar field features as the recent alluvial clastic sediments in the Sanaga Maritime region (southern Cameroon) studied by Ndjigui *et al.* (2015).

Mineralogical composition

Knowledge of the mineralogical and chemical properties of the clayey materials used is required to make ceramic products (Vieira & Sanchez Monteiro, 2008; Dondi *et al.*, 2014). Bulk powder XRD traces of the Foumban clays (Fig. 3a) reveal a mineral

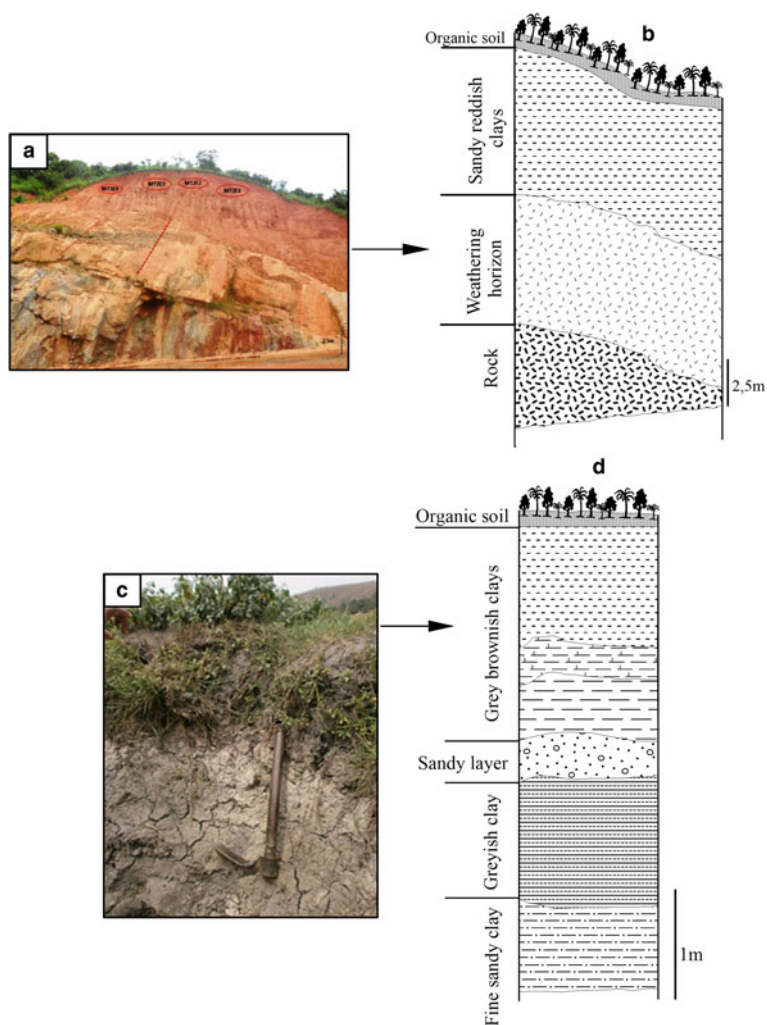


FIG. 2. Description of the clay materials of Foumban. (a) Outcrop of lateritic cover on a hill at Njimom. (b) Vertical cross-section of the clayey laterite. (c) Alluvial clays from Nkoup swampy valley in Koutaba. (d) Vertical cross-section of the clayey hydromorphic materials.

assemblage comprising kaolinite, quartz, K-feldspar, plagioclase, smectite, illite, gibbsite, goethite, rutile and hematite. The proportions of the various minerals vary among the study areas and also within the same area (Table 2). Quartz is the most common non-clay mineral with low (<10%) to moderate (21–44%) amounts at Njimom and Marom. K-feldspars and plagioclase are abundant at Marom, Njindare (NJAb) and in two samples from Koutaba (15–27% and 23–26%, respectively). Gibbsite, goethite, rutile and hematite are generally present in minor quantities (<5%). The oriented clay fractions consist of kaolinite,

illite and smectite (Fig. 3b); the presence of smectite was verified from the shift of the d_{001} spacing from 14.00 Å to 16.66 Å after EG treatment (KG3e).

The quantitative mineralogical analysis showed that kaolinite (25–84%) is ubiquitous and illite (0–18%) is present in most of the studied samples (Table 2). Samples from Marom and Njindare are richer in illite (8–18% and 11–17%, respectively). Smectite is mostly present in samples from Koutaba (3–31%) and as a trace phase in samples from Marom and Njimom (~5%). Chlorite appears scarcely in some alluvial clays from Koutaba and Bangourain (3–8%). The clay

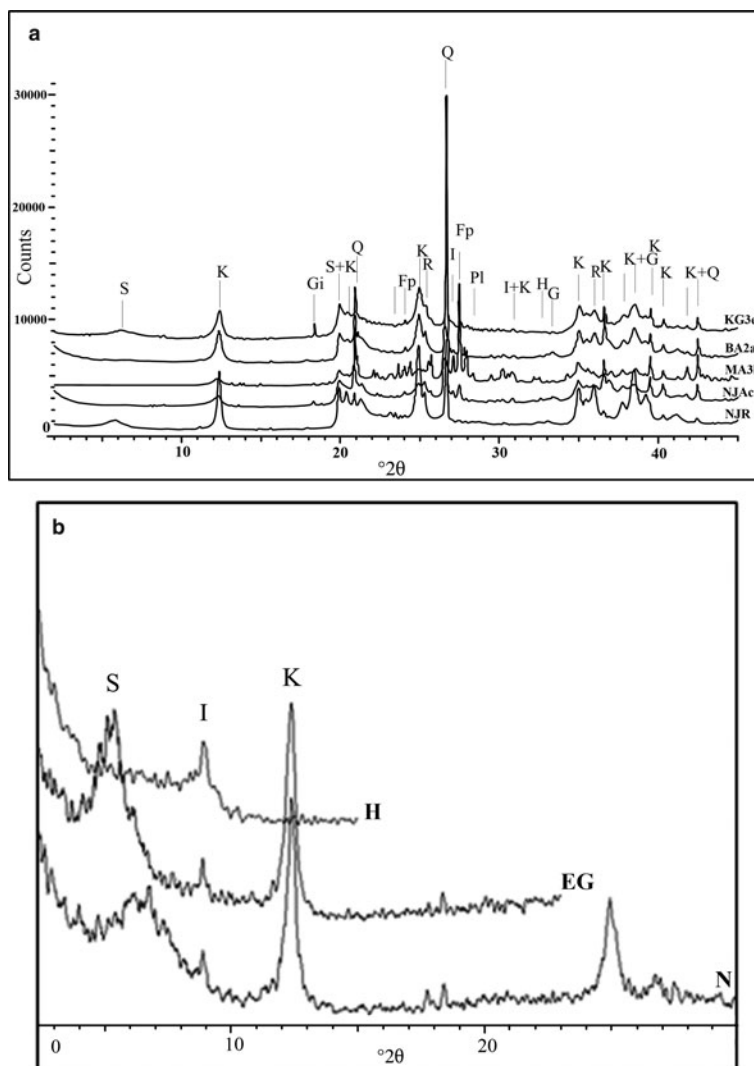


FIG. 3. XRD patterns of Fouban clays. (a) Bulk powder (KG3e – Koutaba; BA2a – Bangourain; MA3b – Marom; NJAc – Njindare; NJR – Njimom). (b) Oriented clay fraction of the KG3e sample. N: untreated; EG: ethylene glycol solvated; H: heat-treated at 500°C; K: kaolinite; Q: quartz; Fp: K-feldspars; Pl: plagioclase; I: illite; S: smectite; G: goethite; Gi: gibbsite; H: hematite; R: rutile.

minerals are abundant in clays from Njimom (85–87%), Bangourain (59–76%), Njindare (63–80%) and Koutaba (35–95%) and low at Marom (22–50%).

The FTIR spectra (Fig. 4) are typical of kaolinite-rich clays. In samples from Koutaba (KG3e), Bangourain (BA2a) and Njimom (NJR), the bands at 3694, 3664, 3650, 3620 and 918 cm^{-1} are due to the presence of hydroxyl groups (Fialips *et al.*, 1999). The absence of bands at 3667 and 3652 cm^{-1} in the KG3e

and BA2a samples indicates disordered or poorly crystallized kaolinite; this is further confirmed by the absence of Al_2OH bending bands at 938 cm^{-1} (Cases *et al.*, 1982). In addition, the FTIR analyses revealed the presence of impurities. The bands at ~2925 (2918) and 2855 (2851) cm^{-1} correspond to the C–H stretching vibrations related to the organic matter. The presence of quartz in all samples is confirmed by the Si–O symmetrical stretching vibration at

TABLE 2. Mineralogical composition (wt.%) of clay materials from Founban.

Sample	Kaolinite	Illite	Smectite	Chlorite	Total clays	Quartz	K-feldspar	Plagioclase	Goethite	Hematite	Rutile
Koutaba clays (S1)											
KB3f	35	13	22	7	77	21	—	—	—	—	2
KB3c	25	5	5	—	35	37	5	23	—	—	—
KF5c	79	—	7	—	86	14	—	—	—	—	—
KF5d	60	9	3	6	78	18	5	—	—	—	—
KF5e	39	15	—	3	57	28	15	—	—	—	—
KG2f	51	5	4	—	60	39	—	—	1	—	—
KG2c	70	5	20	3	98	2	—	—	—	—	—
KG2b	84	—	—	—	84	5	2	4	1	2	—
KC4f	62	2	10	—	74	21	5	—	—	—	—
KC4d	84	—	11	—	95	5	—	—	—	—	—
KC4b	84	—	—	—	84	5	2	5	2	2	—
KG3e	51	4	31	—	86	11	3	—	—	—	—
KG3c	62	3	23	—	88	12	—	—	—	—	—
KG3d	60	2	17	—	79	21	—	—	—	—	1
Bangourain clays (S2)											
BA2a	67	4	—	—	71	19	8	—	2	—	—
BA2b	63	8	—	5	76	15	6	—	3	—	—
KP11	49	4	—	7	60	30	6	4	—	—	—
KP12	46	5	—	8	59	36	5	—	—	—	—
Marom clays (S3)											
MA1e	13	7	2	—	22	24	19	26	9	—	—
MA3c	33	15	2	—	50	32	15	3	—	—	—
MA3b	27	18	2	—	47	21	27	5	—	—	—
MA2d	16	8	2	—	26	44	26	4	—	—	—
Njindare clays (S4)											
NJAb	63	17	—	—	80	20	—	—	—	—	—
NJAc	52	11	—	—	63	30	7	—	—	—	—

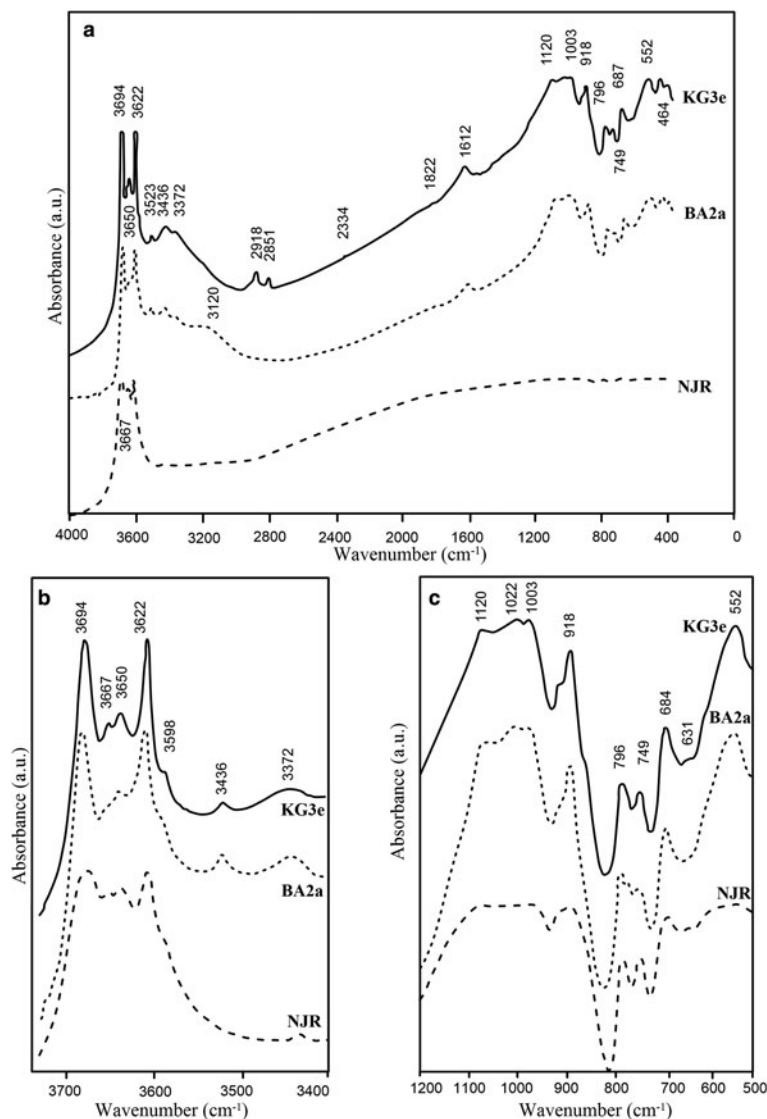


FIG. 4. FTIR spectra of Koutaba (KG3e), Bangourain (BA2a) and Njimom (NJR) samples: (a) complete spectrum; (b) 3800–3400 cm^{-1} region; (c) 500–1200 cm^{-1} region.

$\sim 795 \text{ cm}^{-1}$. The wide band at $\sim 1626 \text{ cm}^{-1}$ is attributed to bending of adsorbed water molecules.

Two significant weight-loss events on TGA curves are characteristic of kaolinite-rich clays (Fig. 5). The first weight loss below 100°C (78°C , 1–3%) is due to the loss of adsorbed water. The second one between 486 and 500°C corresponds to kaolinite dehydroxylation (5–10%) and is usually indicative of the fraction of kaolinite reacting during firing (Christidis, 2011). The minor weight loss (1–3%)

between 226 and 266°C might be attributed to the presence of organic matter, goethite and/or gibbsite (Mackenzie, 1957), identified by XRD. These observations were confirmed in differential thermal analysis (DTA) curves with two main endothermic peaks at 104 – 115°C and 486 – 500°C , respectively. The first endothermic peak corresponds to the dehydration and the second to the dehydroxylation of kaolinite and its transformation into meta-kaolinite.

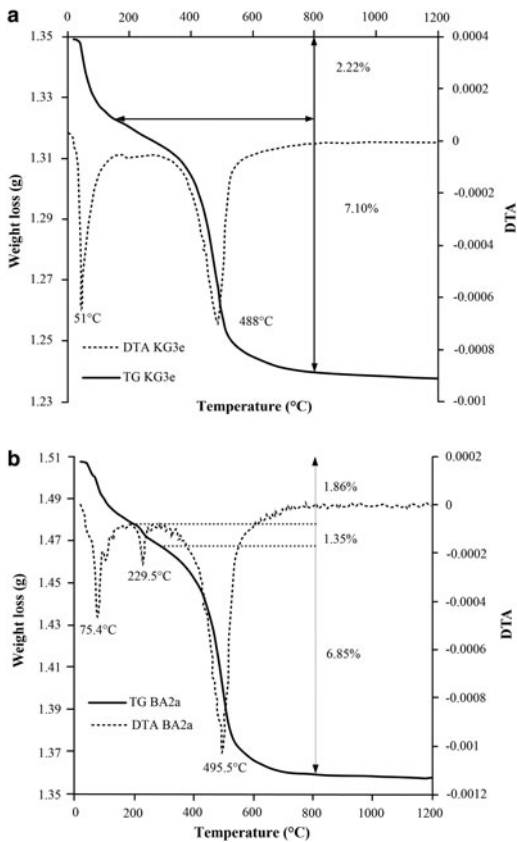


FIG. 5. TG/DTA curves of the clay samples from: (a) Koutaba and (b) Bangourain.

Geochemistry

Table 3 presents the major chemical composition of the clay samples. The most abundant oxides are SiO_2 (45–71%), Al_2O_3 (14–31%) and Fe_2O_3 (1–12%), with high Fe contents (>8%) in some samples from Bangourain. The TiO_2 , MnO, MgO, CaO, Na_2O and P_2O_5 contents are generally low, with K_2O (2–6%) being more abundant. The relatively high K_2O content in samples from Marom and Njindare is due to the presence of K-feldspars and illite. Some samples have high Al_2O_3 content (>22%) in accordance with their high kaolinite content. The low $\text{SiO}_2/\text{Al}_2\text{O}_3$ ratio (~2) in the Koutaba, Bangourain and Njimom clay samples is also compatible with the high kaolinite content in these samples. In contrast, the high $\text{SiO}_2/\text{Al}_2\text{O}_3$ ratio (3–5) in the Marom and Njindare samples is controlled by the quartz content. The mixture of mainly kaolinite and quartz in the clays studied might be compared to

that of the Romana kaolinitic materials (Ligas *et al.*, 1997). The loss of ignition (LOI) ranging from 3% to 9% in Marom and some Njindare clays and of >10% in other areas is associated with the loss of structural water in clay minerals, as was confirmed by thermal analysis and XRD. The relatively high LOI in some samples (Table 4) might also be attributed to the presence of volatile organic components or smectite (KG3e and KG3c).

The Chemical Index of Alteration (CIA; Nesbitt & Young, 1984) ranges from 80 to 100 (Table 3), except for MA2d (63) and MA1e (70) in Marom clays. The high CIA values for Foumban clay deposits are due to their enrichment in kaolinite crystallized during intense chemical weathering (Goldberg & Humayun, 2010). The lower CIA for Marom clays and the high K_2O contents are related to the occurrence of K-feldspars. The relatively low CIA values confirm moderate weathering of sediments (Ndjigui *et al.*, 2015).

Principal component analysis and genesis of clay materials

The chemistry and mineralogical composition of clays depend on the origin of clay (hydrothermal, residual or alluvial), the nature of the parent rocks, topography and climatic conditions. Figure 6 presents the results of a principal component analysis (PCA) for the major element data obtained from the analyses of clays from Foumban. The two factors F1 and F2 describe 47.6% and 19.6% of the total variance, respectively. High positive F1 correlation indicates high amounts of TiO_2 , Al_2O_3 , Fe_2O_3 , MnO, MgO and P_2O_5 and might be due to the high proportion of clay minerals, rutile and Fe and Mn oxides. The negative F1 scores of SiO_2 and K_2O may be due to the relatively abundant quartz, K-feldspar and plagioclase. The positive F2 correlation between MgO and CaO probably reflects the abundance of smectite. The projection diagram F1–F2 shows three separate fields corresponding to the three mentioned geochemical groups. Based on the PCA, two groups of common clays are identified. The first group, with SiO_2 , Na_2O and K_2O , derives from felsic minerals (quartz, feldspar) through the weathering of granite or rhyolite. All the Foumban common clays, except some from Njimom and Koutaba, are weathered products of granites or rhyolites. The kaolinite and quartz contents support their relationship with acidic rocks (Velde & Meunier, 2008). The relatively high Fe_2O_3 and MnO contents in some samples from Koutaba and Njimom might relate their source to a mafic rock, like basalt.

TABLE 3. Chemical composition (wt.%) of clay materials from Fouban.

Sample	SiO ₂	TiO ₂	Al ₂ O ₃	Fe ₂ O ₃	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	LOI	S/A	CIA
Koutaba clays (S1)														
KB3f	58.20	2.59	17.93	8.82	0.02	0.22	0.16	0.06	1.20	0.15	0.00	9.47	3.25	92.69
KB3c	70.17	1.80	15.97	1.55	0.01	0.12	0.09	0.06	1.39	0.06	0.00	6.92	4.39	91.20
KF5c	52.27	2.10	25.97	2.65	0.01	0.28	0.16	0.12	0.57	0.16	0.00	14.16	2.01	96.82
KF5d	50.52	2.39	27.80	2.91	0.02	0.31	0.16	0.07	0.70	0.14	0.00	13.72	1.82	96.74
KF5e	57.35	2.59	22.53	2.65	0.03	0.27	0.09	0.04	1.13	0.14	0.00	11.67	2.55	94.67
KG2f	60.42	1.76	20.96	3.73	0.01	0.38	0.29	0.04	0.81	0.11	0.00	10.23	2.88	94.84
KG2c	58.87	1.33	19.22	4.03	0.01	0.62	0.62	0.14	0.97	0.06	0.00	12.95	3.06	91.74
KG2b	62.20	0.88	15.69	4.51	0.02	0.48	0.59	0.13	0.46	0.03	0.00	14.40	3.97	92.95
KC4f	47.73	1.20	26.86	3.50	0.01	0.39	0.45	0.10	0.43	0.16	0.00	17.84	1.78	96.49
KC4d	45.05	1.44	30.79	4.79	0.02	0.48	0.28	0.05	0.26	0.06	0.00	15.52	1.46	98.15
KC4b	46.16	1.39	30.65	3.69	0.02	0.40	0.22	0.02	0.28	0.07	0.00	16.07	1.51	98.31
KG3e	48.85	1.47	23.50	4.64	0.02	0.68	0.46	0.10	0.82	0.13	0.00	18.28	2.08	94.47
KG3c	49.12	1.67	25.77	5.21	0.02	0.66	0.51	0.09	0.72	0.08	0.00	15.25	1.91	95.12
KG3d	58.16	1.19	18.91	4.72	0.02	0.74	0.57	0.18	0.64	0.08	0.00	14.66	3.08	93.15
Bangourain clay (S2)														
BA2a	45.25	2.07	28.65	7.35	0.03	0.31	0.19	0.04	0.69	0.14	0.00	14.51	1.58	96.91
BA2b	47.25	2.54	22.97	10.88	0.05	0.36	0.23	0.09	1.02	0.36	0.00	13.62	2.06	94.51
KP11	56.23	1.30	23.38	3.80	0.03	0.31	0.18	0.11	1.30	0.18	0.00	12.61	2.40	93.64
KP12	58.83	1.39	22.64	2.56	0.01	0.19	0.15	0.06	0.92	0.12	0.00	11.71	2.60	95.23
Marom clays (S3)														
MA1e	71.07	0.64	14.49	1.54	0.01	0.30	0.62	1.51	6.10	0.04	0.00	2.77	4.91	63.80
MA3c	62.46	1.18	17.85	4.83	0.02	0.32	0.18	0.24	4.32	0.06	0.00	7.59	3.50	79.01
MA3b	59.89	1.54	19.92	4.11	0.01	0.49	0.34	0.47	3.94	0.05	0.00	8.19	3.01	80.75
MA2d	68.91	1.12	15.71	1.58	0.01	0.21	0.55	1.11	5.01	0.06	0.00	5.18	4.39	70.16
Njindare clays (S4)														
NJAb	63.19	1.28	19.18	3.81	0.01	0.19	0.08	0.09	2.42	0.09	0.00	8.92	3.29	88.11
NJAc	43.10	1.28	29.16	7.52	0.02	0.03	0.04	0.00	0.25	0.09	0.00	16.48	1.48	97.94
Njimom clays (S5)														
NJJ	40.63	1.42	32.46	8.52	0.02	0.52	0.05	0.00	0.85	0.25	0.00	14.43	1.25	97.30
NJR	40.36	3.40	30.04	4.13	0.02	0.32	0.08	0.00	0.12	0.10	0.00	14.48	1.34	99.34

CIA = Chemical index of alteration; S/A = SiO₂/Al₂O₃.

TABLE 4. Chemical composition ranges (%) of Foumban common clays compared with chemical compositions of other standard clays.

Sample	SiO ₂	TiO ₂	Al ₂ O ₃	Fe ₂ O ₃	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	LOI
Koutaba clays (N=14)	45–70	1–3	15–31	2–9	0.010–0.003	0.2–0.8	0.1–0.6	0.1–0.2	0.3–1.4	0.1–0.2	0	7–18
Bangourain clays (N=4)	45–58	1–2	22–29	3–11	0.01–0.05	0.2–0.4	0.1–0.2	0.0–0.1	0.7–1.3	0.10–0.04	0	12–15
Marom clays (N=4)	59–71	1–2	14–20	1–5	0.01–0.02	0.2–0.5	0.2–0.6	0.2–1.6	4–6	0.0–0.1	0	2–8
Njindare clays (N=2)	43–63	1–2	19–29	3–8	0.01–0.02	0.0–0.2	0.0–0.1	0.0–0.1	0.3–2.4	0.0–0.1	0	8–16
Njimom clays (N=2)	40–41	1–4	30–33	4–9	0.02	0.3–0.5	0.1	0	0.1–0.8	0.1–0.3	0	14
Fireclays ^d	56.30	1.6	25.50	3.19	–	0.30	0.74	0.11	2.1	–	–	9.8
Ball clays ^b	67.00	1.4	22.00	0.90	–	0.30	0.10	0.30	2.20	–	–	5.8
Italian clays ^c	42–63	0.6–1.0	11–21	4–7.5	–	0.7–3.9	0.2–16.0	0.7–1.2	1–3.6	0.2	–	6–19
French clays ^d	35–80	0.3–2.0	8–30	2–10	0–5	–	0.5–18.0	0.1–1.5	0.1–4.0	–	0–4	3–18

^aEtruria Marl Staffordshire (Ridgeway, 1982).

^bBall clays (Group 4 Devon; Watts Blake Bearne technical literature).

^cComposition range for the raw materials of fired bricks and tiles in France (Kormann & Ingénieurs du Centre Technique des Tuiles et Briques, 2005).

^dComposition range for the raw materials of fired bricks in Italy (Kormann & Ingénieurs du Centre Technique des Tuiles et Briques, 2005).

The TiO₂/Al₂O₃ binary diagram of Ekosse *et al.* (2001) was used to identify the source rocks of the clays (Fig. 7). The Foumban common clays dominantly indicate strong acidic affinities from rhyolitic or granitic source rocks with a minor basaltic component.

The major-element contents of the common clays were compared with those of average composition in the regional potential source rocks (*e.g.* Mekwene-Njimafofire Panafrican granitoids: Nzina *et al.*, 2010; Mount Mbapit rhyolite: Wandji *et al.*, 2008; Bamoun plateau Eocene basalts: Moundi *et al.*, 2007; and Njimom mylonite: Njonfang *et al.*, 1998). Granitic and basaltic rocks are easily and rapidly weathered to clay minerals and quartz with high rainfall and a warm climate on gentle slopes with a fluctuating water table and rapid water percolation (Murray & Keller, 1993). This is characteristic of the formation of the ferrallitic soils that cover the entire humid tropical zone (Tardy & Roquin, 1998). Kaolinite clays could have been chemically weathered from primary minerals, particularly feldspars. These weathered materials are further transported either to the river margins of Nkoup and Monoun for Koutaba and Bangourain, respectively, or to the bottom of the hill at Njindare and Marom, where significant amounts are accumulated. Smectite forms either from the chemical weathering of basalts or as a neof ormation product in environments with limited drainage. Illite comes from the transformation by aggradation of mica (Reeves *et al.*, 2006). The relatively high proportions of K-feldspars and plagioclase of Marom and some Njindare and Koutaba clay materials might be due to the moderate weathering of the source rocks, as observed in immature recent sediments (Israde-Alcántara *et al.*, 2008).

Suitability for ceramic products

The mineralogical association of Foumban clays, mainly represented by kaolinite, illite and quartz, is suitable for ceramic application. In ceramic building materials, kaolinite might provide sufficient strength, plasticity and refractoriness. Illite may promote the vitrification that is responsible for the densification of the final product, while quartz prevents cracking, shrinking and warping and also provides a uniform shape to the final product (Rajput, 2004). The presence of a relatively large smectite content (>5%) limits the application of some Koutaba clays for ceramic building materials.

Figure 8 suggests three main areas for the clay materials studied: (1) the quartz-rich field (sample MA1e with 71.07 wt.% SiO₂); (2) the average quartz-

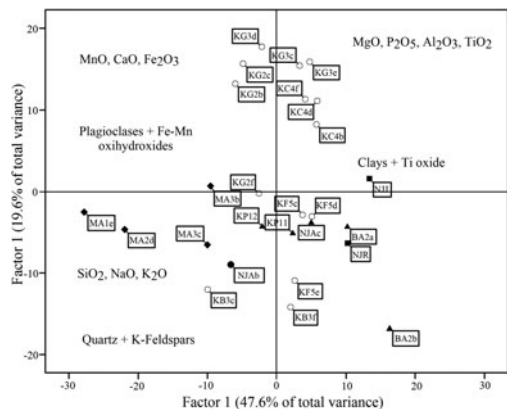


FIG. 6. Principal component analysis diagram of the geochemical data from the studied clays.

rich field (Marom samples MA3c, MA3b and MA2d and sample KB3c from Koutaba); (3) and the clay-rich field (most samples from Koutaba, Bangourain, Njindare and Njimom). In view of the very high sand content of sample MA1e, sintering might occur in the temperature range of fired bricks and tiles (850–1050°C). Therefore, it might be preferable to use this sample as a degreaser for ceramic pastes. The remaining samples from Marom (MA3c, MA3b and MA2d) have relatively low contents of clay minerals, suggesting more porous matrices, and therefore they may not be suitable for tiles and fired bricks. Their iron oxides content (1.58–4.83%) and alkalis (3.94–5.01%) is an indication of their sintering temperature, which should be relatively low (*cf.* thermal analysis curves). Samples from Koutaba, Bangourain, Njindare and Njimom are very rich in clay minerals. Apart from

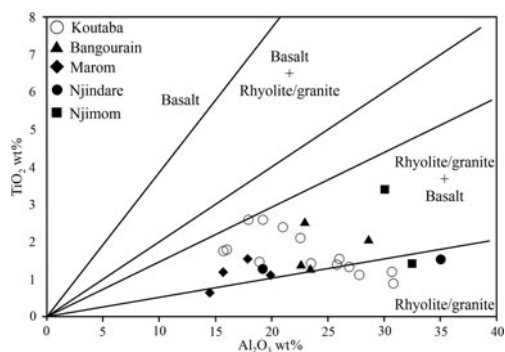


FIG. 7. Projection of studied samples on the TiO_2/Al_2O_3 binary diagram (after Ekosse *et al.*, 2001).

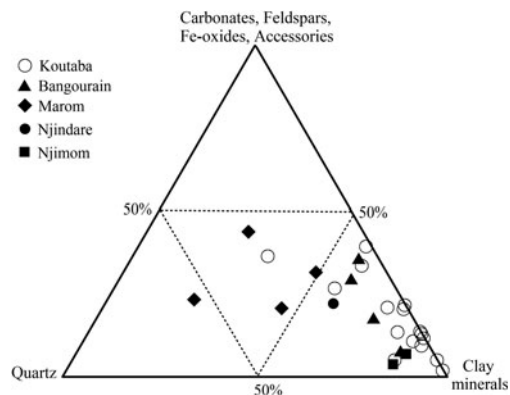


FIG. 8. Ternary diagram: quartz/carbonates + Fe-oxides + accessories + feldspars/clay minerals for the Fouban common clays, after Fiori *et al.* (1989).

samples KF5c, KF5d, KC4f, KC4d, KC4b, NJAc, NJJ and NJR, the iron oxides content and alkali elements is generally ≥ 10 wt.%, which guarantees a low vitrification temperature and a low porosity. Indeed, the presence of Fe in clay minerals is generally associated with octahedral and even tetrahedral substitution, which affects the structure and degree of crystal order, favouring a low sintering temperature. Those of the samples that have a percentage of $Al_2O_3 \geq 25$ wt.% with a low Fe content and alkali elements might be suitable for refractories. This interpretation is in line with the mineralogy and the thermal properties of the clay materials studied.

Table 4 shows the chemical composition of the studied samples in comparison with the composition range of clay materials used in fired bricks and tiles in France and Italy (Kornmann & Ingéieurs du Centre Technique des Tuiles et Briques, 2005). The chemical compositions of the studied clays are within the range limits for French bricks and tiles. However, the proportions of SiO_2 in some Marom and Koutaba clays are higher than those used for Italian bricks. The composition of Njimom clays and some Koutaba clays is close to that used for sanitary ware and Al–Si refractories. They might be used after removal of TiO_2 and Fe_2O_3 (Murray & Keller, 1993). The relatively high Fe content ($>1\%$) in most of the studied clays suggests a light to red colour of fired products. The alkali and alkaline earth contents are responsible for the vitrification and therefore the ability to provide sufficient porosity, permeability and mechanical strength. Figure 9 compares the bulk major-element composition of Fouban common clays with those used for red stoneware in Italy and white stoneware in

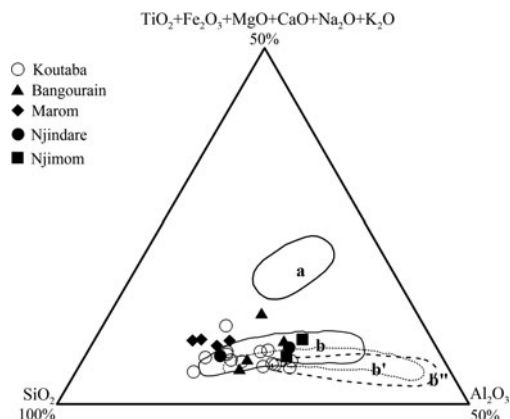


FIG. 9. Ternary diagram of Foumban clays: $\text{SiO}_2/\text{Al}_2\text{O}_3$ /other oxides. a = red stoneware (Italy); b, b', b'' = white stoneware for German, English and French industries, respectively (data are from Fabbri & Fiori, 1985).

German, English and French industries, as given in the ternary diagram for $\text{SiO}_2\text{--Al}_2\text{O}_3\text{--remaining oxides}$ proposed by Fabbri & Fiori (1985). In this diagram, all clays lie out of the red stoneware field and most studied clays plot in the white body field. Some Koutaba and Bangourain clays have very low SiO_2 contents in comparison with the optimal value for any white body products (*i.e.* 72 wt.%; Fiori *et al.*, 1989). Those samples require addition of SiO_2 for application in white bodies.

CONCLUSIONS

The Foumban area, Cameroon, was surveyed in order to locate, characterize and determine the genesis of clayey materials with the principal objective of evaluating their potential for use in ceramic industries. The Foumban common clays occur as grey, grey-brown, grey-greenish to dark grey, brownish, mottled clays dominated by the clay size fractions. Most of these materials are alluvial clays formed by weathering, transport and accumulation at the lower part of the landscape. They are composed of kaolinite, illite, smectite and chlorite, with minor quartz, K-feldspars, plagioclase, goethite and traces of rutile and hematite. Kaolinite dominates the $<2\ \mu\text{m}$ fractions. Geochemical data suggest felsic rocks as the main parent rocks for common clays from Foumban. Based on their mineralogical and geochemical characteristics, they might be suitable for ceramic products. The proportion of alkali and alkaline earth elements in Marom clays (6–9%) would enable lower firing temperatures. Some Bangourain clays with high Fe_2O_3 contents ($>11\ \text{wt.}\%$)

might require processing prior to use. In addition, clays with $>25\ \text{wt.}\%$ Al_2O_3 might be suitable as fireclays after beneficiation.

ACKNOWLEDGMENTS

This study was carried out within the framework of a research and development project funded by ARES-CCD/PRD 'Caractérisation et valorisation des Matériaux Argileux de Foumban (Ouest-Cameroun) – MAFO' of the Académie de Recherche et d'Enseignement Supérieur (ARES-CCD), Belgium. The authors are grateful to this institution for financial support.

REFERENCES

- Boski T., Pessoa J., Pedro P., Thorez J., Dias J.M.A. & Hall I.R. (1998) Factors governing abundance of hydrolysable amino acids in the sediments from the N.W. European Continental Margin (47–50°N). *Progress in Oceanography*, **42**, 145–164.
- Cailleux A. (1992) *Notice sur le Code des Couleurs des Sols*. Boubée, Paris, France.
- Cases J.M., Lietard O., Yvon J. & Delon J.F. (1982) Etude des propriétés cristallographiques, morphologiques et superficielles de la kaolinite désordonnée. *Bulletin Minéralogie*, **105**, 439–457.
- Christidis G.E. (2011) Industrial clays. Pp. 341–414 in: *Advances in the Characterization of Industrial Minerals* (G.E. Christidis, editor). EMU Notes in Mineralogy, **9**. Mineralogical Society, London, UK.
- Cook H.E., Johnson P.D., Matti J.C. & Zemmels I. (1975) Methods of sample preparation and X-ray diffraction analysis in X-ray mineralogy laboratory. Pp. 997–1007 in: *Initial Report DSDP XXVIII* (A.G. Kaneps *et al.*, editor). Printing Office, Washington, DC.
- Daoudi L., Elboudour Elidrissi H., Saadi L., Albazane A., Bennazha J., Waquif M., Elouahabi M. & Fagel N. (2014) Characteristics and ceramic properties of clayey materials from Amezmiz region (Western High Atlas, Morocco). *Applied Clay Science*, **102**, 139–147.
- Diko M.L., Ekosse G.E., Ayonghe S.N. & Ntasin E.B. (2011) Physical characterization of clayey materials from tertiary volcanic cones in Limbe (Cameroon) for ceramic applications. *Applied Clay Science*, **51**(3), 380–384.
- Djangang C.N., Elimbi A., Lecomte G.L., Nkoumbou C., Soro J., Blanchart P., Bonnet J.P. & Njopwouo D. (2008a) Sintering of clay-chamotte ceramic composites for refractory bricks. *Ceramic International*, **34**(5), 1207–1213.
- Djangang C.N., Elimbi A., Lecomte G.L., Soro J., Nkoumbou C., Yvon J., Blanchart P. & Njopwouo D. (2008b) Refractory ceramics from

- clays of Mayouom and Mvan in Cameroon. *Applied Clay Science*, **39**(1–2), 10–18.
- Djangang C.N., Elimbi A., Melo U.C., Nkoumbou C., Lecomte G., Yvon J., Bonnet J.P. & Njopwouo D. (2007) Characteristics and ceramic properties of clays from Mayouom deposit (west Cameroon). *Industrial Ceramics*, **27**(2), 79–88.
- Dondi M., Raimondo M. & Zanelli C. (2014) Clays and bodies for ceramic tiles: reappraisal and technological classification. *Applied Clay Science*, **96**, 91–109.
- Ekosse G. (2001) Provenance of the Kgwakgwa kaolin deposit in south eastern Botswana and its possible utilization. *Applied Clay Science*, **20**, 137–152.
- Ekosse G.E. (2010) Kaolin deposits and occurrences in Africa: geology, mineralogy and utilization. *Applied Clay Science*, **50**(2), 212–236.
- Elimbi A. & Njopwouo D. (2002) Firing characteristics of ceramics from the Bomkoul kaolinitic clay deposit (Cameroon). *Tile & Brick International*, **18**(6), 364–369.
- Elimbi A., Yeugouo E., Nenwa J., Liboum & Njopwouo D. (2003) Caractérisations chimiques et minéralogiques de deux matériaux du gisement argileux de Bakong (Cameroon). *African Journal of Material and Minerals*, **6**(1), 13–19.
- Fabbri B. & Fiori C. (1985) Clays and complementary raw materials for stoneware tiles. *Mineralogica & Petrographica Acta*, **29A**, 535–545.
- Fadil-Djenabou S., Ndjigui P.D. & Mbey J.A. (2014) Mineralogical and physicochemical characterization of Ngaye alluvial clays (northern Cameroon) and assessment of its suitability in ceramic production. *Journal of Asian Ceramic Society*, **3**, 50–58.
- Fialpis C.I., Petit S. & Decarreau A. (1999) Hydrothermal formation of kaolinite from various metakaolins. *Clay Minerals*, **35**, 559–572.
- Fiori C., Fabbri B., Donati F. & Venturi I. (1989) Mineralogical composition of the clay bodies used in the Italian tiles industry. *Applied Clay Science*, **4**, 461–473.
- Goldberg K. & Humayun M. (2010) The applicability of the Chemical Index of Alteration as a paleoclimatic indicator: an example from the Permian of the Paraná Basin, Brazil. *Palaeogeography, Palaeoclimatology, Palaeoecology*, **293**, 175–183.
- Israde-Alcántara I., Robles-Camacho J. & Domínguez J.M. (2008) Beidellite-nontronite clays in Neogene sediments from Cuitzeo-Charo lacustrine basin Michoacán, México. Geological setting and paleoenvironmental implications. *Boletín de la Sociedad Geológica Mexicana*, **60**(2), 159–171.
- Kamseu E., Leonelli C., Boccaccini D.N., Veronesi P., Miselli P., Pellacani G. & Melo U.C. (2007) Characterization of porcelain compositions using two china clays from Cameroon. *Ceramic International*, **33**(5), 851–857.
- Kornmann M. & Ingénieurs du Centre Technique des Tuiles et Briques (2005) *Matériaux de Construction en Terre Cuite, Fabrication et Propriétés*. Pp. 33–34. Editions Septima, Paris, France.
- Ligas P., Vras I., Dondi M. & Marsigli M. (1997) Kaolinitic materials from Romana (north-west Sardinia, Italy) and their ceramic properties. *Applied Clay Science*, **12**, 145–163.
- Mackenzie R.C. (1957) *The Differential Thermal Investigation of Clays*. Mineralogical Society, London, UK.
- Manning D.A.C. (1995) *Introduction to Industrial Minerals*. Chapman & Hall, London, UK.
- Moore D. & Reynolds R.C., Jr (1997) *X-Ray Diffraction and the Identification and Analysis of Clay Minerals*. 2nd ed. Oxford University Press, Oxford, UK.
- Moundi A., Wandji P., Bardintzeff J.M., Menard J.J., Okomo Atouba L.S., Mouncherou O.F., Reusser E., Bellon H. & Tchoua F.M. (2007) Les basaltes éocènes à affinité transitionnelle du Plateau Bamoun, témoin d'un réservoir mantellique enrichi sous la ligne volcanique du Cameroun. *Comptes Rendus Géoscience*, **339**, 396–406.
- Moundi A., Ménard J.J., Reusser E., Tchoua F.M. & Dietrich V.J. (1996) Découverte de basaltes transitionnels dans le secteur continental de la Ligne du Cameroun (Massif du Mbam, Ouest Cameroun). *Comptes Rendus Académie des Sciences, Paris*, **322**, 831–837.
- Moundi A., Wandji P., Ghogomu R.T., Bardintzeff J.M., Njilah I.K., Fouboure I., Ntieche B. (2009) Existence of quaternary ankaramites among Tertiary floods basalts at Koutaba (Bamoun Plateau, western Cameroon): petrology and isotope data. *Review of the Bulgarian Geological Society*, **70**, 115–124.
- Murray H.H. & Keller W.D. (1993) Kaolins, kaolins and kaolins. Pp. 1–24 in: *Kaolin Genesis and Utilization* (H. Murray, W. Bundy & C. Harvey, editors). Clay Minerals Society Special Publication **1**, Chantilly, VA, USA.
- Ndjigui P.D., Ebah Abeng S.A., Ekomané E., Nzeukou N. A., Ngo Mandeng F.S. & Lindjeck M.M. (2015) Mineralogy and geochemistry of pseudogley soils and recent alluvial clastic sediments in the Ngog-Lituba region, southern Cameroon: an implication to their genesis. *Journal of African Earth Sciences*, **108**, 1–14.
- Ndjigui P.D., Mbey J.A. & Nzeukou N.A. (2016) Mineralogical, physical and mechanical features of ceramic products of the alluvial clastic clays from the Ngog-Lituba region, southern Cameroon. *Journal of Building Engineering*, **5**, 151–157.
- Nesbitt H.W. & Young G.M. (1984) Prediction of some weathering trends of plutonic and volcanic rocks based on thermodynamic and kinetic considerations. *Geochimica et Cosmochimica Acta*, **48**, 1523–1534.
- Ngon Ngon G.F., Yongue-Fouateu R., Bitom D.L. & Bilong P. (2009) A geological study of clayey laterite

- and clayey hydromorphic material of the region of Yaoundé (Cameroon): a prerequisite for local material promotion. *Journal of African Earth Sciences*, **55**, 69–78.
- Ngon Ngon G.F., Etame J., Ntamak-Nida M.J., Mbog M. B., Maliengoue Mpondo A.M., Yongue-Fouateu R. & Bilong P. (2012) Geological study of sedimentary clayey materials of the Bomkoul area in the Douala region (Douala sub-basin, Cameroon) for the ceramic industry. *Comptes Rendus Geoscience*, **344**, 366–376.
- Njonfang E., Moreau C. & Tchoua M.F. (1998) La bande mylonitique Foumban-Bankim, Ouest-Cameroun. *Une zone de cisaillement de haute température*. Comptes Rendus Académie des Sciences, Paris, **327**, 735–741.
- Njonfang E., Nono A., Kamgang P., Ngako V. & Tchoua M. F. (2011) Cameroon Volcanic Line alkaline magmatism (central Africa): a reappraisal. Pp. 173–191 in: *Volcanism and Evolution of the African Lithosphere*, The Geological Society of America Special Papers 478 (L. Becaluva, G.B. Bianchini & M. Wilson, editors). Geological Society of America, Boulder, CO, USA.
- Njoya A., Nkoumbou C., Grosbois C., Njopwouo D., Njoya D., Courtin N.A., Yvon J. & Martin F. (2006) Genesis of Mayouom kaolin deposit (west Cameroon). *Applied Clay Science*, **32**, 125–140.
- Nkalih Mefire A., Njoya A., Yongue Fouateu R., Tapon Nsandamoun A., Nzeukou Nzeugang A., Mache J.R., Siniapkin S., Flament P., Melo Chinje. U., Ngono A. & Fagel N. (2015) Kaolin occurrence in Koutaba (west-Cameroon): mineralogical and physicochemical characterization for ceramic products. *Clay Minerals*, **50**, 593–606.
- Nkoumbou C., Villiéras F., Barres O., Bihannic I., Pelletier M., Razafitianamaharavo A., Metang V., Yonta Ngoune C., Njopwouo D. & Yvon J. (2008) Physicochemical properties of talc ore from Pout-Kelle and Memel deposits (central Cameroon). *Clay Minerals*, **43**(2), 317–337.
- Nkoumbou C., Njoya A., Njoya D., Grosbois C., Njopwouo D., Yvon J. & Martin F. (2009) Kaolin from Mayouom (Western Cameroon): industrial suitability evaluation. *Applied Clay Science*, **43**, 118–124.
- Nzeukou N.A., Fagel N., Njoya A., Beyala Kamgang V., Eko Medjo R. & Chinje Melo U. (2013) Mineralogical and physico-chemical properties of alluvial clays from Sanaga valley (Center, Cameroon): suitably for ceramic application. *Applied Clay Science*, **83–84**, 238–243.
- Nzeukou A., Traina K., Medjo E.R., Kamseu E., Njoya A., Melo U.C., Kamgang B.V., Cloots R. & Fagel N. (2014) Mineralogical and physical changes during sintering of plastic red clays from Sanaga Swampy Valley, Cameroon. *Inter陶瓷*, **63**, 186–192.
- Nzina C.A., Nzenti J.P., Njiosseu Tanko E.L., Ganno S. & Ngotue T. (2010) Synkinematic ferro-potassic magmatism from the Mekwene-Njimafofire Foumban Massif, along the Foumban-Banyo shear zone in central domain of Cameroon Pan-African fold belt. *Journal of Geology and Mining Research*, **2**(6), 142–158.
- Okomo Atouba L., Chazot G., Moundi A., Agranier A., Bellon H., Nonmotte P., Nzenti J.P. & Kankeu B. (2016) Mantle sources beneath the Cameroon Volcanic Line: geochemistry and geochronology of the Bamoun plateau mafic rocks. *Arabian Journal of Geoscience*, **9**, 270.
- Pialy P., Tessier Doyen N., Njopwouo D. & Bonnet J.P. (2009) Effects of densification and mullitization on the evolution of the elastic properties of a clay-based material during firing. *Journal of the European Ceramic Society*, **29**, 1579–1586.
- Rajput R.K. (2004) *Engineering Materials*. S. Chand and Company Ltd, New Delhi, India.
- Reeves G.M., Sims I. & Cripps C. (2006) *Clay Materials Used in Construction*. Engineering Geology Special Publication, 21. Geological Society, London, UK.
- Ridgeway J.M. (1982) *Common Clay and Shale*. Mineral Resources Consultative Committee, Mineral Dossier, 22. HMOS, London, UK.
- Segalen P. (1967) Les sols de la vallée du Noun. *Cahier ORSTOM, Série Pédologie*, **V**(3), 287–345.
- Tardy Y. & Roquin C. (1998) *Dérive des Continents, Paléoclimats et Altérations Tropicales*. Edition BRGM, Orléans, France.
- Tassongwa B., Nkoumbou C., Njoya D., Njoya A., Tchop J.L., Yvon J. & Njopwouo D. (2014) Geochemical and mineralogical characteristics of the Mayouom kaolin deposit, west Cameroon. *Earth Science Research*, **3**(1), 94–107.
- Velde B. & Meunier A. (2008) *The Origin of Clays Minerals in Soils and Weathered Rocks*. Springer Verlag, Berlin, Germany.
- Vieira C.M.F. & Sanchez Monteiro R.S.N. (2008) Characteristics of clays and properties of building ceramics in the state of Rio de Janeiro, Brazil. *Construction and Building Materials*, **22**, 781–787.
- Wandji P. (1995) *Le Volcanisme Récent de la Plaine du Noun (Ouest Cameroun)*. *Volcanologie, Pétrologie, Géochimie et Pouzzolanité*. State doctoral thesis, Université Yaoundé I, Yaoundé, Cameroon.
- Wandji P., Tchokona Seuui D., Bardintzeff J.-M., Bellon H. & Platevo B. (2008) Rhyolites of the Mbepit Massif in the Cameroon Volcanic Line: an early extrusive volcanic episode of Eocene age. *Mineralogy and Petrology*, **94**, 271–286.
- Weecksteen G. (1957) *Carte Géologique de Reconnaissance au 1/500 000, Feuille Douala-Est avec Notice Explicative*. Direction Mines Géologie du Cameroon.
- Wilson M.J. (1998) The origin and formation of clay minerals in soils: past, present and future perspectives. *Clay Minerals*, **34**, 7–25.