
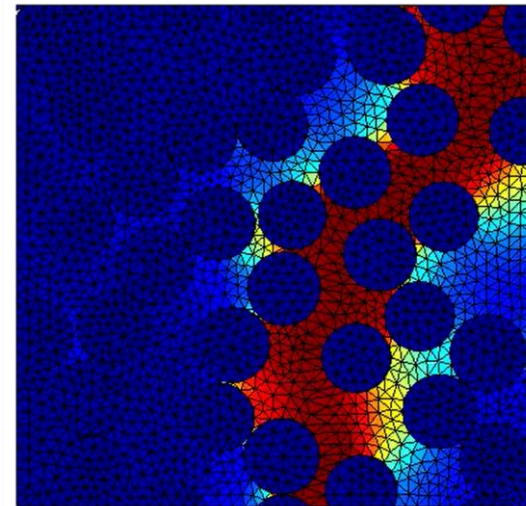



Generation of unidirectional composite SVEs from micro-structural statistical information


*Wu Ling, Bidaine Benoit, Major Zoltan,
Nghia Chnug Chi, Noels Ludovic*

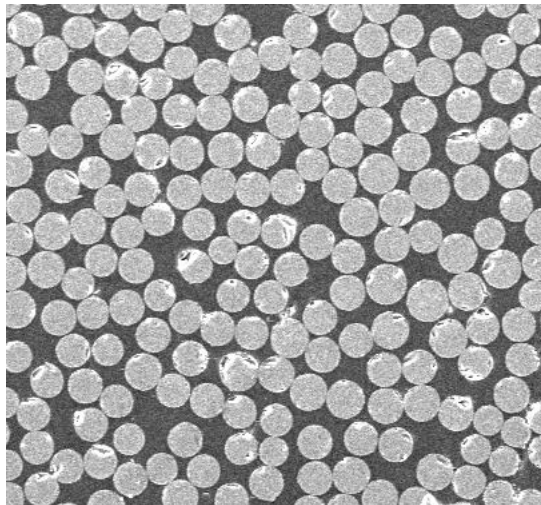

The research has been funded by the Walloon Region under the agreement no 1410246-STOMMMAC (CT-INT 2013-03-28) in the context of the M-ERA.NET Joint Call 2014.




The problem

- Material uncertainties affect structural behaviors

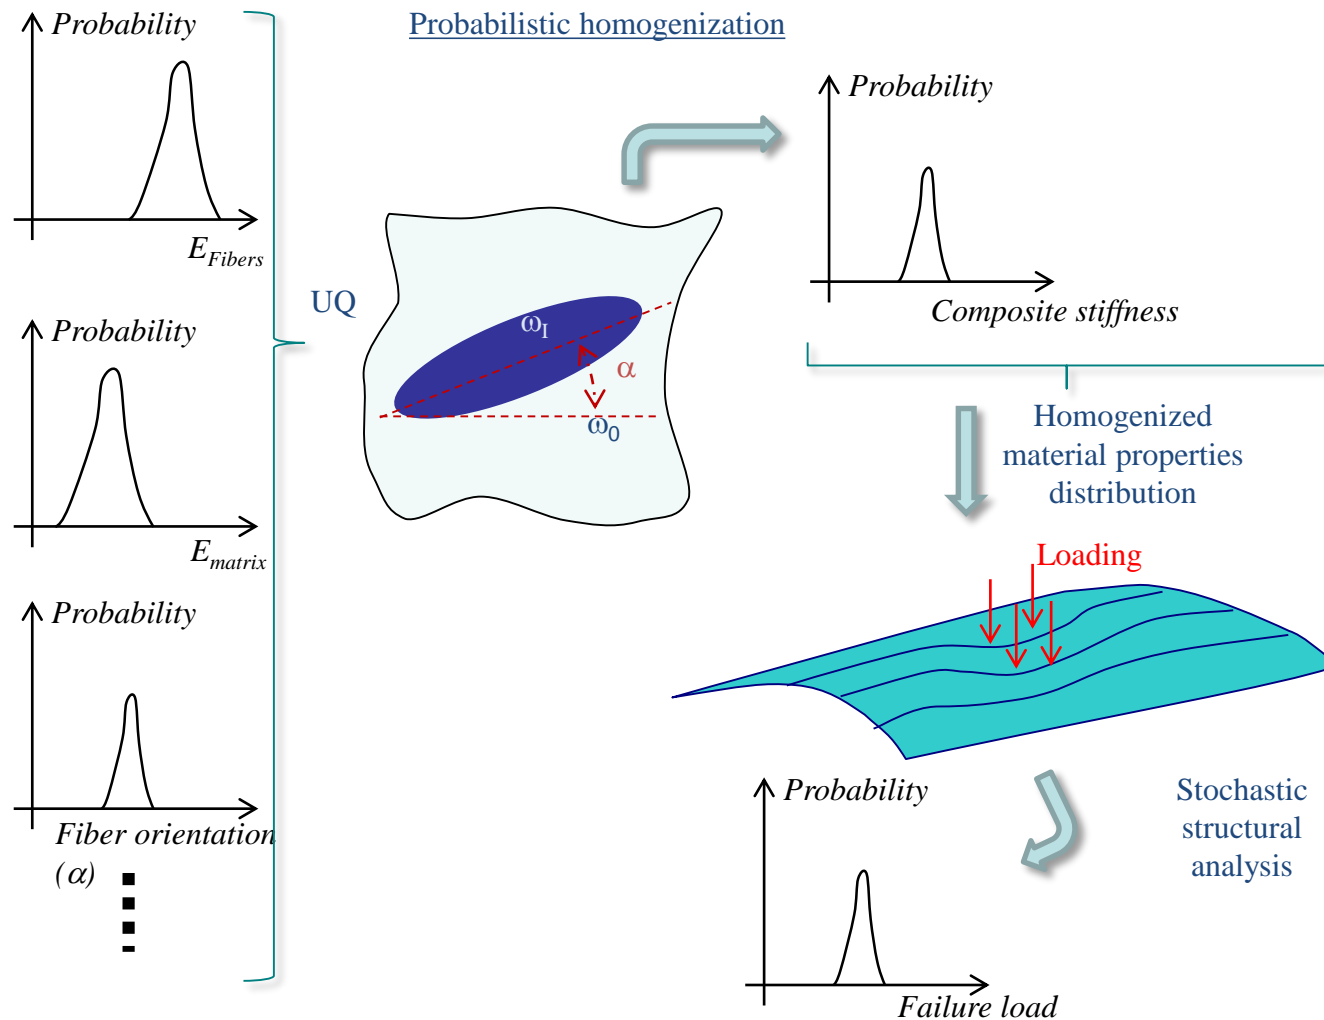

The problem


- Illustration assuming a regular stacking
 - 60%-UD fibers
 - Damage-enhanced matrix behavior

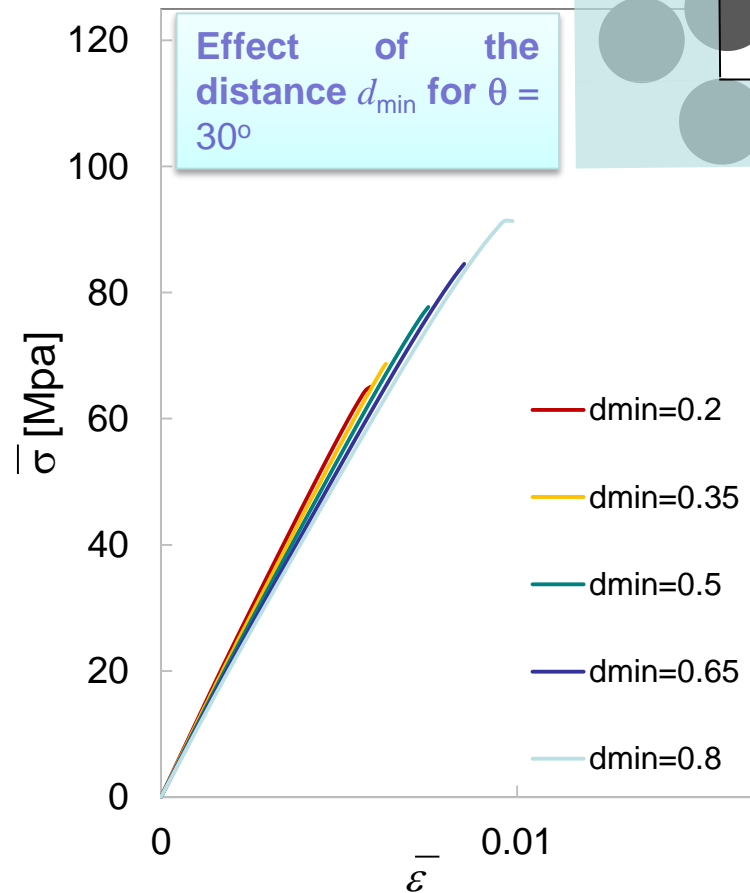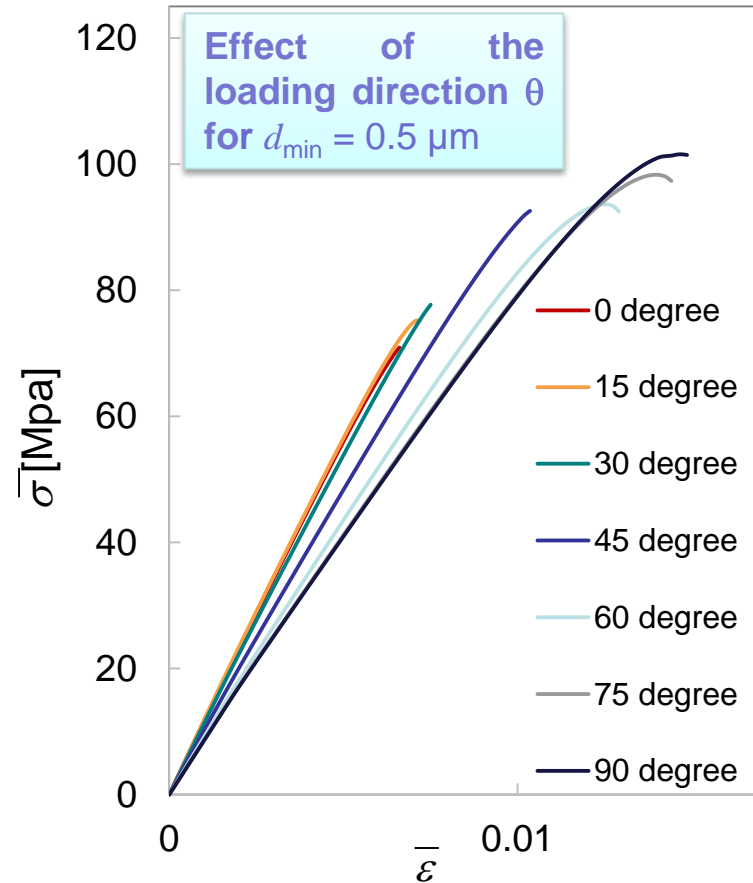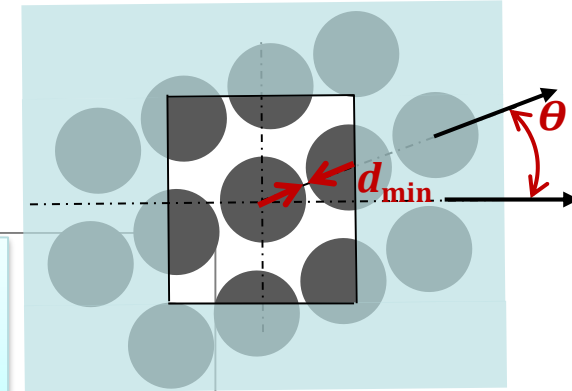


- Question: what does happen for a realistic fibre stacking?

Experimental measurements


- 2000x and 3000x SEM images

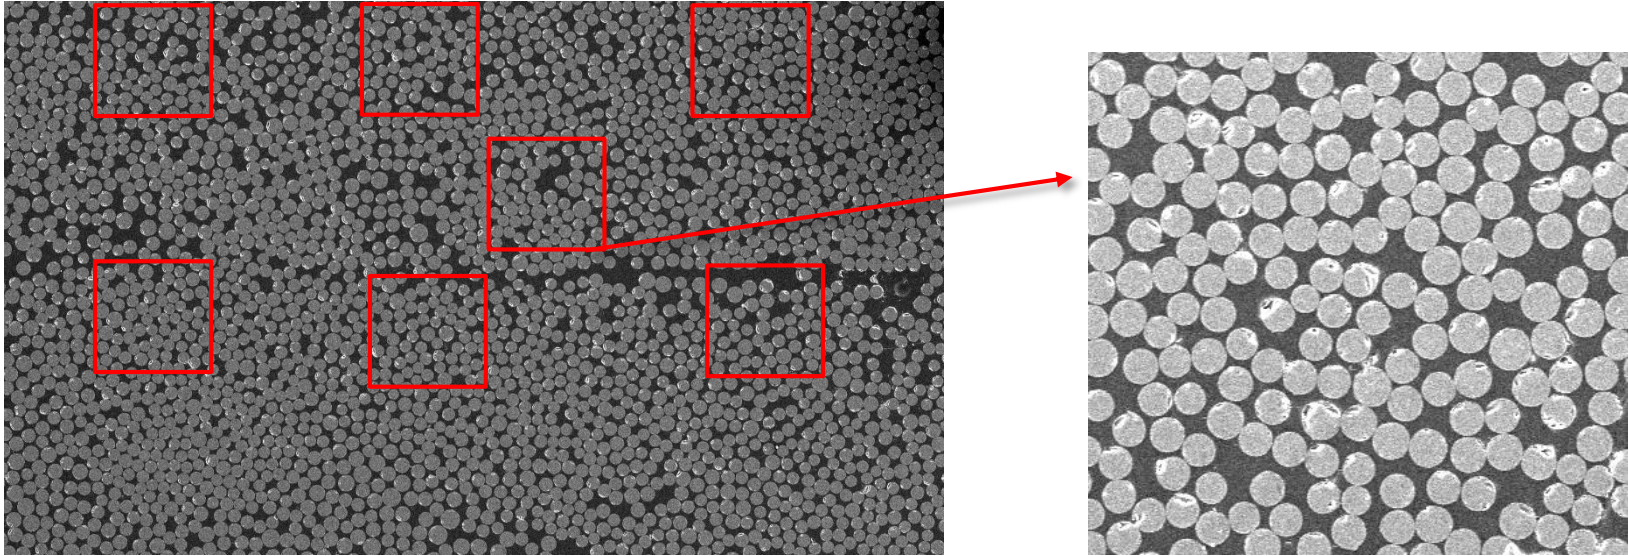





- Fibers detection

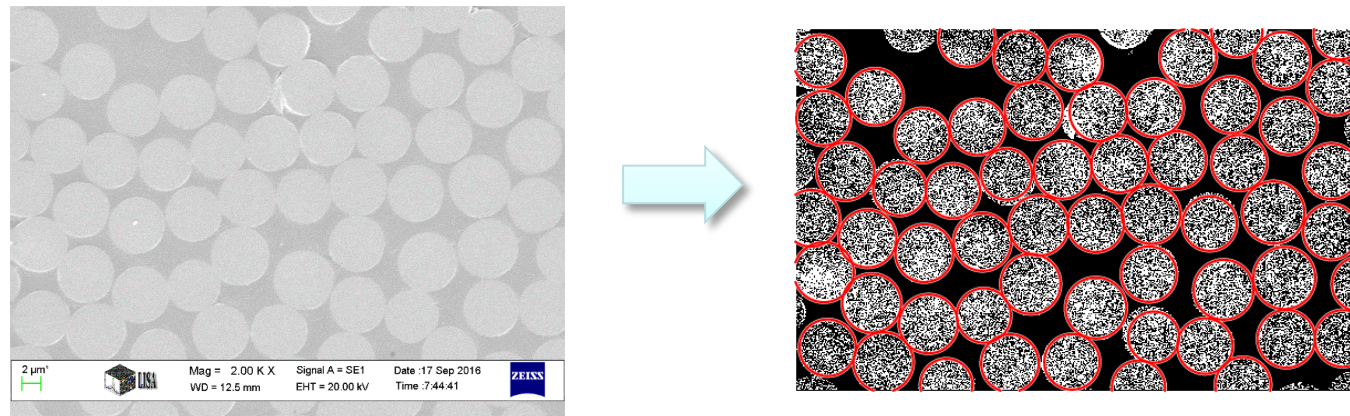

- Basic geometric information of fibers' cross sections
 - Fiber radius distribution $p_R(r)$
- Basic spatial information of fibers
 - The distribution of the nearest-neighbor net distance function $p_{d_{1st}}(d)$
 - The distribution of the orientation of the undirected line connecting the center points of a fiber to its nearest neighbor $p_{\vartheta_{1st}}(\theta)$
 - The distribution of the difference between the net distance to the second and the first nearest-neighbor $p_{\Delta d}(d)$ with $\Delta d = d_{2nd} - d_{1st}$
 - The distribution of the second nearest-neighbor's location referring to the first nearest-neighbor $p_{\Delta\vartheta}(\theta)$ with $\Delta\vartheta = \vartheta_{2nd} - \vartheta_{1st}$

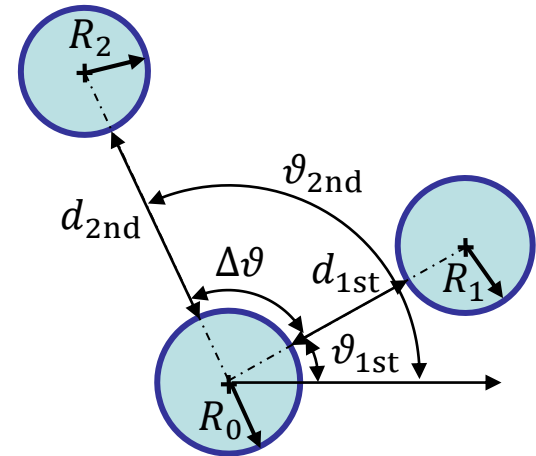


- Histograms of random micro-structures' descriptors

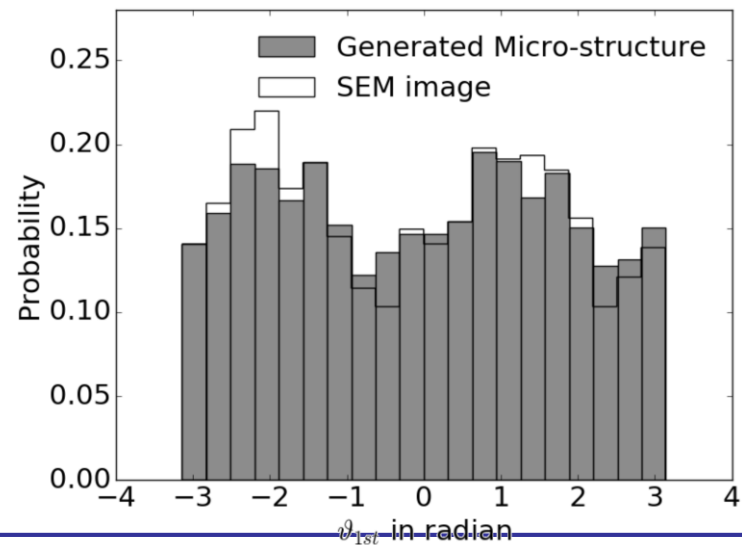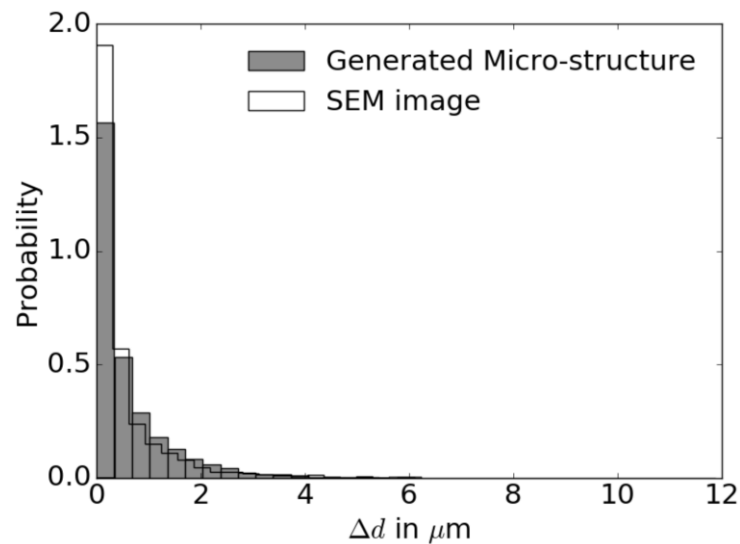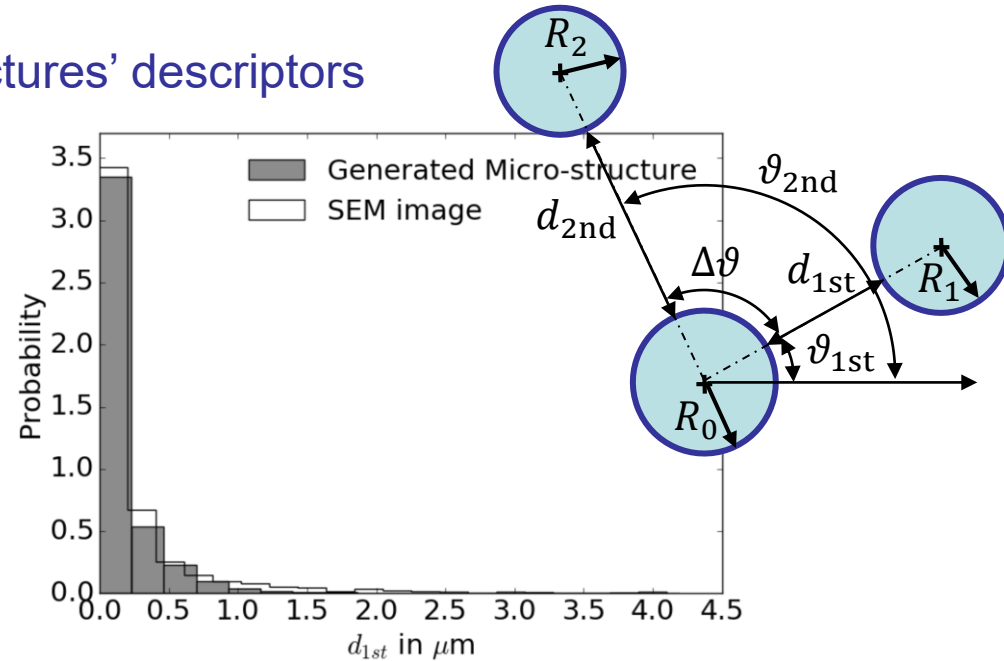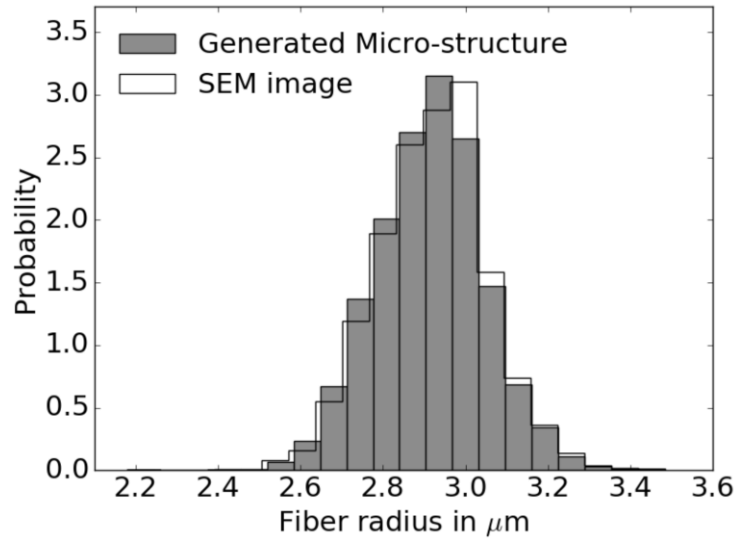

Micro-structure stochastic model

- Dependency of the four random variables $d_{1st}, \Delta d, \vartheta_{1st}, \Delta\vartheta$
- Correlation matrix

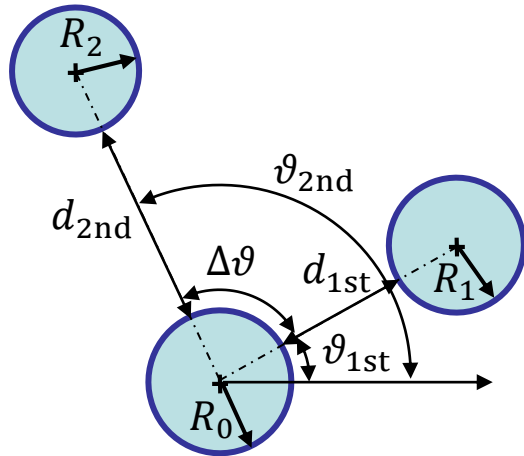

| | d_{1st} | Δd | ϑ_{1st} | $\Delta\vartheta$ |
|-------------------|-----------|------------|-------------------|-------------------|
| d_{1st} | 1.0 | 0.21 | 0.01 | 0.02 |
| Δd | | 1.0 | 0.002 | -0.005 |
| ϑ_{1st} | | | 1.0 | 0.02 |
| $\Delta\vartheta$ | | | | 1.0 |

- Distances correlation matrix

d_{1st} and Δd are dependent they will be generated from their empirical copula



| | d_{1st} | Δd | ϑ_{1st} | $\Delta\vartheta$ |
|-------------------|-----------|------------|-------------------|-------------------|
| d_{1st} | 1.0 | 0.27 | 0.04 | 0.08 |
| Δd | | 1.0 | 0.05 | 0.06 |
| ϑ_{1st} | | | 1.0 | 0.05 |
| $\Delta\vartheta$ | | | | 1.0 |

Micro-structure stochastic model



- d_{1st} and Δd should be generated using their empirical copula

SEM sample

Generated sample

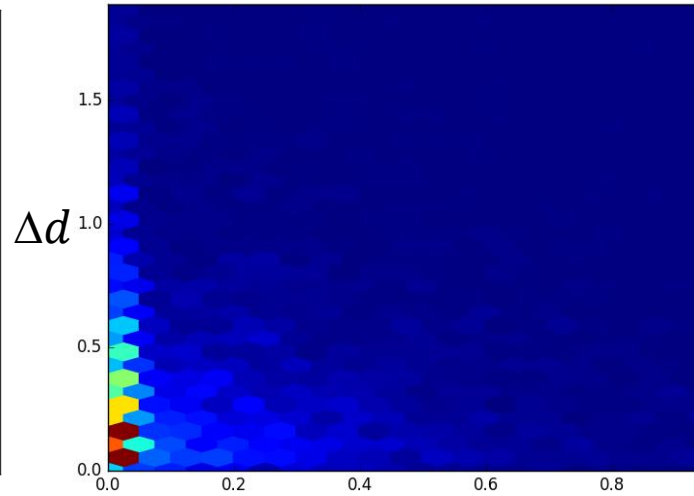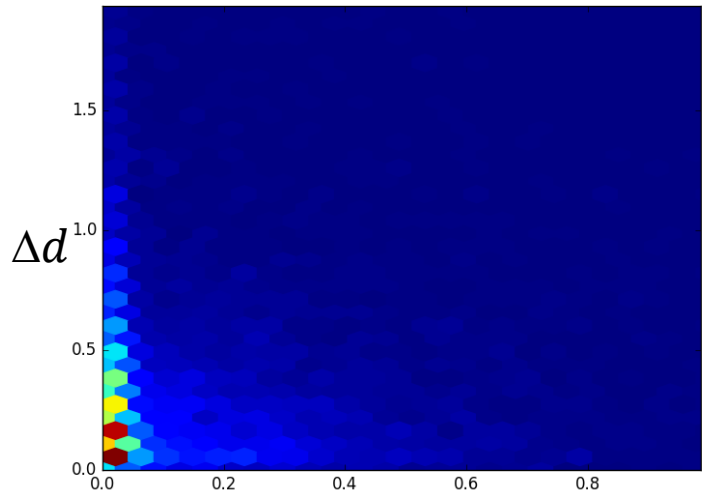


Directly from
copula generator

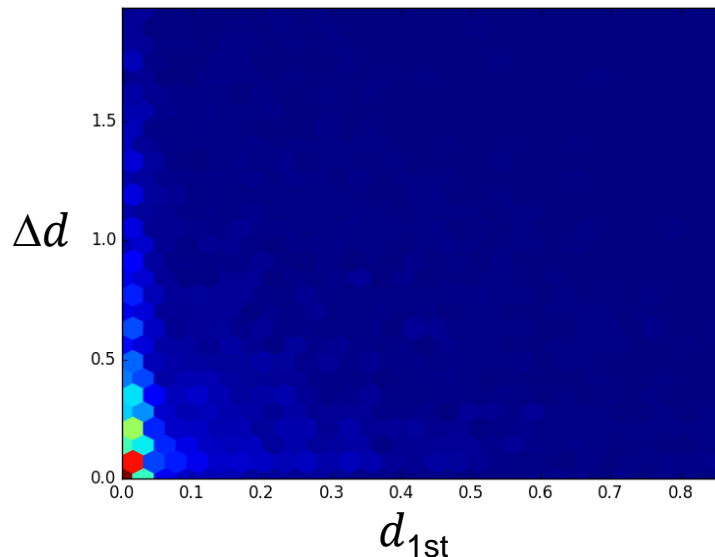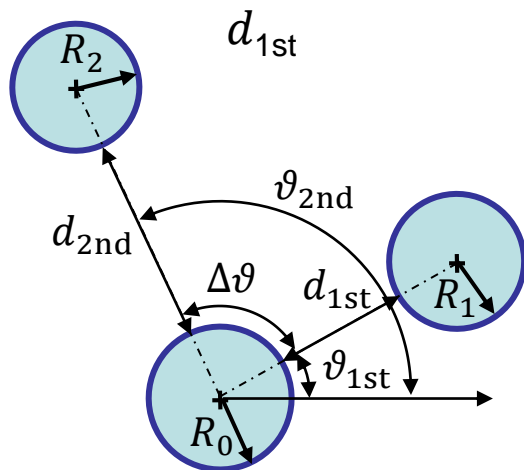


Statistic result from
generated SVE

- The numerical micro-structure is generated by a fiber additive process
 - 1) Define N seeds with first and second neighbors distances

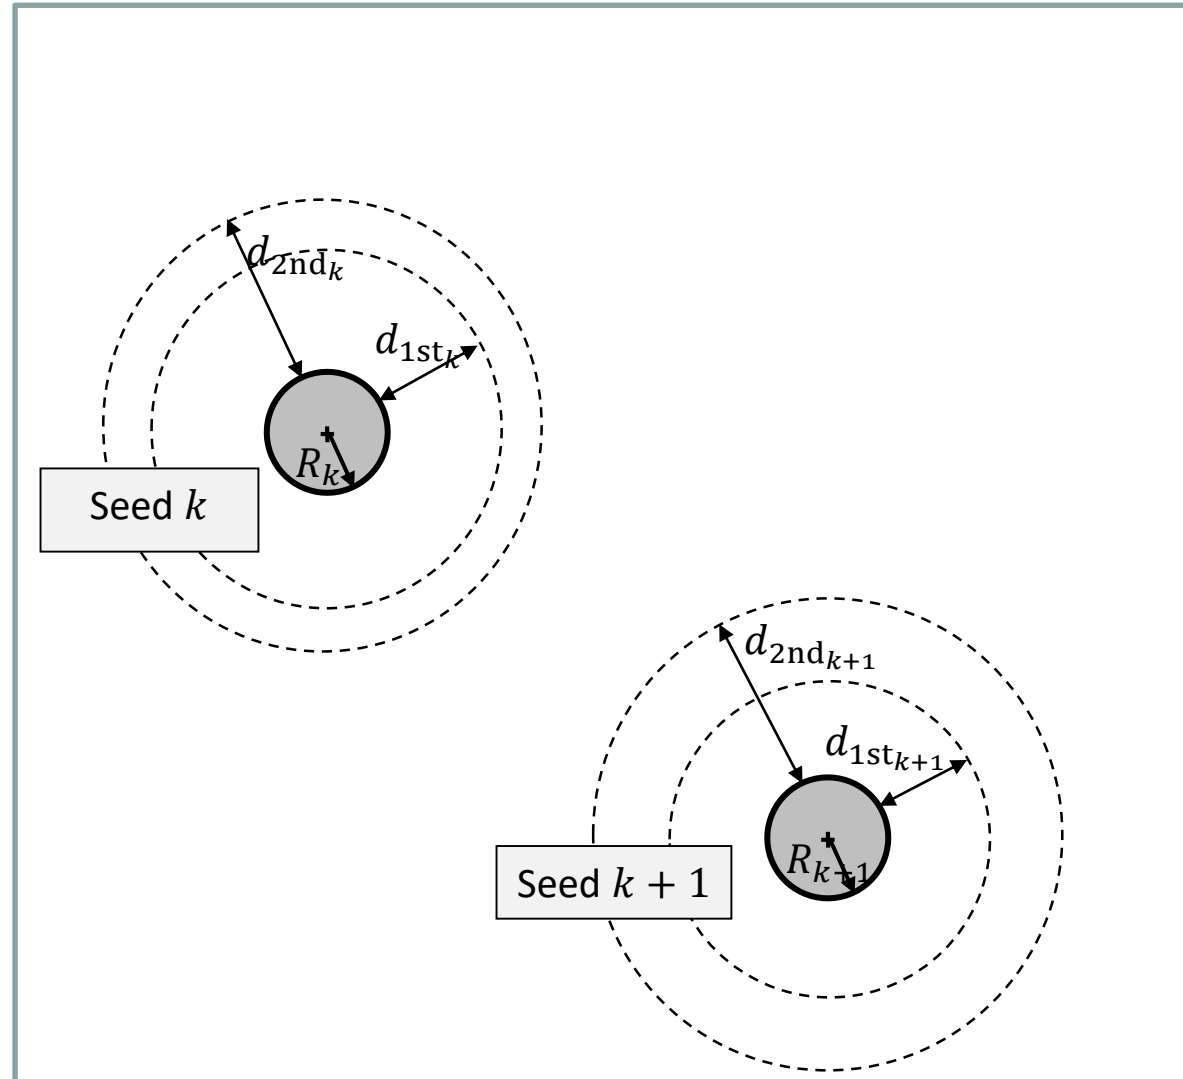


- The numerical micro-structure is generated by a fiber additive process

- 1) Define N seeds with first and second neighbors distances
- 2) Generate first neighbor with its own first and second neighbors distances

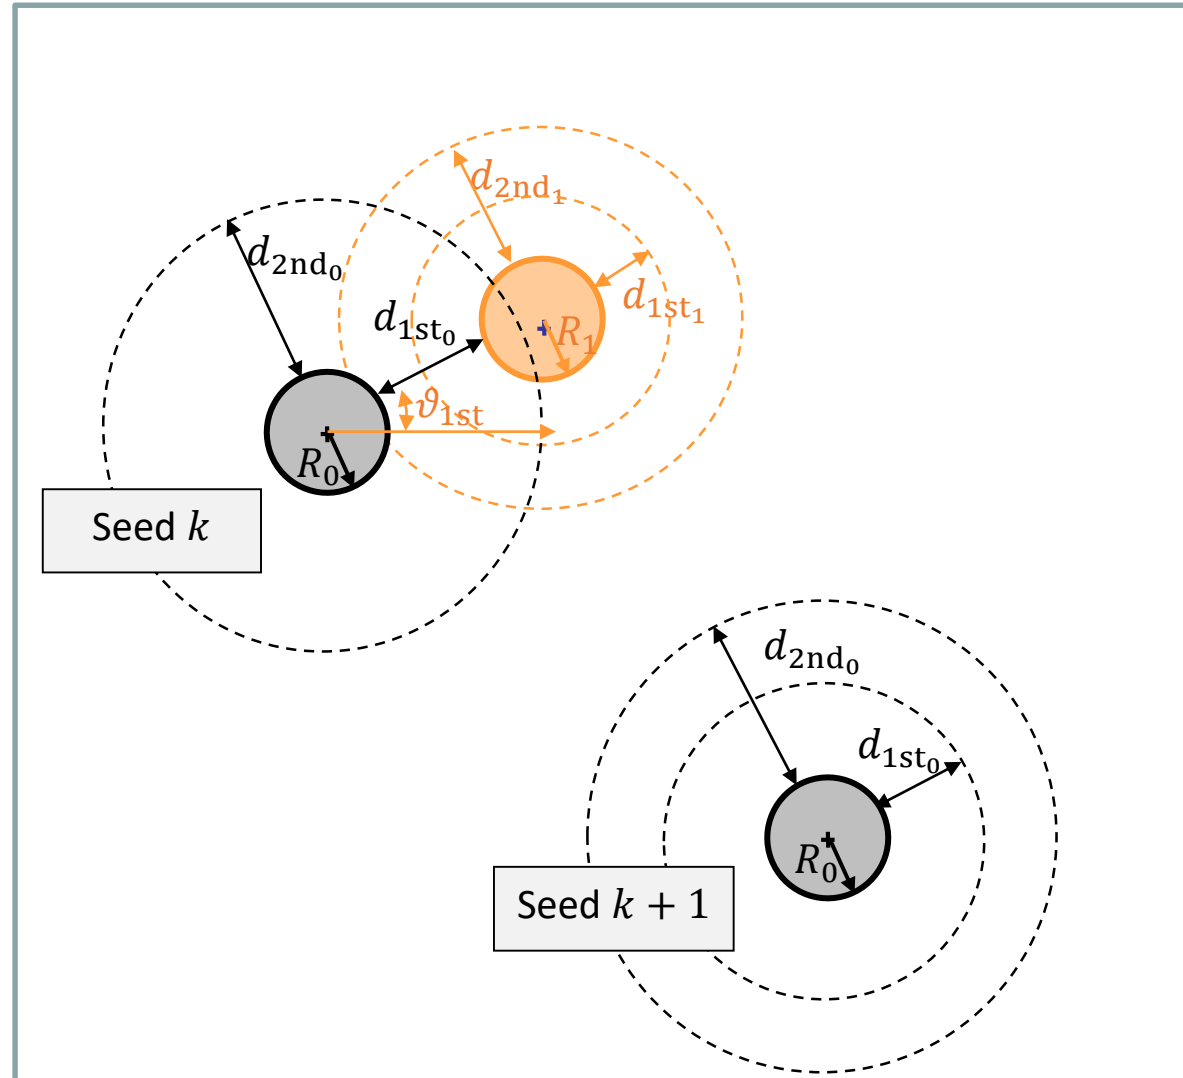


- The numerical micro-structure is generated by a fiber additive process

- 1) Define N seeds with first and second neighbors distances
- 2) Generate first neighbor with its own first and second neighbors distances
- 3) Generate second neighbor with its own first and second neighbors distances

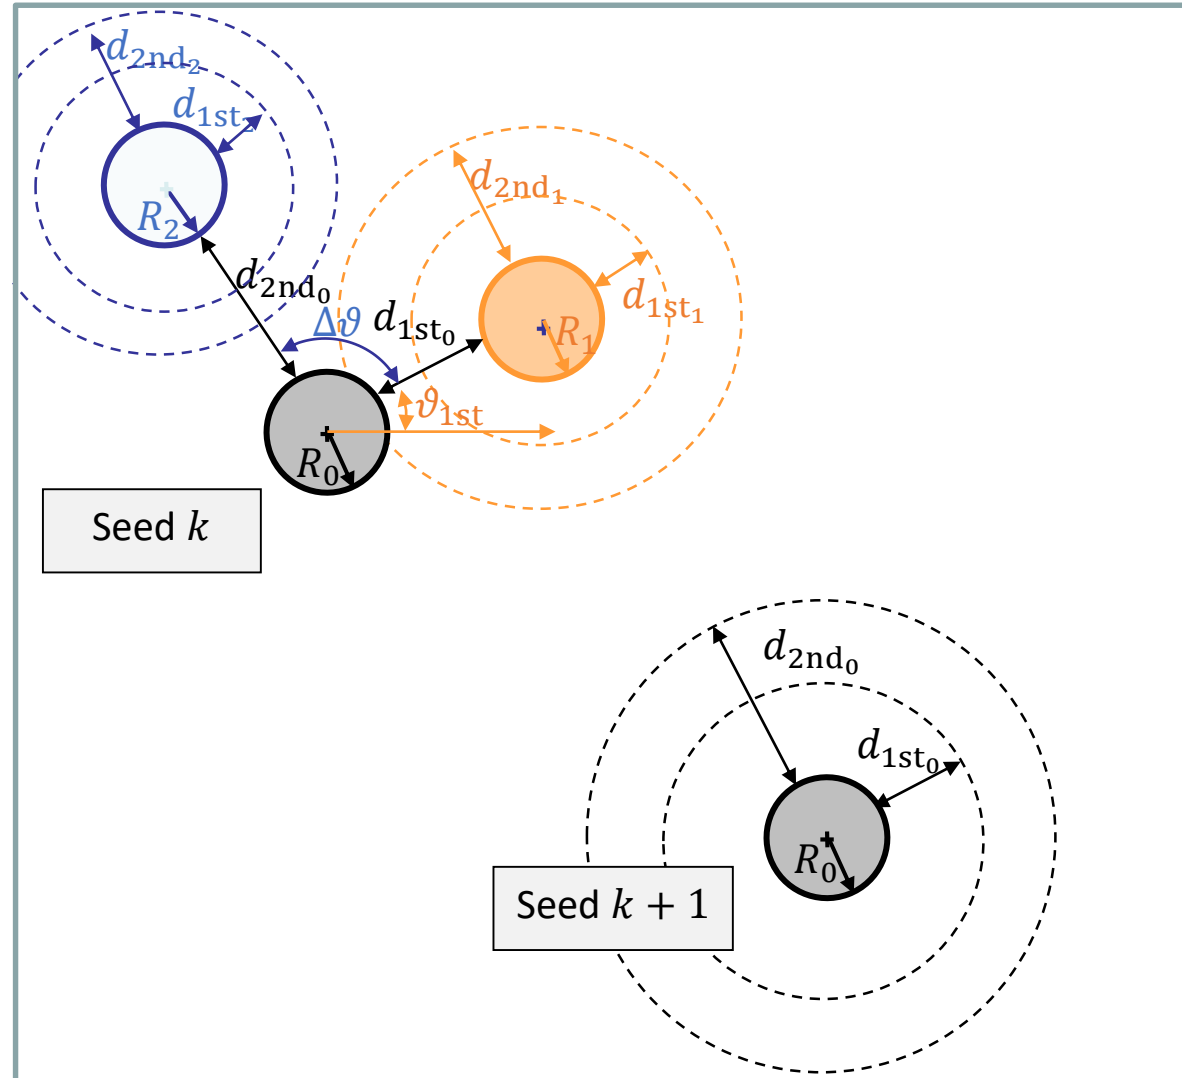

- The numerical micro-structure is generated by a fiber additive process

- 1) Define N seeds with first and second neighbors distances
- 2) Generate first neighbor with its own first and second neighbors distances
- 3) Generate second neighbor with its own first and second neighbors distances
- 4) Change seeds & then change central fiber of the seeds

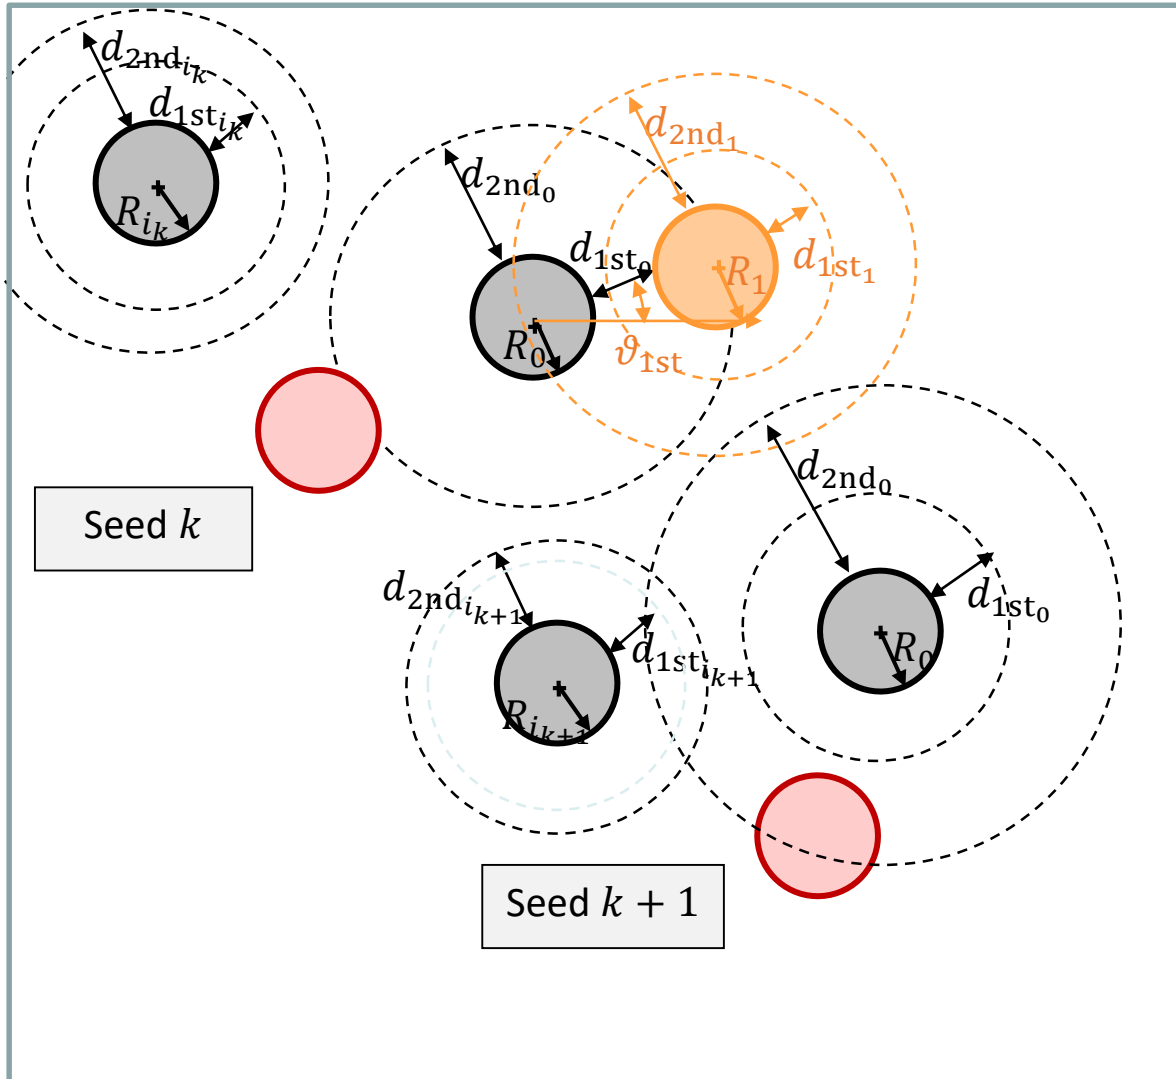


Micro-structure stochastic model

- The numerical micro-structure is generated by a fiber additive process
 - The effect of the initial number of seeds N and
 - The effect of the maximum regenerating times n_{max} after rejecting a fiber due to overlap





SEM: Average V_f of 103 windows;

Numerical micro-structures: Average V_f of 104 windows.

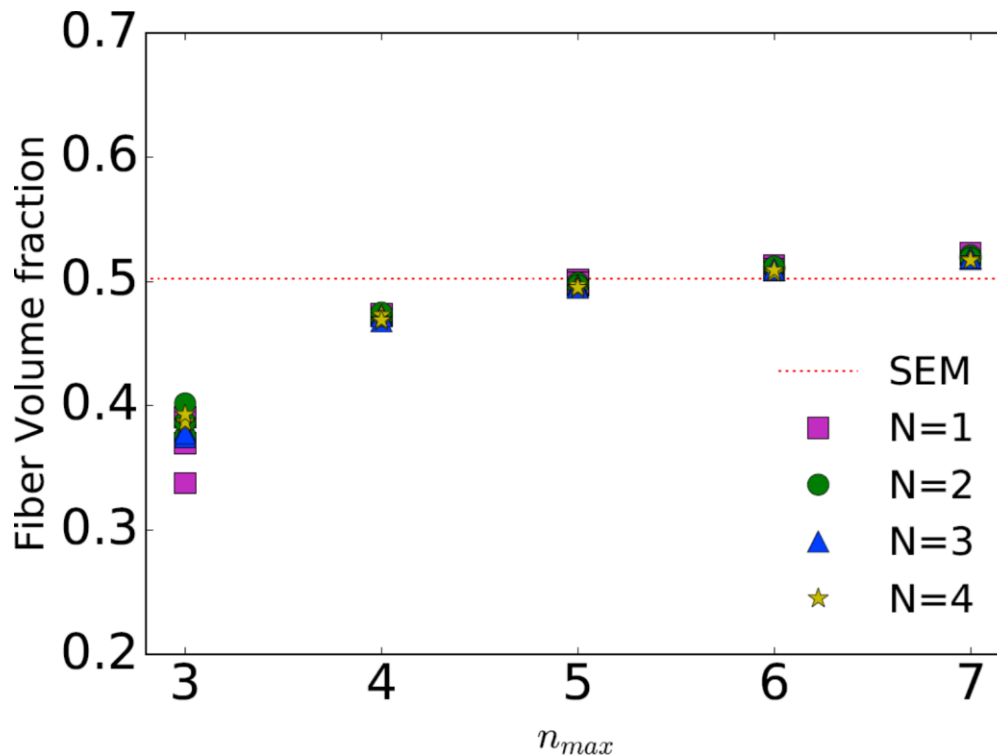



Micro-structure stochastic model

- Comparisons of fibers spatial information

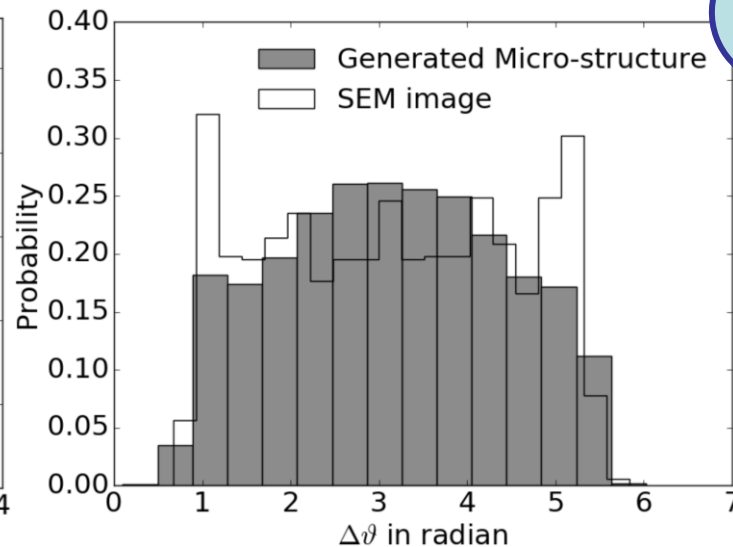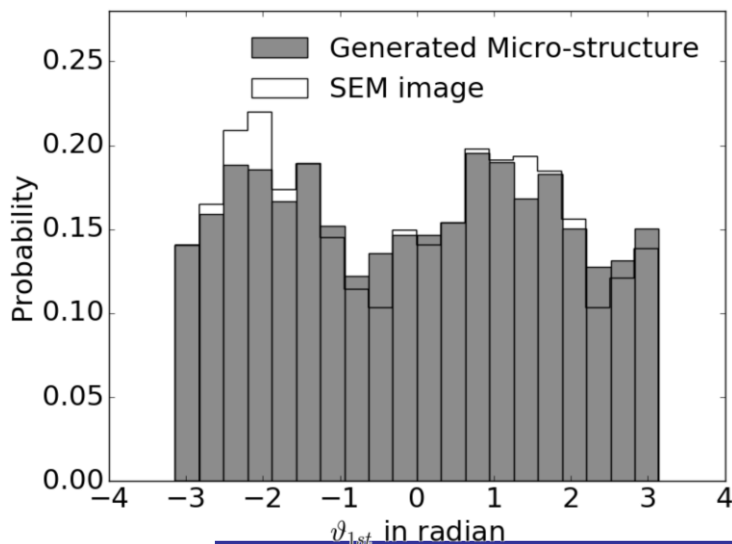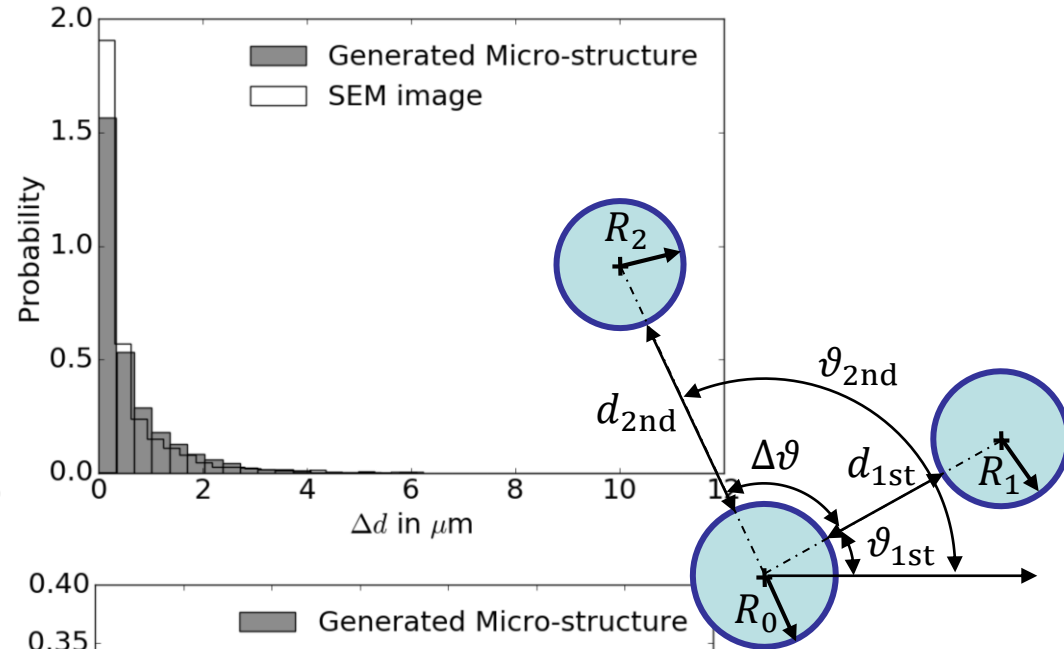
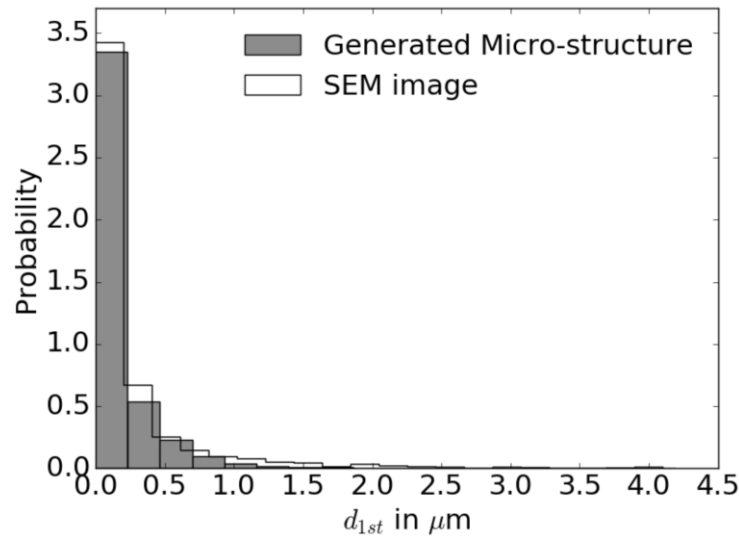


Micro-structure stochastic model

- Numerical micro-structures are generated by a fiber additive process
 - Arbitrary size
 - Arbitrary number

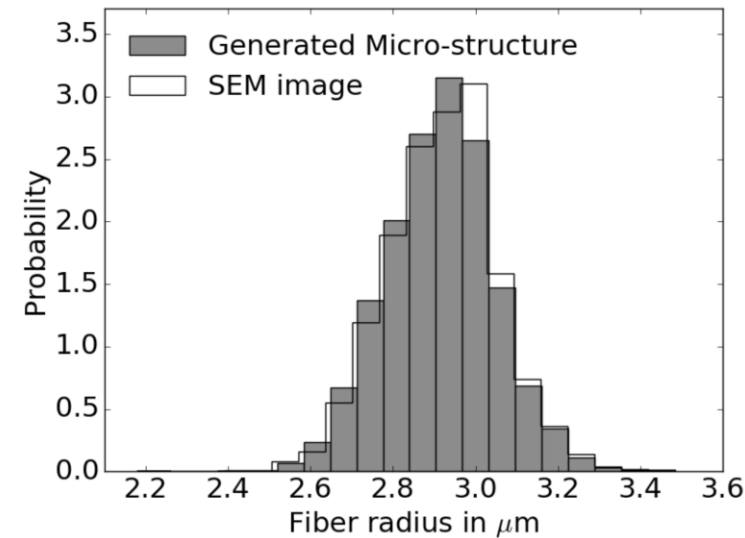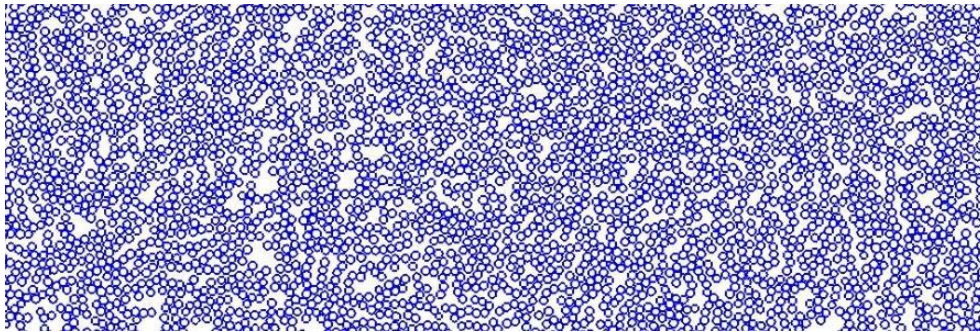

- Possibility to generate non-homogenous distributions

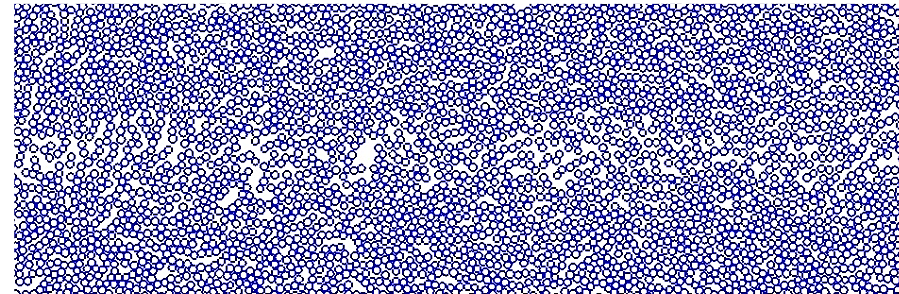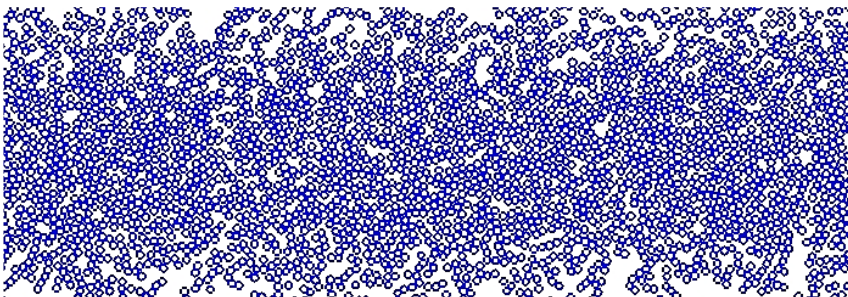

- Stochastic homogenization

- Extraction of Stochastic Volume Elements

- 2 sizes considered: $l_{SVE} = 10 \mu m$ & $l_{SVE} = 25 \mu m$
- Window technique to capture correlation

$$R_{rs}(\tau) = \frac{\mathbb{E}[(r(\mathbf{x}) - \mathbb{E}(r))(s(\mathbf{x} + \boldsymbol{\tau}) - \mathbb{E}(s))]}{\sqrt{\mathbb{E}[(r - \mathbb{E}(r))^2]} \sqrt{\mathbb{E}[(s - \mathbb{E}(s))^2]}}$$


- For each SVE

- Extract apparent homogenized material tensor \mathbb{C}_M



$$\left\{ \begin{array}{l} \boldsymbol{\varepsilon}_M = \frac{1}{V(\omega)} \int_{\omega} \boldsymbol{\varepsilon}_m d\omega \\ \boldsymbol{\sigma}_M = \frac{1}{V(\omega)} \int_{\omega} \boldsymbol{\sigma}_m d\omega \\ \mathbb{C}_M = \frac{\partial \boldsymbol{\sigma}_M}{\partial \mathbf{u}_M \otimes \nabla_M} \end{array} \right.$$

- Consistent boundary conditions:

- Periodic (PBC)
- Minimum kinematics (SUBC)
- Kinematic (KUBC)

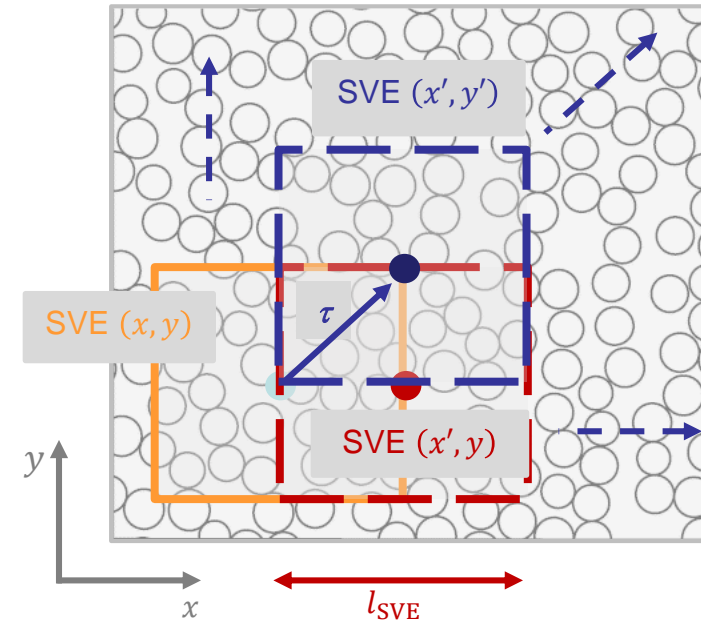

- Apparent properties

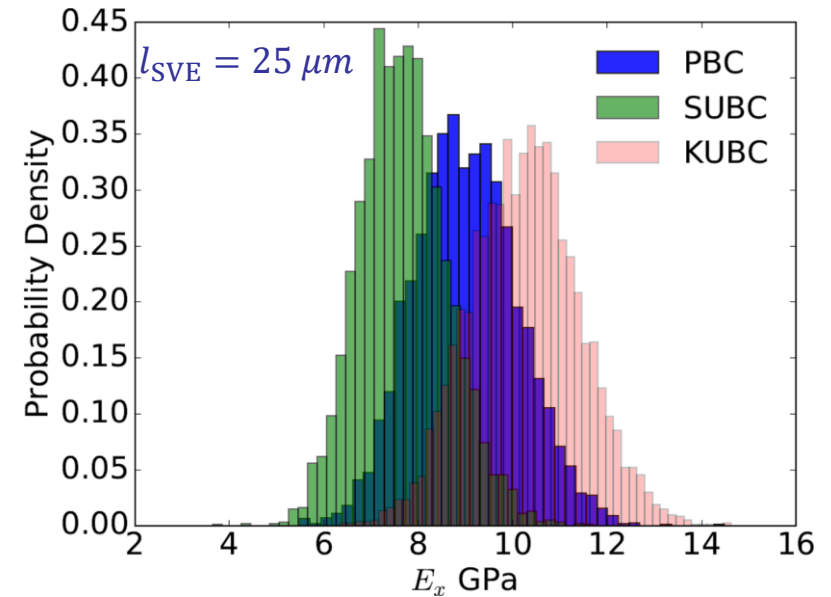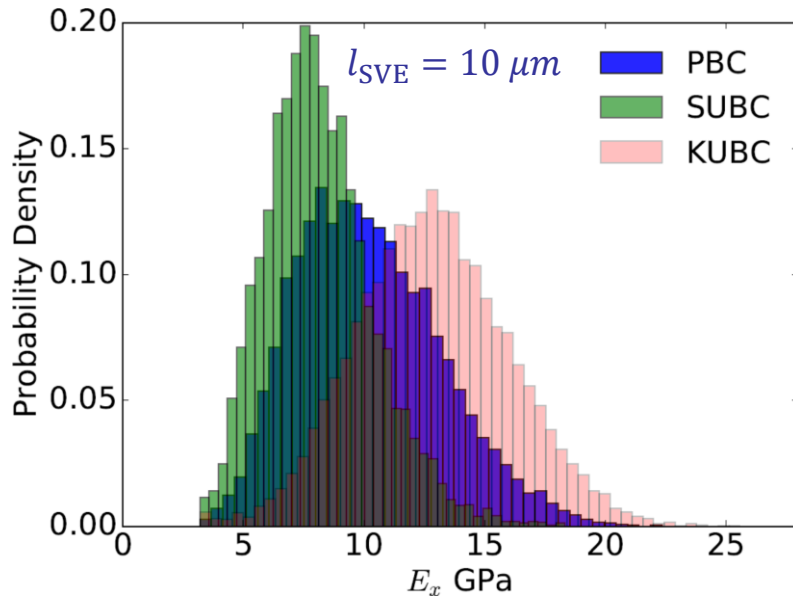

Increasing l_{SVE}


When l_{SVE} increases

- Average values for different BCs get closer (to PBC one)
- Distributions narrow
- Distributions get closer to normal


Stochastic homogenization on the SVEs

- When l_{SVE} increases: marginal distributions of random properties closer to normal



– $l_{\text{SVE}} = 10 \mu\text{m}$

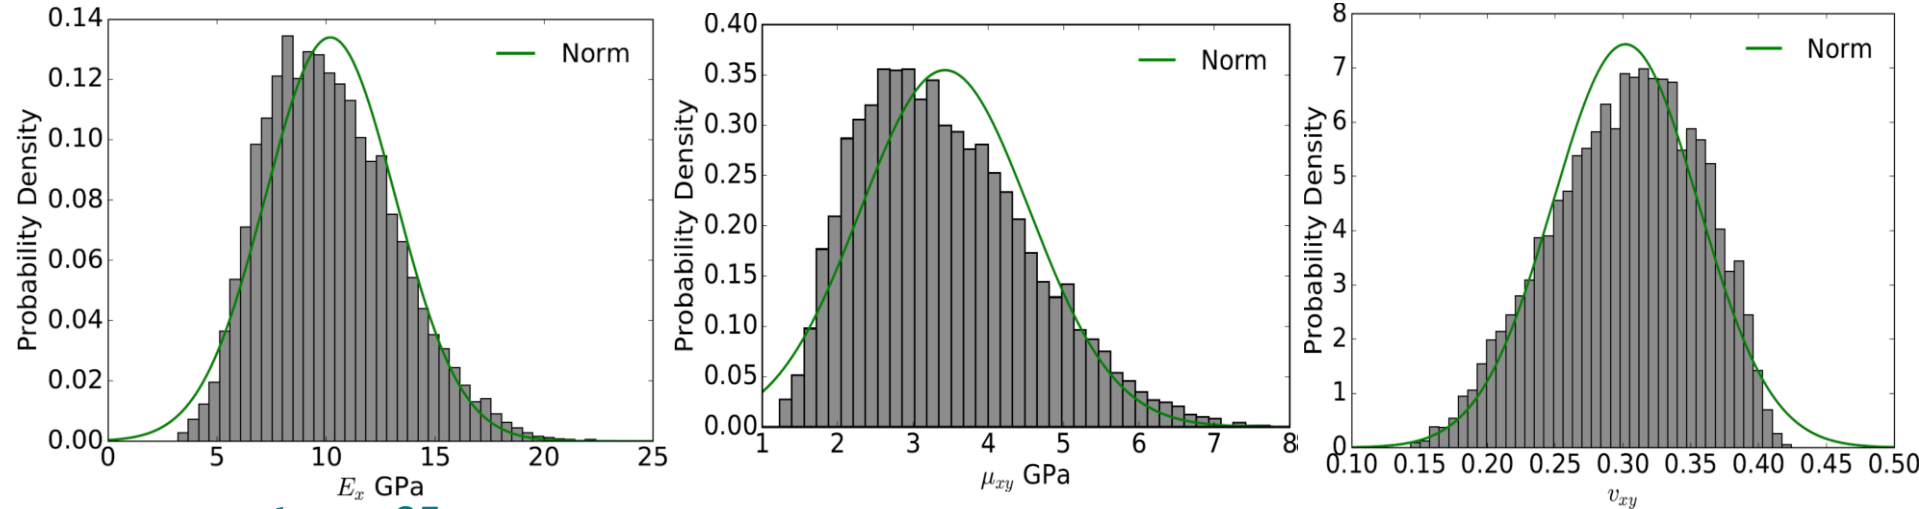

– $l_{\text{SVE}} = 25 \mu\text{m}$

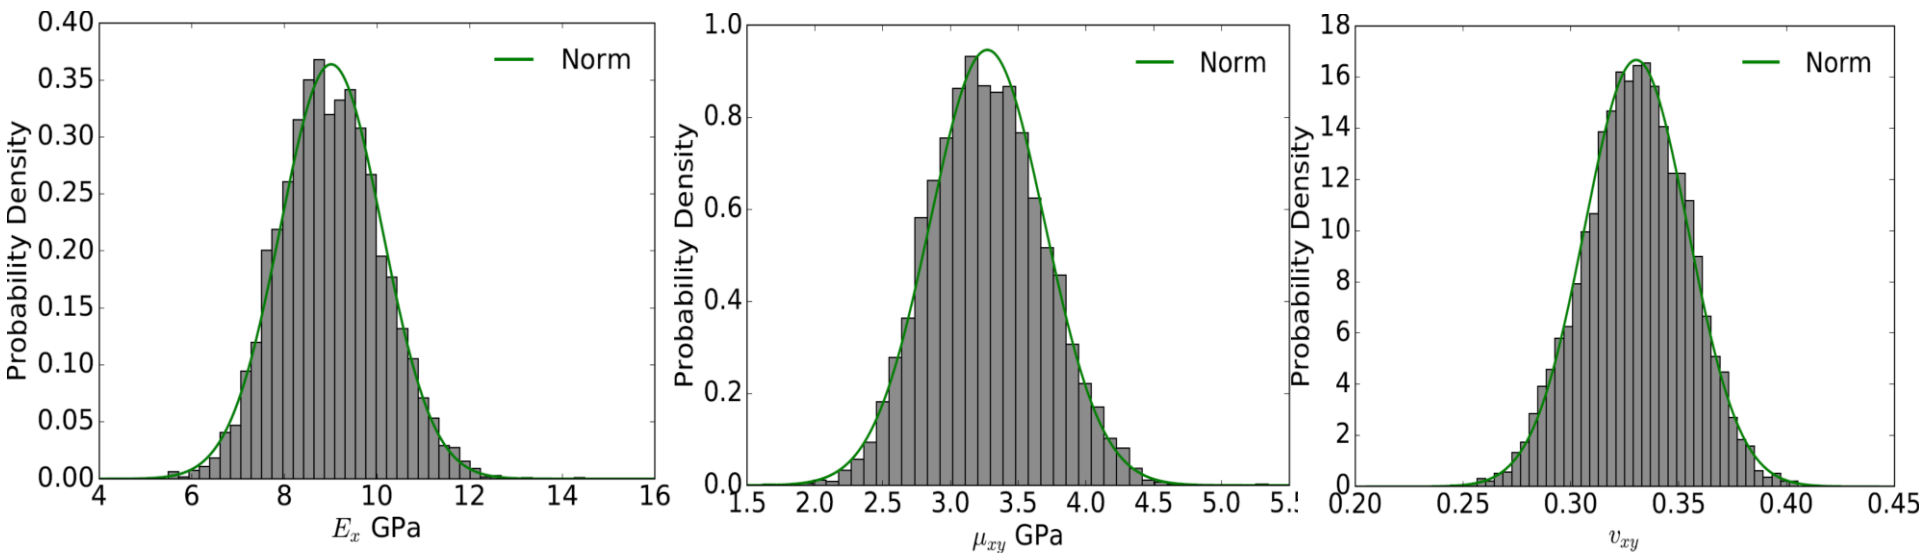

- Correlation

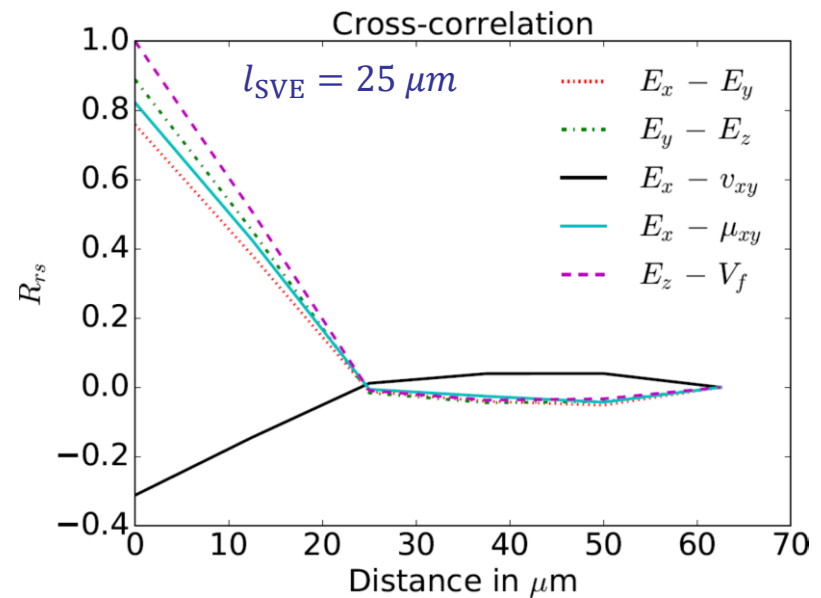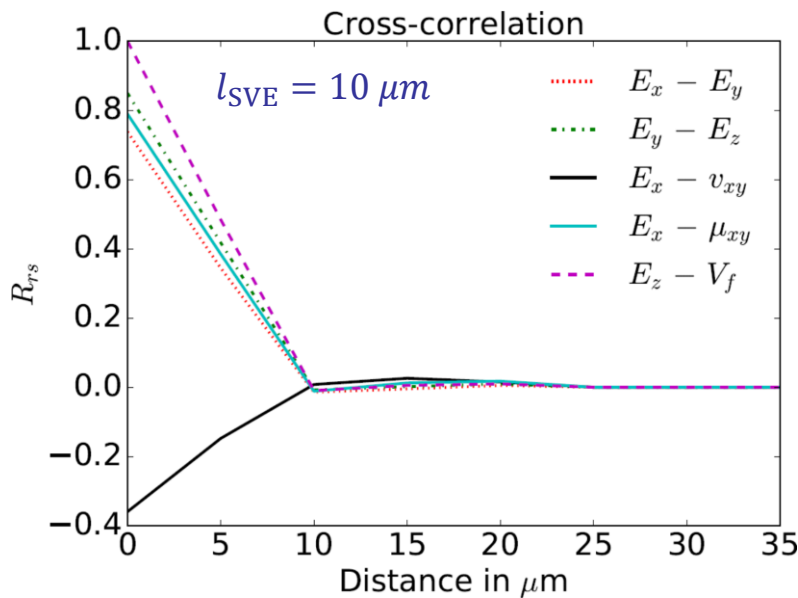


- (1) Auto/cross correlation vanishes at $\tau = l_{SVE}$
- (2) When l_{SVE} increases, distributions get closer to normal

(1)+(2) Apparent properties are independent random variables
 However the distribution depend on



- l_{SVE}
- The boundary conditions

- Quid larger SVEs?
 - Computational cost affordable in linear elasticity
 - Computational cost non affordable in failure analyzes
- How to deduce the stochastic content of larger SVEs?
 - Take advantages of the fact that the apparent tensors can be considered as random variables

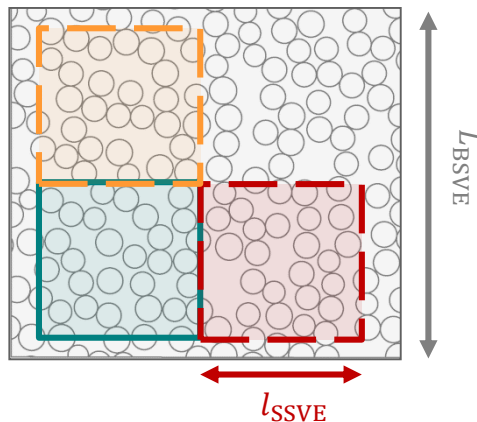




Stochastic homogenization on the SVEs

- Quid larger SVEs?
 - Computational cost affordable in linear elasticity
 - Computational cost non affordable in failure analyzes
- How to deduce the stochastic content of larger SVEs?
 - Take advantages of the fact that the apparent tensors can be considered as random variables

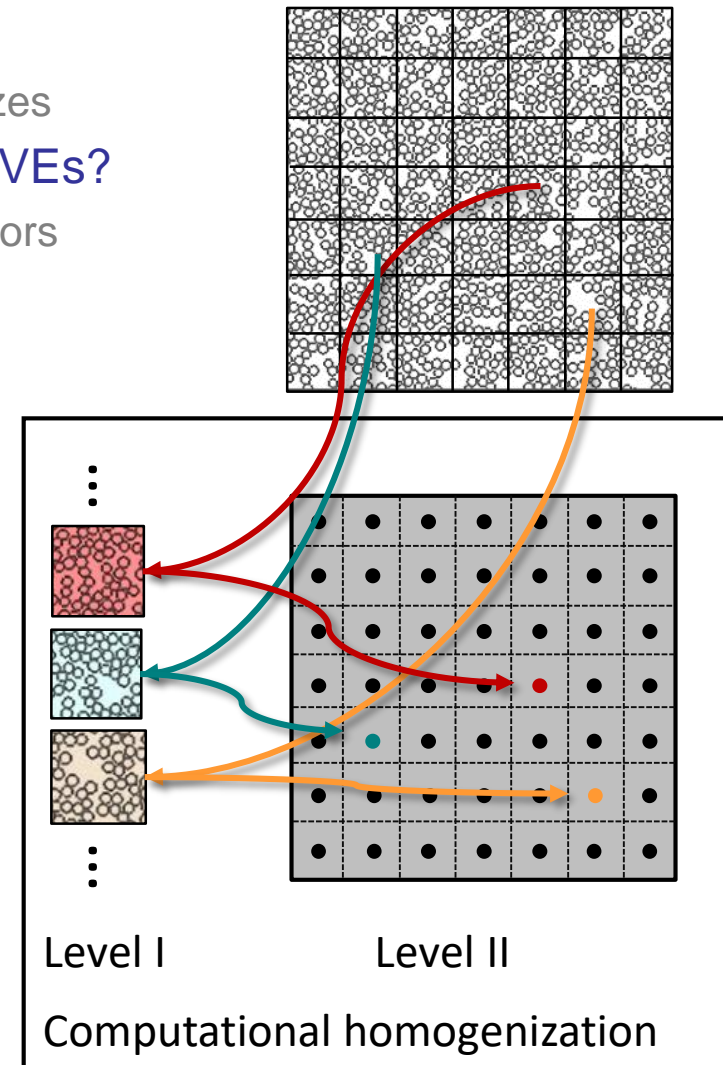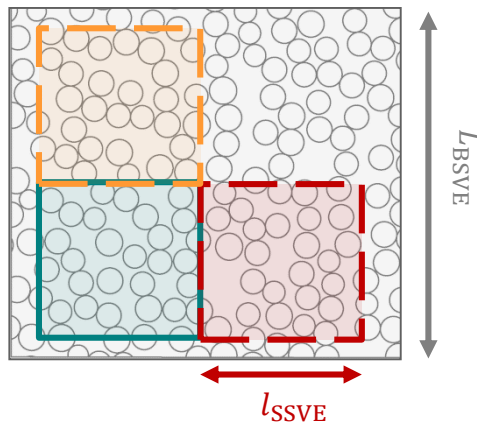



Stochastic homogenization on the SVEs

- Quid larger SVEs?
 - Computational cost affordable in linear elasticity
 - Computational cost non affordable in failure analyzes
- How to deduce the stochastic content of larger SVEs?
 - Take advantages of the fact that the apparent tensors can be considered as random variables
 - Accuracy depends on Small/Large SVE sizes

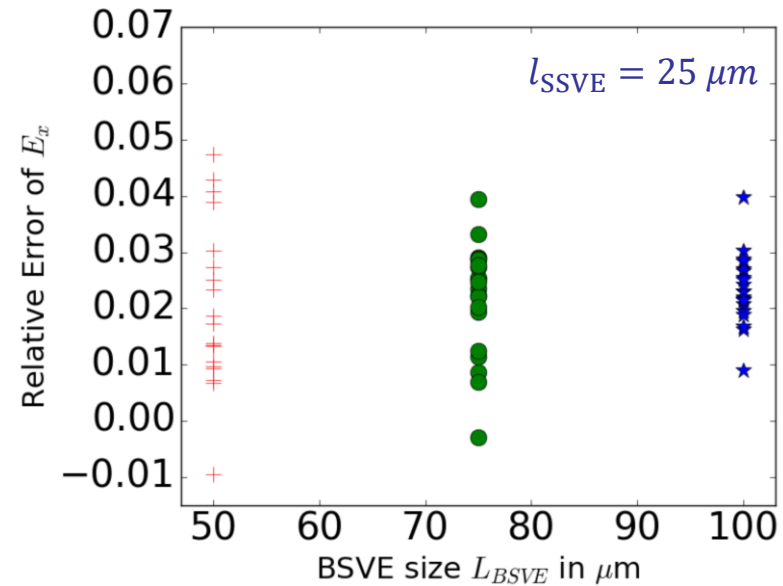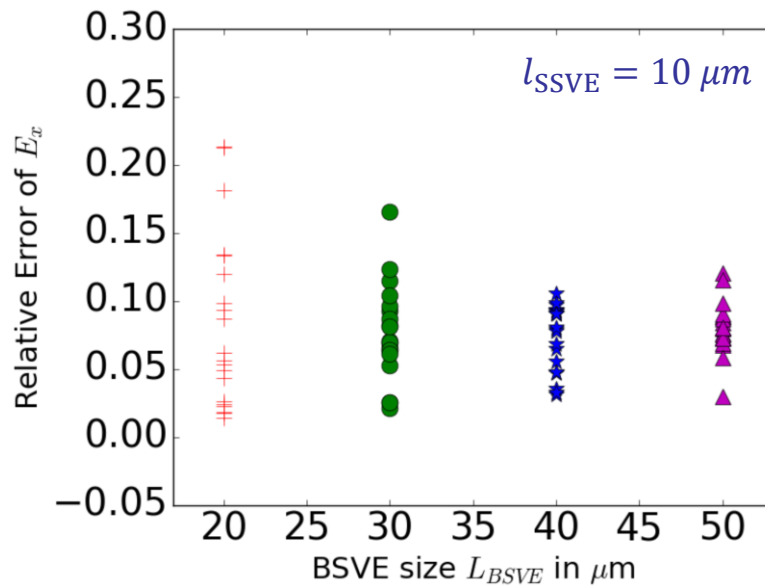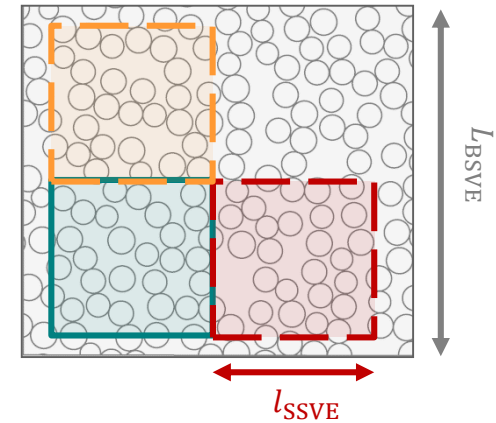

Stochastic homogenization on the SVEs


- Numerical verification of 2-step homogenization
 - Direct homogenization of larger SVE (BSVE) realizations
 - 2-step homogenization using BSVE subdivisions

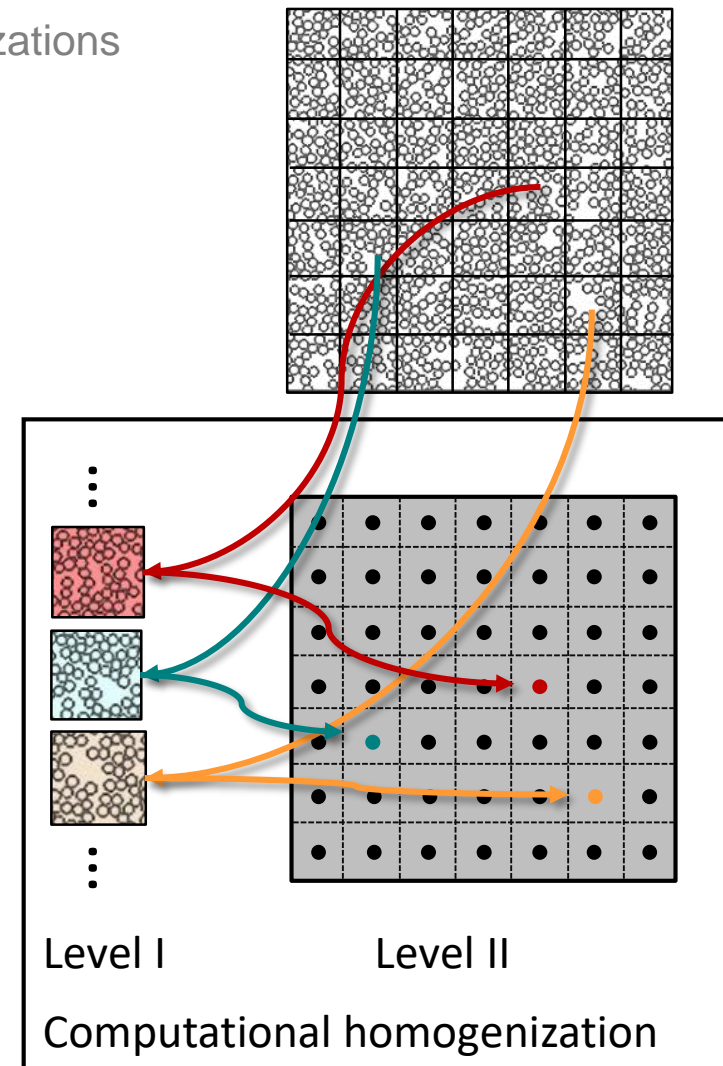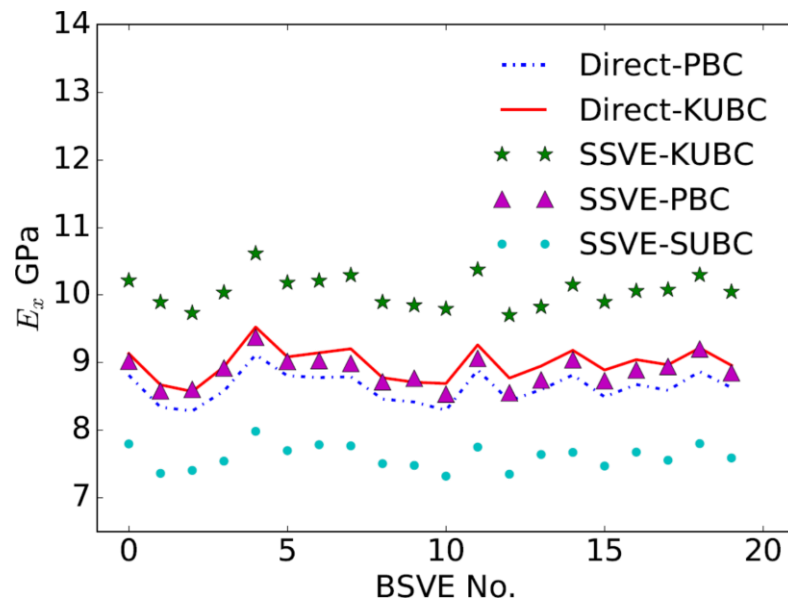

Stochastic reduced order model

- Stochastic model of the anisotropic elasticity tensor

- Extract (uncorrelated) tensor realizations \mathbb{C}_M^i

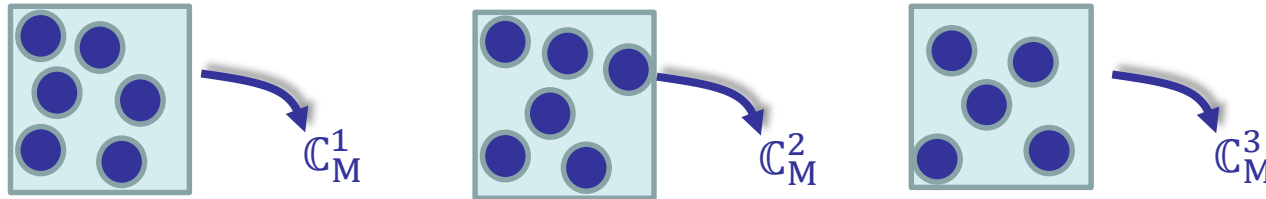


- Represent each realization \mathbb{C}_M^i by a vector \mathcal{V} of 9 (dependant) $\mathcal{V}^{(r)}$ variables
- Generate random vectors \mathcal{V} using the Copula method

- Simulations require two discretizations


- Random vector discretization



- Finite element discretization








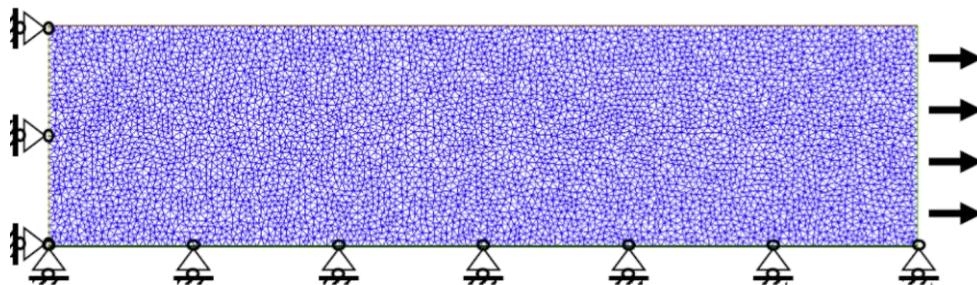


Material Property

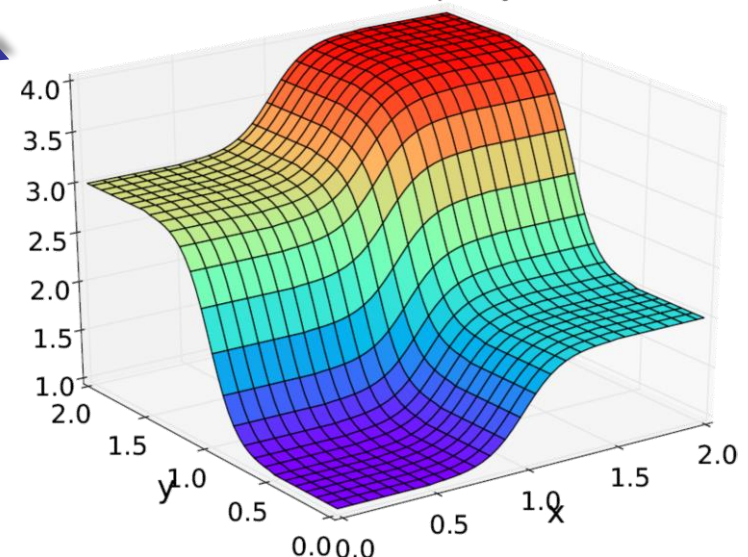

Stochastic reduced order model

- Ply loading realizations
 - Non-uniform homogenized stress distributions
 - Different realizations yield different solutions

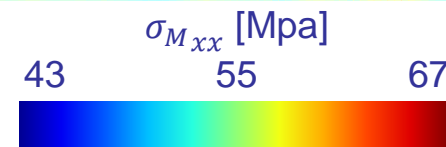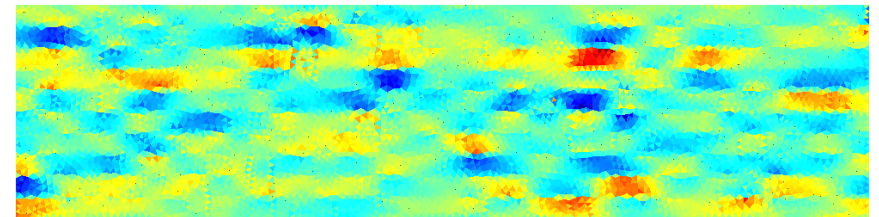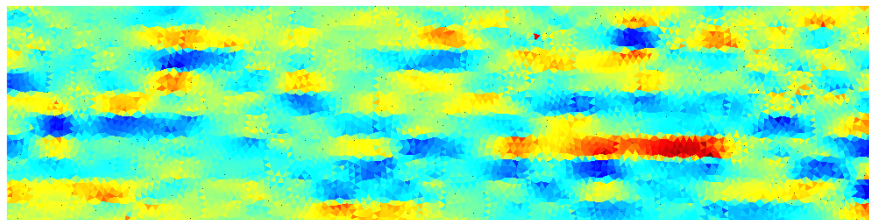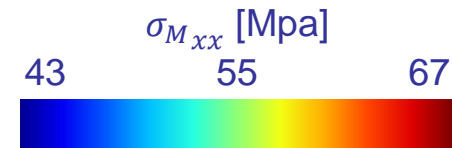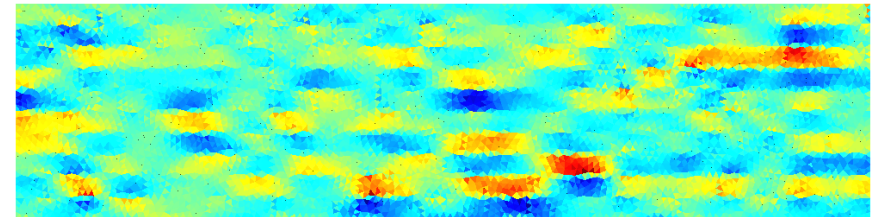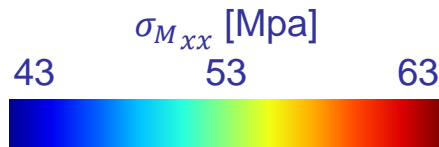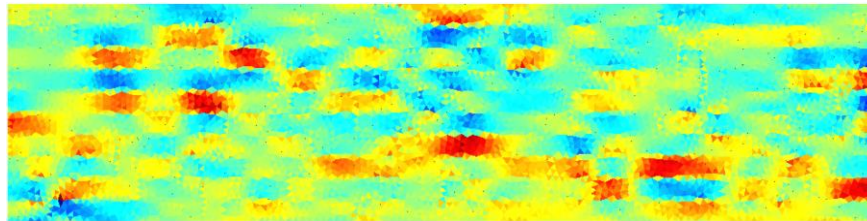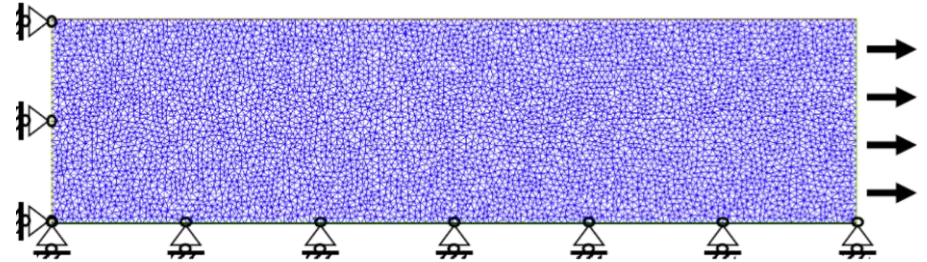

- Stochastic generator based on SEM measurements of unidirectional fibre reinforced composites
- Computational homogenization on SVEs
- Two-step computational homogenization for Big SVEs
- Future work: nonlinear and failure analyzes

Thank you for your attention !