



Contents lists available at ScienceDirect

Construction and Building Materials

journal homepage: www.elsevier.com/locate/conbuildmat

Hygro-thermal and durability properties of a lightweight mortar made with foamed plastic waste aggregates

Bartolomeo Coppola^{a,b}, Luc Courard^b, Frédéric Michel^b, Loredana Incarnato^a, Paola Scarfato^a, Luciano Di Maio^{a,*}


^aUniversity of Salerno, Department of Industrial Engineering, Via Giovanni Paolo II n. 132, 84084 Fisciano SA, Italy

^bUniversity of Liège, ArGenCo Department, Quartier Polytech 1, Allée de la découverte 9, B-4000 Liège, Belgium

HIGHLIGHTS

- Foamed end-of-waste plastic aggregates were used instead of natural silica sand.
- Increasing artificial aggregates content an increase of macropores was observed.
- Water vapour permeability increased while capillary water absorption decreased.
- Plastic aggregates reduced both mortar density and thermal conductivity.
- Lightweight mortars are suitable as pavement and/or roofing materials.

GRAPHICAL ABSTRACT

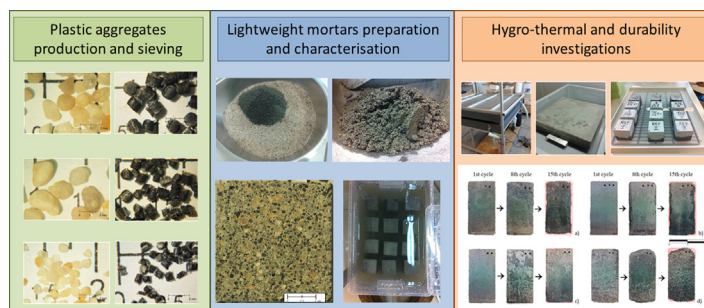

ARTICLE INFO

Article history:

Received 9 November 2017

Received in revised form 6 March 2018

Accepted 9 March 2018

Keywords:

Lightweight mortars
Polymeric foams
Thermal properties
Recycling
Porosity

ABSTRACT

In the present study, hygro-thermal and durability related properties of a cementitious mortar containing highly porous foamed aggregates obtained from polymeric end-of-waste materials were investigated. The evaluation of capillary water absorption, thermal conductivity, water vapour permeability and sulfate attack resistance of samples where natural quartz sand was replaced by 10%, 25% and 50% in volume with foamed aggregates was carried out. Experimental investigations showed that the presence of plastic aggregates decreased mortar density (up to 36%, compared to the reference sample, for the maximum investigated natural sand volume replacement) as well as thermal conductivity (10% for the 50% volume replacement). Moreover, water vapour transmission rate increased at increasing natural sand replacement while capillary water absorption decreased. Finally, after fifteen cycles of sulfate attack test, lightweight mortars evidenced a lower mass loss compared to the reference sample. The results were related to morphological modifications in the mortars bulk porosity, demonstrating by mercury intrusion porosimetry investigations, that polymeric foamed aggregates determine a variation of the pores microstructure, resulting in an increased pores dimension.

© 2018 Elsevier Ltd. All rights reserved.

1. Introduction

Replacement of natural aggregates in mortar and concrete production is one of the main issue to reduce depletion of natural resources in production of construction materials. Crushed asphalt from road rehabilitation [1], cast iron industry by-products [2]

* Corresponding author.

E-mail addresses: bcoppola@unisa.it (B. Coppola), luc.courard@ulg.ac.be (L. Courard), frederic.michel@ulg.ac.be (F. Michel), lincarnato@unisa.it (L. Incarnato), pscarfato@unisa.it (P. Scarfato), ldimaio@unisa.it (L. Di Maio).

electric arc furnace slag [3,4] and limestone filler recycled from marble industry [5] have been proposed to manufacture environmentally friendly mortars and concretes. More recently, the use of polymeric waste based materials as natural aggregates replacement in concrete is a relatively recent idea driven mainly by the energy and environmental concerns which are becoming remarkably relevant in the construction industry. On the other hand, the use of polymeric lightweight aggregates represent a promising solution in reducing the specific mass of concrete and mortars. From the environmental point of view, as plastic waste management is one of the most critical drawbacks of such versatile materials, the use of lightweight aggregates produced from end-of-waste or post-consumer materials is particularly interesting and the perspective of their use for new applications represent a challenge for researchers. To this extent, in the last ten years, several studies demonstrated the outcomes deriving from the use of recycled plastic wastes as natural aggregates replacement in cementitious materials [6,7]. The incorporation of lightweight aggregates provides several advantages: reduced specific mass, improved thermal properties, impact resistance, sound insulation properties, fire resistance and durability enhancement [8–28]. However, one of the main disadvantages of using polymeric and lightweight aggregates is the reduction of mechanical properties. Thus, authors generally focus the attention on such aspects which are related to the chemical and physical incompatibility between the polymeric phase and the cementitious matrix but also to the lower mechanical properties of plastic aggregates compared to natural aggregates. In the literature, plastic aggregates of different polymeric nature and shape have been investigated but only few studies dealt with hygro-thermal properties of lightweight mortars containing plastic aggregates. Moreover, even less authors investigated durability related problems of such mortars or concretes [8–10]. Hygro-thermal properties are very important parameters that should be taken into account in order to provide favorable living conditions in terms of temperature and relative humidity. Among all plastic waste materials, better results in terms of interfacial transition zone (ITZ) and insulating properties were reported when expanded polymeric aggregates were used, thanks to their porous structure [11–17,22–24]. Recently, Ramírez-Arreola et al. investigated also the possibility to produce foamed HDPE nanocomposite aggregates with different porosity varying nanoclay content [27]. Nanofillers have also been investigated as consolidating and protective agents to improve durability of different construction materials [29,30]. Durability related issues negatively affect structures service life, influencing maintenance costs and structural safety. Thus, it is very important to investigate durability also of lightweight cementitious materials. Dulsang et al. [10] reported an increased resistance to sulfuric acid of ethyl vinyl acetate (EVA) waste lightweight concrete. Turatsinze et al. [19,20] investigated the effects of rubber aggregates, obtained from shredded non-reusable tyres, on the concrete resistance to cracking and toughness increase. Authors demonstrated that cement-based mortars containing rubber aggregates are less prone to crack. Moreover, the use of waste plastic materials as mortar or concrete aggregates instead of virgin polymers, to obtain insulating materials, has not only environmental but also economic benefits [23]. Finally, as widely reported in the literature, one of the main drawbacks in the use of plastic aggregates or fibers in cementitious materials is the weak adhesion among polymeric materials, especially polyolefin, and the cementitious matrix [24,31]. In a previous work [24], Coppola et al. investigated the possibility to use polymeric aggregates with a rough surface, produced from end-of-waste materials by a foam extrusion process. The investigations reported an improved bond between plastic aggregates and the cement paste but also a good dispersion in the specimens cross-section. Moreover, a sharp decrease of density was achieved but

also consistency decreased at increasing natural sand replacement. In this study, hygro-thermal and durability properties of lightweight mortars containing such foamed end-of-waste aggregates were studied with the aim of correlating the results to composite morphology which resulted to be strongly influenced by the presence of lightweight aggregates.

2. Experimental procedures

2.1. Materials

Mortar samples were produced using an ordinary Portland cement (CEM I 42.5 N), quartz sand (CEN standard sand according to EN 196-1 [32], density of 2610 kg/m³) and lightweight aggregates (LWAs). LWAs were produced starting from an end-of-waste material represented by a polyolefinic blend (polypropylene and polyethylene coming from the recycling of flexible packaging materials), supplied in densified pellets. A chemical foaming agent (Hydrocerol CF) was used to produce by extrusion foamed strands that were subsequently grinded to obtain aggregates of four different particle size (2–1.4 mm, 1.4–1.0 mm, 1.0–0.50 mm and 0.50–0.18 mm), according to the procedure described in a previous article [24]. Finally, aggregates were sieved and proportioned to partially reproduce EN 196-1 [32] quartz sand particle size distribution.

2.2. Mixtures preparation

Mortar samples were prepared using dry LWAs to avoid an increase of porosity due to the presence of free water released from LWAs [24], using a w/c ratio of 0.50 and a cement/sand ratio of 0.33. Nomenclature of the studied mixtures is reported in Table 1. All the mortar samples were prepared according to EN 196-1 [32]; natural and LWAs were dry mixed in advance to better disperse the aggregates in the mixture. Three natural quartz sand volume replacements (10%, 25% and 50%) were investigated comparing lightweight mortars (LWMs) samples to control specimens, i.e. without LWAs. All the samples were wet cured for 28 days in a humid chamber at 90% RH and 20 °C.

2.3. Density measurement

The oven-dry density, ρ_d , of hardened mortars was determined on specimens dried at 105 °C until constant mass, according to EN 12390-7 [33]. Three specimens for each composition were tested (experimental data are reported in Ref. [34]).

2.4. Capillary water absorption

Lightweight mortars water absorption coefficient due to capillary action, C_w , was determined according to EN 1015-18 [35]:

$$C_w = 0.1(M_2 - M_1) \quad (1)$$

Table 1
Investigated mixtures containing three natural sand volume replacement by lightweight aggregates (LWAs).

Mortar	LWA (%)
Reference	–
LWM10	10
LWM25	25
LWM50	50

where M_2 and M_1 are the mass of the specimen, in grams, after 90 min and 10 min of immersion, respectively. Three prismatic specimens for each investigated mixture were prepared and tested after 28 days of wet curing. Prior to test, specimens were oven dried up to constant mass at 60 °C. Then, prismatic samples were immersed in deionized water for about 5 mm and the mass change was measured. Considering mass variation, the capillary absorption coefficient was calculated for all the investigated mortars. Experimental data are reported in Ref. [34].

2.5. Water vapour permeability

Water vapour permeability, W_{vp} , of lightweight mortar samples was determined according EN 1015-19 [39] that defines a test method to determine water vapour permeability in steady-state conditions:

$$W_{vp} = \frac{s}{A \Delta p / (\Delta G / \Delta t) - R_A} \quad (2)$$

where s , A and ΔG are sample thickness, area and mass variation; Δt is the time interval; Δp is the gradient of water vapour tension between saturated solution and samples storing chamber and R_A is the resistance to water vapour diffusion in the air between the sample and the KNO_3 saturated solution ($0.048 \cdot 10^9$ Pa m² s/kg, for 10 mm of interspace). Three flat cylindrical specimens (diameter of 75 mm and thickness of about 20 mm), conditioned at relative humidity of 50% and 20 °C, were prepared for each lightweight mortar and sealed on glass containers, in which a saturated solution of KNO_3 was contained. This solution, at 20 °C, provides a relative humidity of 93.2%: the gradient of water vapour pressure between the lower part of the sample (RH = 93.2%) and the environment in which samples are stored (RH = 50%) causes a water vapour flow through the mortar sample. Water vapour resistance factor (μ) was measured according to the following equation:

$$\mu = \frac{\delta_A}{W_{vp}} \quad (3)$$

where δ_A is air permeability ($1.94 \cdot 10^{-10}$ kg/(Pa m s)) in test conditions (20 °C and 50% RH) and W_{vp} is water vapour permeability. Experimental data are reported in Ref. [34].

2.6. Thermal conductivity

Thermal conductivity was measured using the so-called “guarded hot plate technique” (GHP), defined in the ISO 8302 and specified in European standards EN 12664 [36] and EN 12667 [37] (Fig. 1a). The device used in this research was designed, constructed and validated by Dubois and Lebeau [38]. Thermal conductivity measurements were carried out on mortar specimens of size equal to $30 \times 30 \times 5$ cm³ (Fig. 1b), manufactured in wood molds. After 28 days of water curing specimens were conditioned

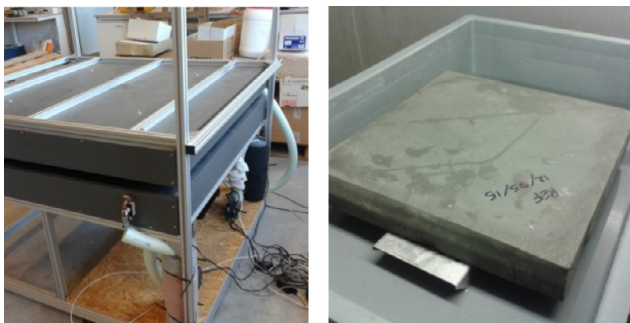


Fig. 1. a) GHP apparatus and b) slab-shaped specimen.

(25 °C and 50% RH) until constant mass before testing. Five tests were performed for each mortar sample to ensure the reproducibility (experimental data are reported in Ref. [34]).

2.7. Sulfate attack

The evaluation of lightweight mortar samples resistance to sulfate attack was evaluated according to the ASTM C88-05 procedure, opportunely modified [40,41]. Mortar specimens were immersed in a saturated solution of sodium-sulfate (Na_2SO_4) at room temperature for not less than 16 h and not more than 18 h, followed by a drying period in an oven at 110 °C up to constant weight. All these steps represent a drying-wetting cycle procedure. The evaluation of mortar behavior to sulfate attack is then made by measuring the weight variation of the lightweight mortar samples after a total of 15 cycles. The volume of the solution was at least five times the volume of the immersed specimens ($75 \times 75 \times 150$ mm³). A visual assessment of specimen deterioration was carried out by taking photos of mortar specimens at the first, eighth and fifteenth cycle.

2.8. Mercury Intrusion Porosimetry

Pore size distribution measurements and cumulative intruded volume were carried out on all the investigated LWMs by a mercury intrusion porosimeter (Pascal 140 and Pascal 240, Thermo Finnigan). The Mercury Intrusion Porosimetry (MIP) measurements were carried out using a contact angle of 141.3°, a Hg surface tension of 0.48 N/m and a pressure ranging from 0 to 200 MPa. Such pressure range covers a pores diameter range between about 0.0075 and 150 μm. Tests were performed on small samples of approximately 0.5 cm³. Samples for porosimetry were dried under vacuum at 60 °C for 12 h and stored in a desiccator until testing.

3. Results and discussion

3.1. Density of lightweight mortars (LWMs)

The possibility to use lighter materials in the building and construction field is very important, thanks to the possibility to reduce the structures dead load. To this extent, using plastic aggregates is possible to reduce mortars density. As expected, at increasing sand replacement, a decrease of mortar density was achieved, considering that artificial aggregates density is 65% lower than mineral sand density and that aggregates generally represent about the 70% of mortar or concrete volume [24]. Dry density values, ρ_d , of hardened mortars are reported in Table 2. A linear relationship exists between sand replacement and mortars dry density, as evident in Fig. 2. Compared to the reference sample, a density reduction of 8, 16 and 36% was obtained for LWM10, LWM25 and LWM50, respectively.

3.2. Capillary water absorption

The water sorption due to capillary suction was evaluated by specimens mass variation measurements and the capillary absorption coefficient C_w was calculated according to Eq. (1) and reported in Table 2. Increasing natural sand volume replacement, capillary water suction decreased of 32, 45 and 61%, compared to the reference sample, following a non-linear relationship (as evident from Fig. 3). A plateau in the values of C_w is reached for a sand substitution of approximately 40%, suggesting that at high polymeric aggregates volume content, capillary pores structure is not

Table 2

Mortars physical and mechanical properties (ρ_d = dry density; W_{vp} = water vapour permeability; μ = resistance to water vapour).

Mortar	Reference	LWM10	LWM25	LWM50
ρ_d [g/cm ³]	2.143	1.981	1.805	1.374
Total open porosity [%]	16	16	17	23
W_{vp} 10 ⁻¹¹ [kg/m s Pa]	2.97	3.60	3.97	5.88
μ	6.56	5.72	4.90	3.38
C_w [kg/(m ² h ^{0.5})]	1.87	1.26	1.02	0.72
Thermal conductivity [W/m K]	1.408	1.365	1.311	1.266

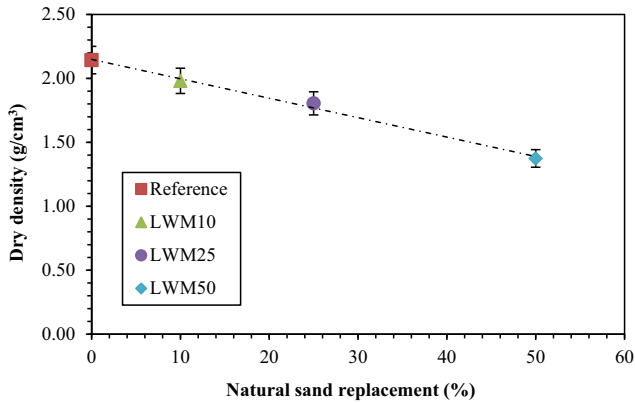


Fig. 2. LWMs dry densities vs. sand replacement.

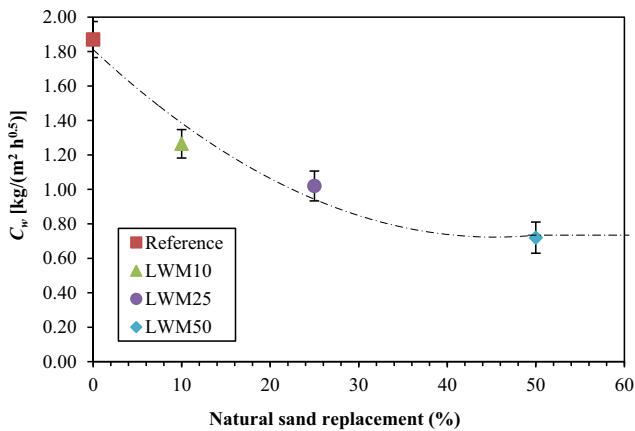


Fig. 3. Capillary water absorption vs. natural sand replacement.

affected. Such a behavior could be due to an effect of foamed aggregates on the degree of compaction of fresh mortars.

In a previous work, Coppola et al. [24] obtained a decrease of workability at increasing natural sand volume replacement, resulting in a non-linear open porosity increase (Table 2). More specifically, at increasing of polymeric foamed aggregates content samples present a decrease of capillary pores and an increase of macroporous structure in the sample volume. Moreover, as reported also by Marzouk et al. for PET aggregates [42], the hydrophobic nature of polymeric aggregates contributes to slow down the capillary water absorption. As stated previously, such porous structure is advantageous both for water vapour permeability and thermal conductivity, as discussed later.

3.3. Water absorption by total immersion

Water absorption is a crucial property for construction materials, as it represents one of the most important indicator of the

material durability. The total open porosity was obtained by measuring water absorption and is reported in Table 2. As expected, open porosity increased with sand replacement corresponding to a sharp increase of water absorption occurring with sand replacement higher than 25% (Fig. 4).

As seen before for the capillary water suction, a non-linear relationship exists also between water absorption of the different LWMs and natural sand replacement (Fig. 4). In this case, water absorption of lightweight mortars with more than 25% substitution of sand significantly increased compared to the reference mortar, according to results obtained by other authors [21,43,44]. Such behavior, is in agreement with the aforementioned effect of LWAs on mortar porous structure: the increase of macropores at increasing LWAs content, determined an increase of water absorption and a decrease of capillary suction.

3.4. Water vapour permeability

Hygro-thermal properties are very important to give favourable living conditions and a good water vapour permeability is able to avoid fungi and condensation phenomena. Water vapour permeability of lightweight mortars (LWM10, LWM25 and LWM50) were compared to the reference sample in order to obtain further data about the effect of polymeric foamed aggregates on the transport properties of LWMs. Water vapour permeability (W_{vp}) and resistance (μ) of the investigated samples (calculated according Eqs. (2) and (3), respectively) are reported in Table 2. Vapour permeability increased proportionally to natural sand replacement, corresponding to a reduction of water vapour resistance down to about 50% respect to the reference for lightweight mortars containing 50% of plastic aggregates as recognizable in Fig. 5. Such improvement of vapour transmission capability of LWMs tested samples is related to the overall porosity morphology (i.e. not only to capillary and macropores) and can be explained taking into account that, in the case of foamed polymeric aggregates, the intrinsic open porosity of the aggregates themselves is able to create a path both for water and water vapour permeation. On this

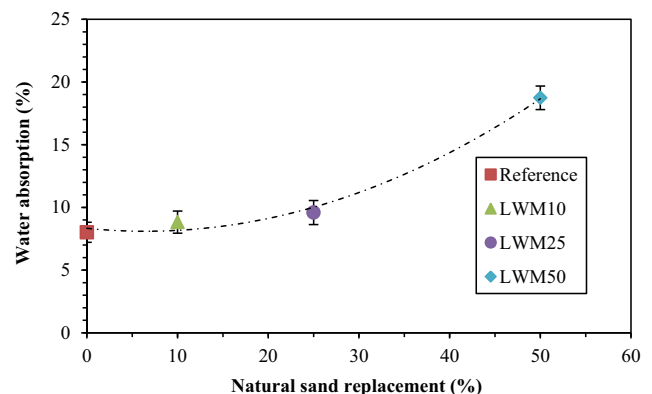


Fig. 4. LWMs water absorption (total immersion).

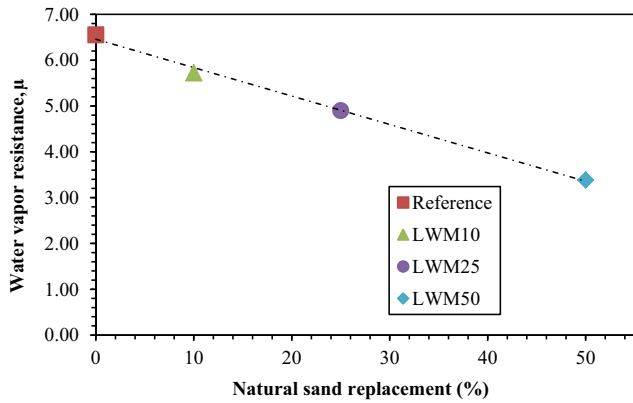


Fig. 5. Water vapour resistance vs. natural sand replacement.

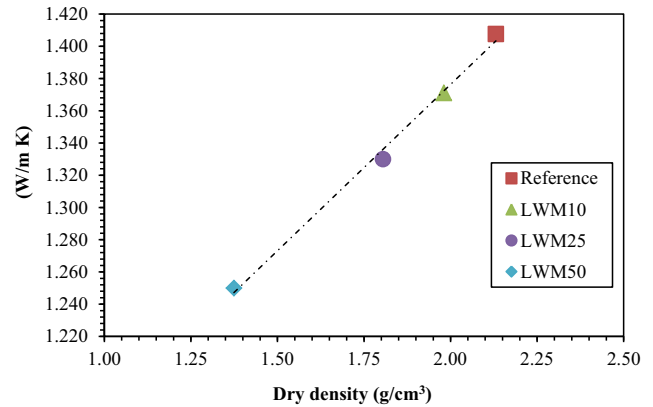


Fig. 7. LWMs thermal conductivity vs. dry densities.

point, it has also to be considered that no contribution to this result was given by ITZ around the foamed aggregates, which presented lower porosity and higher density, as reported previously [24], unlike other literature results on lightweight mortars containing plastic wastes [16–18].

As well known, LWMs properties are strictly correlated also to aggregates/matrix ITZ. In Fig. 6 is shown the linear relationship that exists between capillary water absorption and water vapour resistance. At increasing natural sand replacement a decrease of both capillary water absorption and resistance to water vapour was obtained, confirming what stated before about pores morphology.

3.5. Thermal conductivity

The influence of artificial aggregates on lightweight mortars thermal conductivity was investigated by GHP apparatus, considering that quartz sand have a very high thermal conductivity compared to the plastic one (about 20 times [45]). As expected, at increasing natural sand replacement, a decrease of thermal conductivity was obtained (Table 2). In particular, a reduction of thermal conductivity of 3, 7 and 10% was obtained replacing 10, 25 and 50% of natural quartz sand, respectively. Similarly to other literature results [16,46] a linear relationship is recognizable between thermal conductivity and lightweight mortars dry density which is, in turn, linearly related to sand replacement (Fig. 7).

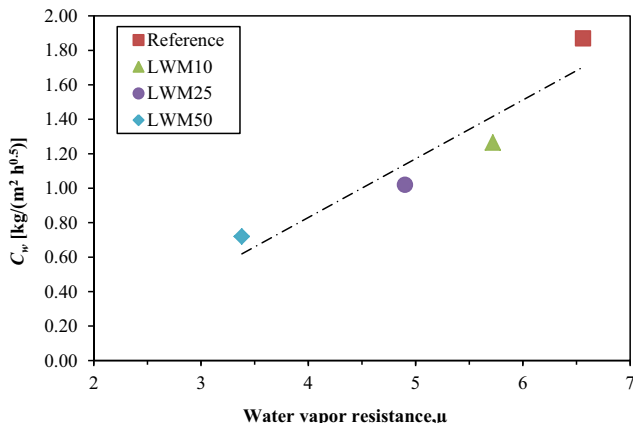


Fig. 6. Capillary water absorption vs. resistance to water vapour.

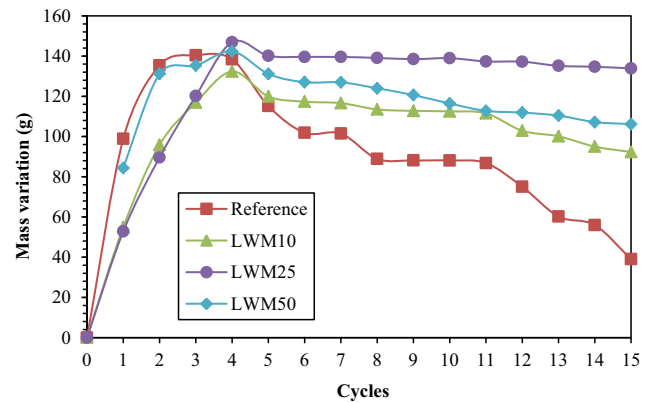


Fig. 8. Mass variation at increasing cycles of the sulfate attack test.

3.6. Sulfate attack

The resistance of LWMs to sulfate attack was evaluated by mass variation and relative mass (Fig. 8) after 15 wet/dry cycles into a saturated solution of sodium sulfate.

The role of capillary pores is crucial for the resistance to sulfate attack, resulting in a better behavior of lightweight mortars. As shown in Fig. 8, the specimens mass initially increases due to the solution absorption, reaching a peak value that corresponds to the third cycle for the reference sample and the fourth cycle for the lightweight mortars regardless the LWAs substitution. Such different behavior is mainly due to the different porosity of the samples and the different time necessary to saturate pores. As stated before, lightweight mortars have bigger pores that are able to contrast expansive phenomena associated to ettringite production. The presence of bigger pores is also very useful in the case of freeze/thaw phenomena because also in this case the pressure exerted on pores surface can lead to cracking and/or disintegration. In Fig. 9 is reported the relative mass loss (i.e. the ratio between the mass loss of the specimen and the mass loss of the reference sample, in percentage). For the previously stated reasons, lightweight mortar samples reported a lower mass loss than the reference sample. In particular, LWM25 showed the lowest relative mass loss while LWM10 and LWM50 have approximately the same value despite a progressive decrease of relative mass loss could be expected. However, it should be considered that the lightweight mortar with the highest artificial aggregates content is more prone to disintegration due to the low compaction level compared to the other samples. Thus, LWM50 specimens degradation is due both to

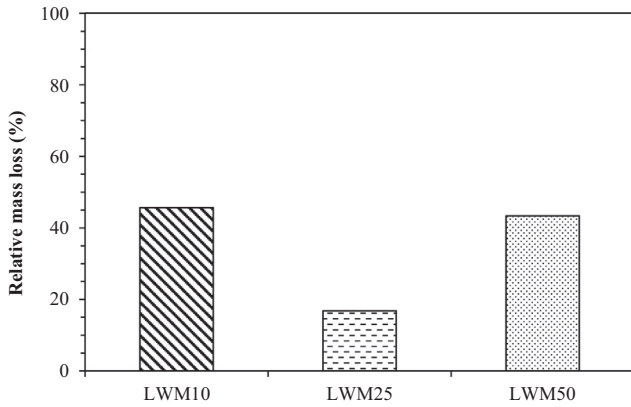


Fig. 9. Relative mass loss after fifteen cycles of sulfate attack.

ettringite formation and disintegration caused by the low cohesion of the sample.

Such different behavior is also clearly visible in Fig. 10 where a visual assessment of mortar specimens deterioration is reported at increasing test cycle (at the first, eighth and fifteenth cycle). The deterioration clearly appears already after 8 cycles as samples are affected by cracking, corners spalling and edge fragmentation. Visual observations confirm mass loss results: the extent of attack of lightweight mortar samples is lower in comparison to the reference sample. In the latter case degradation was more depth while in the formers only the skin was attacked.

3.7. Mercury Intrusion Porosimetry

Pores size distribution strongly influences mortars durability and hygro-thermal properties. Pores size distribution was investigated by Mercury Intrusion Porosimetry (MIP) and results are reported in Fig. 11 where the total open porosity was divided into micropores (<0.1 μm), mesopores (0.1–1 μm) and macropores (>1 μm). The results clearly confirmed what discussed in the previous paragraphs: at increasing natural sand replacement, a decrease of micropores and a contextual increase of macropores were

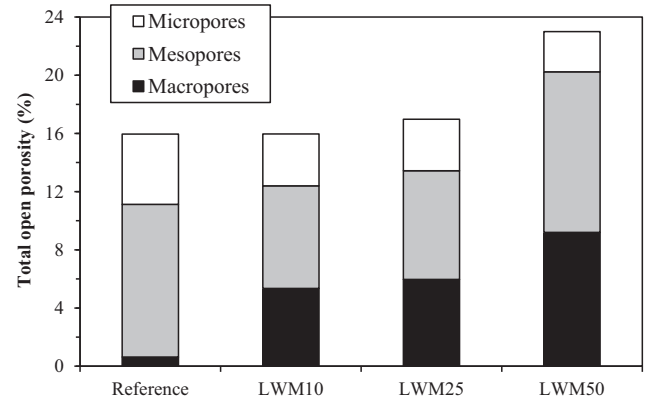


Fig. 11. Mercury Intrusion Porosimetry results for the investigated mortars.

observed. The lower capillary water absorption coefficient (Table 2) measured for LWMs is correlated to the lower amount of micropores. On the contrary, the increase of macropores in LWMs determines the higher water vapour permeability (Table 2).

4. Conclusions

In this study, hygro-thermal and durability properties of a lightweight mortar containing foamed end-of-waste plastic aggregates were investigated. Artificial plastic aggregates were manufactured according to the procedure described in a previous article in a three step process: foamed strand production, grinding and sieving [24]. Such procedure determined higher adhesion with the cementitious matrix thanks to the presence of interlocking positions onto aggregates surface thanks to the high porosity and rough surface of foamed aggregates. Three lightweight mortars (LWMs) were produced replacing natural quartz sand, in volume, by 10%, 25% and 50% of foamed end-of-waste plastic aggregates. Experimental investigations showed that the pores morphology of LWMs differs from the reference samples. In particular, due to the pores microstructure variation at increasing LWAs, there is an increase of macropores, which positively influence thermal conductivity and water vapour permeability, reducing at the same time the cap-

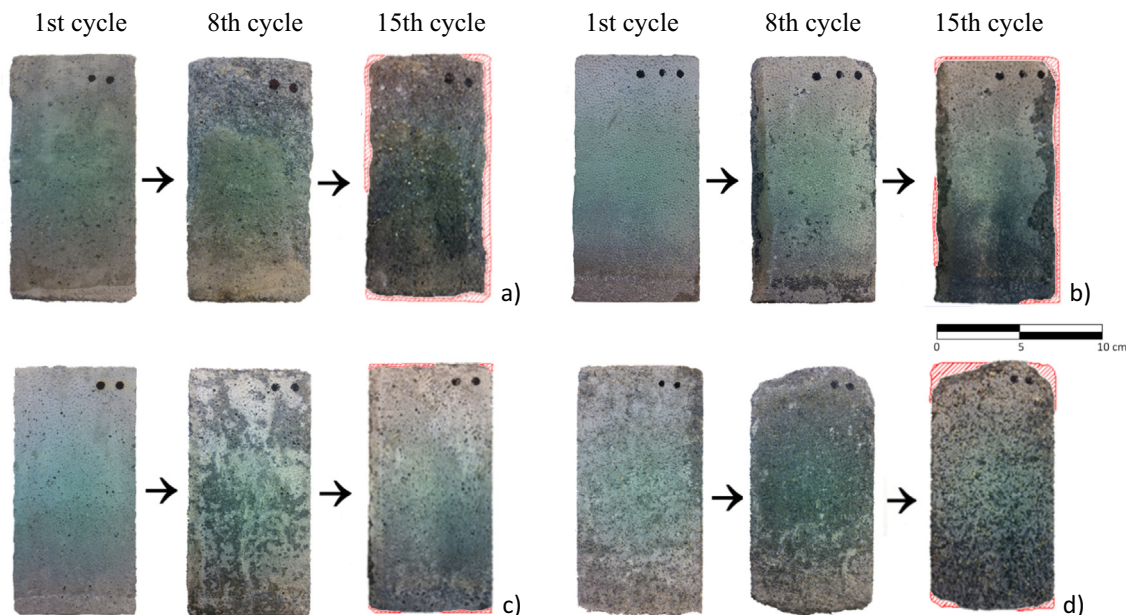


Fig. 10. Samples at the beginning, after 8 and 15 cycles of sulfate attack. a) Reference, b) LWM10, c) LWM25 and d) LWM50.

illary water absorption. Thus, the presence of plastic foamed aggregates decreased mortar density (up to 36%, compared to the reference sample, for the 50% of natural sand volume replacement) as well as thermal conductivity (10% for the 50% volume replacement). Moreover, water vapour resistance significantly decreased at increasing natural sand replacement whereas capillary water absorption decreased. Also resistance to sulfate attack achieved good results, thanks to the different pores morphology. In order to confirm the hypothesis about pores size distribution, mercury intrusion porosimetry (MIP) investigations were performed on LWMs. MIP results confirmed the increase of macropores and the contextual decrease of micropores, at increasing LWAs content. In the end, this study demonstrated that polymeric end-of-waste materials can be used to produce artificial aggregates for the replacement of natural sand in LWMs manufacturing. Such replacement leads to a more sustainable lightweight mortar with better hygro-thermal properties.

Acknowledgments

Authors would like to thank Prof. F. Lebeau (University of Liège) for the use of the GHP test apparatus. The authors are also grateful to COREPLA (Italian Consortium for the Collection and Recycling of Plastic packages) for providing the end-of-waste materials.

References

- [1] L. Coppola, P. Kara, S. Lorenzi, Concrete manufactured with crushed asphalt as partial replacement of natural aggregates, *Mater. Constr.* 66 (2016) 101.
- [2] L. Coppola, S. Lorenzi, P. Marcassoli, G. Marchese, Concrete production by using cast iron industry by-products, *Ind. Ital. del. Cem.* 836 (2007) 748.
- [3] L. Coppola, A. Buoso, D. Coffetti, P. Kara, S. Lorenzi, Electric arc furnace granulated slag for sustainable concrete, *Constr. Build. Mater.* 123 (2016) 115.
- [4] L. Coppola, S. Lorenzi, A. Buoso, Electric arc furnace granulated slag as a partial replacement of natural aggregates for concrete production, in: Proceedings of the 2nd International Conference on Sustainable Construction Materials and Technologies, 2010, vol. 1.
- [5] L. Coppola, T. Cerulli, D. Salvioni, Sustainable development and durability of self-compacting concretes, in: Proceedings of the 11th International Conference on Fracture (ICF11), 2005.
- [6] N. Saikia, J. de Brito, Use of plastic waste as aggregate in cement mortar and concrete preparation: a review, *Constr. Build. Mater.* 34 (2012) 385.
- [7] R. Siddique, J. Khatib, I. Kaur, Use of recycled plastic in concrete: a review, *Waste Manage.* 28 (2008) 1835.
- [8] V. Ferrándiz-Mas, E. García-Alcocel, Durability of expanded polystyrene mortars, *Constr. Build. Mater.* 46 (2013) 175.
- [9] A.M. da Silva, J. de Brito, R. Veiga, Incorporation of fine plastic aggregates in rendering mortars, *Constr. Build. Mater.* 71 (2014) 226.
- [10] N. Dulsang, P. Kasemsiri, P. Posi, S. Hiziroglu, P. Chindapasirt, Characterization of an environment friendly lightweight concrete containing ethyl vinyl acetate waste, *Mater. Des.* 96 (2016) 350.
- [11] S. Gutiérrez-González, J. Gadea, A. Rodríguez, C. Junco, V. Calderón, Lightweight plaster materials with enhanced thermal properties made with polyurethane foam wastes, *Constr. Build. Mater.* 28 (2012) 653.
- [12] P. Mounanga, W. Gbongbon, P. Poullain, P. Turcry, Proportioning and characterization of lightweight concrete mixtures made with rigid polyurethane foam wastes, *Cem. Concr. Compos.* 30 (2008) 806.
- [13] V. Corinaldesi, A. Mazzoli, G. Moriconi, Mechanical behaviour and thermal conductivity of mortars containing waste rubber particles, *Mater. Des.* 32 (2011) 1646.
- [14] K.G. Babu, D.S. Babu, Behaviour of lightweight expanded polystyrene concrete containing silica fume, *Cem. Concr. Res.* 33 (2003) 755.
- [15] R. Wang, C. Meyer, Performance of cement mortar made with recycled high impact polystyrene, *Cem. Concr. Compos.* 34 (2012) 975.
- [16] V. Corinaldesi, J. Donnini, A. Nardinocchi, Lightweight plasters containing plastic waste for sustainable and energy-efficient building, *Constr. Build. Mater.* 94 (2015) 337.
- [17] J. Gadea, A. Rodríguez, P.L. Campos, J. Garabito, V. Calderon, Lightweight mortar made with recycled polyurethane foam, *Cem. Concr. Compos.* 32 (2010) 672.
- [18] D. Pedro, J. de Brito, R. Veiga, Mortars made with fine granulate from shredded tires, *J. Mater. Civ. Eng.* 25 (2012) 519.
- [19] A. Turatsinze, S. Bonnet, J.L. Granju, Potential of rubber aggregates to modify properties of cement based-mortars: improvement in cracking shrinkage resistance, *Constr. Build. Mater.* 21 (2007) 176.
- [20] A.C. Ho, A. Turatsinze, R. Hameed, D.C. Vu, Effects of rubber aggregates from grinded used tyres on the concrete resistance to cracking, *J. Cleaner Prod.* 23 (2012) 209.
- [21] C. Albano, N. Camacho, M. Hernández, A. Matheus, A. Gutiérrez, Influence of content and particle size of waste PET bottles on concrete behavior at different w/c ratios, *Waste Manage.* 29 (2009) 2707.
- [22] R.S. Ravindrarajah, A.J. Tuck, Properties of hardened concrete containing treated expanded polystyrene beads, *Cem. Concr. Compos.* 16 (1994) 273.
- [23] F. Tittarelli, C. Giosuè, A. Mobili, C. di Perna, S. Monosi, Effect of Using Recycled Instead of Virgin EPS in Lightweight Mortars, *Proc. Eng.* 161 (2016) 660.
- [24] B. Coppola, L. Courard, F. Michel, L. Incarnato, L. Di Maio, Investigation on the use of foamed plastic waste as natural aggregates replacement in lightweight mortar, *Compos. Part B-Eng.* 99 (2016) 75.
- [25] J.N. Eiras, F. Segovia, M.V. Borrachero, J. Monzó, M. Bonilla, J. Payá, Physical and mechanical properties of foamed Portland cement composite containing crumb rubber from worn tires, *Mater. Des.* 59 (2014) 550.
- [26] S. Herrero, P. Mayor, F. Hernández-Olivares, Influence of proportion and particle size gradation of rubber from end-of-life tires on mechanical, thermal and acoustic properties of plaster-rubber mortars, *Mater. Des.* 47 (2013) 633.
- [27] D.E. Ramírez-Arreola, C. Sedano-de la Rosa, N.B. Haro-Mares, J.A. Ramírez-Morán, A.A. Pérez-Fonseca, J.R. Robledo-Ortiz, Compressive strength study of cement mortars lightened with foamed HDPE nanocomposites, *Mater. Des.* 74 (2015) 119.
- [28] M. Záleská, J. Pokorný, M. Pavlíková, Z. Pavlík, Thermal properties of light-weight concrete with waste polypropylene aggregate, in: THERMOPHYSICS, 22nd International Meeting of Thermophysics 2017 and 4th Meeting of EnRe 2017, Terchova, Slovakia, 12–14 September 2017 2017 AIP Publishing Melville, NY, USA, 2017.
- [29] P. Scarfato, E. Avallone, L. Incarnato, L. Di Maio, Development and evaluation of halloysite nanotube-based carrier for biocide activity in construction materials protection, *Appl. Clay Sci.* 132 (2016) 336.
- [30] L. D'Arienzo, P. Scarfato, L. Incarnato, New polymeric nanocomposites for improving the protective and consolidating efficiency of tuff stone, *J. Cult. Heritage* 9 (2008) 253.
- [31] B. Coppola, L. Di Maio, P. Scarfato, L. Incarnato, Use of polypropylene fibers coated with nano-silica particles into a cementitious mortar, in *Polymer Processing with Resulting Morphology and Properties: Feet in the Present and Eyes at the Future*, Proceedings of the GT70 International Conference, Salerno, Italy, 15–17 October 2015, AIP Publishing, Melville, NY, USA, 2015.
- [32] EN 196-1, Methods of testing cement: Determination of strength, July, 2005.
- [33] EN 12390-7, Testing hardened concrete: Density of hardened concrete, June, 2002.
- [34] L. Di Maio, B. Coppola, L. Courard, F. Michel, L. Incarnato, P. Scarfato, Data on thermal conductivity, water vapour permeability and water absorption of a cementitious mortar containing end-of-waste plastic aggregates, Data in Brief (submitted).
- [35] EN 1015-18, Methods of test for mortar for masonry. Determination of water absorption coefficient due to capillary action of hardened mortar, December, 2002.
- [36] EN 12664, Thermal performance of building materials and products. Determination of thermal resistance by means of guarded hot plate and heat flow meter methods. Dry and moist products of medium and low thermal resistance, March, 2001.
- [37] EN 12667, Thermal performance of building materials and products. Determination of thermal resistance by means of guarded hot plate and heat flow meter methods, Products of high and medium thermal resistance, March, 2001.
- [38] S. Dubois, F. Lebeau, Design, construction and validation of a guarded hot plate apparatus for thermal conductivity measurement of high thickness crop-based specimens, *Mater. Struct.* 48 (2015) 407.
- [39] EN 1015-19, Methods of test for mortar for masonry. Determination of water vapour permeability of hardened rendering and plastering mortars, January, 1999.
- [40] ASTM C88-13, Standard Test Method for Soundness of Aggregates by Use of Sodium Sulfate or Magnesium Sulfate, ASTM International, West Conshohocken, PA, 2013.
- [41] P. Scarfato, L. Di Maio, M.L. Fariello, P. Russo, L. Incarnato, Preparation and evaluation of polymer/clay nanocomposite surface treatments for concrete durability enhancement, *Cem. Concr. Compos.* 34 (2012) 297.
- [42] O.Y. Marzouk, R.M. Dheilly, M. Queneudec, Valorization of post-consumer waste plastic in cementitious concrete composites, *Waste Manage.* 27 (2007) 310.
- [43] K. Hannawi, S. Kamali-Bernard, W. Prince, Physical and mechanical properties of mortars containing PET and PC waste aggregates, *Waste Manage.* 30 (2010) 2312.
- [44] S. Akçaözöğlü, C.D. Atiş, K. Akçaözöğlü, An investigation on the use of shredded waste PET bottles as aggregate in lightweight concrete, *Waste Manage.* 30 (2010) 285.
- [45] M.I. Khan, Factors affecting the thermal properties of concrete and applicability of its prediction models, *Build. Environ.* 37 (2002) 607.
- [46] L.H. Nguyen, A.L. Beaucour, S. Ortolá, A. Noumowé, Influence of the volume fraction and the nature of fine lightweight aggregates on the thermal and mechanical properties of structural concrete, *Constr. Build. Mater.* 51 (2014) 121.