

# Improving the Building Energy Efficiency and Thermal Comfort through the Design of Walls in Compressed Earth Blocks of Agricultural and Biopolymer Residues Masonry: A Recent Study

Etienne Malbila <sup>a,b\*</sup>, Simon Delvoie <sup>c</sup>, David Toguyeni <sup>d</sup>,  
Luc Courard <sup>c</sup> and Shady Attia <sup>e</sup>

DOI: 10.9734/bpi/rdst/v9/2852C

---

## ABSTRACT

The impact of wall construction materials on dwelling hygrothermal behavior and energy efficiency is investigated in this research. Most people want to live in a sophisticated ambiance in this modern age and spend massive investment on improving their buildings' inside condition. The building design was created in the Design Builder interface using three types of construction materials for the wall: CSEB of fonio straw and Shea butter cakes, cement blocks, and cut laterite blocks. Dynamic modeling with Energy Plus software was used to calculate the thermal comfort and overall amount of energy required for building cooling. The simulation was done using the meteorological characteristics of Ouagadougou city, and we discovered that the thermal behavior of the housing is influenced by the wall in earth-based simulations. The findings demonstrate that in housing with a CSEB of fonio straw and Shea butter cakes masonry wall, the number of warm thermal discomfort hours and cooling energy loads are reduced by an average of 10.60 percent and 93.86 percent, respectively, when compared to housing with a cement or cut laterite blocks masonry wall. In terms of the inside environment, the earth-based impact of this wall allows for an average internal temperature and indoor operating temperature of 28.64°C and 25.82°C, respectively. 6.54°C is attained as the average indoor temperature peaks dampening (i.e. 22.83 percent). As a result, these CSEB walls offer an effective contribution to the development of sustainable dwellings in a hot climate.

---

<sup>a</sup> *Laboratoire d'Energies Thermiques Renouvelables, (LETRE), Université Joseph KI-ZERBO, Ouagadougou, Burkina Faso.*

<sup>b</sup> *Université de Fada N'Gourma, Fada N'Gourma, Burkina Faso.*

<sup>c</sup> *Laboratoire de Matériaux de Construction (LMC), Université de Liege, Liege, Belgium.*

<sup>d</sup> *Laboratoire de Physique et Chimie de l'Environnement (LPCE), Université Joseph KI-ZERBO, Ouagadougou, Burkina Faso.*

<sup>e</sup> *Sustainable Building Design Laboratory, Université de Liege, Liege, Belgium.*

\*Corresponding author: E-mail: t.malbila@gmail.com;

**Keywords:** *Modelling and simulation; eco-materials; thermal comfort; energy efficiency; housing; hot region.*

## **NOMENCLATURES**

$\lambda$  : Thermal conductivity in  $W/m \cdot K$ ;  
 $C_p$  : Specific heat ( $kJ/kg \cdot K$ );  
 $\rho$  : Density in  $kg/m^3$ ;  
 $^{\circ}C$  : Celsius degree;  
 $K$  : Kelvin degree;  
 $T_{opm}$  : Average operative temperature (in  $^{\circ}C$ );  
 $U_{bat}$  : Overall heat transfer coefficient, ( $W \cdot m^{-2} \cdot K^{-1}$ );  
 $G$  : Coefficient of heat loss, ( $W \cdot m^{-3} \cdot K^{-1}$ );

## **ACRONYMS AND ABBREVIATIONS**

$A13FF$  : Clay material mixed with 3% of fonio straw ( $N^{\circ}1$ );  
 $A23FF$  : Clay material mixed with 3% of fonio straw ( $N^{\circ}2$ );  
 $A13RL$  : Clay material mixed with 3% of Shea butter cakes.  
 $BLT$  : Cut laterite blocks;  
 $BTC$  : Compressed Earth Blocks;  
 $CSEB$  : Compressed Stabilized Earth Blocks;  
 $CV$  : Split cooling capacity unit;  
 $LMC$  : Laboratory of Construction Materials;  
 $STD$  : Dynamic Thermal Simulation;

## **1. INTRODUCTION**

Since the building sector is the world's greatest user of materials and energy [1] and has sparked significant interest [2], the influence of the built environment on the climate and the earth's resources is critical. The rise in energy consumption in building design and construction, as well as environmental concerns, have prompted many present researchers to look into ways to reduce total CO<sub>2</sub> emissions, resulting in the development of numerous energy efficiency measures [3,4] and much more sustainable solutions [5]. The Positive Energy Building is announced as the contribution of the construction sector to the solution of the major problems facing humanity at the beginning of the 21st century: global warming, depletion of fossil energy resources, scarcity of raw materials, and the finiteness of our world in general [6]. The building efficiency codes are important regulatory tools that establish the minimum and maximum levels of energy efficiency for different building types [2]. According to [7], by controlling lighting, the energy saving of the original school building design was found most significant, and increased by 32% when the design was improved.

Local materials based on earth and natural resources are gradually giving way to concrete and its derivatives, which are now the most widely used building materials in the construction industry in Burkina Faso. Various considerations

contribute to this and increase the cost of construction and operation of buildings. Most people want to live in a sophisticated ambiance in this modern age and spend massive investment on improving their buildings' inside condition [8]. Indeed, the unsuitability of these imported materials with the climate leads to an increase in energy needs over the entire life cycle. Sustainable development is becoming increasingly important in the construction sector. Therefore, building techniques that reduce environmental impacts by minimizing industrial processes and using locally available materials, such as earth, are receiving a new impetus [9]. The authors in [9] presented a strengths, weaknesses, opportunities and threats analysis in order to assess and support the introduction of such a ZEB definition and framework.

A study on materials used in the building industry provides a basis for construction projects, but this must be done to local conditions so that all parameters are examined for optimal use. In Burkina Faso, the materials used in the current construction such as concrete, cement block, are characterized by poor thermal properties of solar radiation in hot regions. Instead of local materials based on natural soil or stabilized with industrial, forestry, and agricultural by-products [10-12]

This study is part of this dynamic and focuses on the use of local build materials in a dry tropical climate such as that of Burkina Faso. For [8], in construction, finding energy-saving problems can be done using a thermal insulator's intelligent design. Building constructed with local material present nowadays interest in the perspective of sustainable development [13], as they are better adapted to the local climate. Implementing walls in adobe or CSEB is an alternative a sustainable construction [14]. Indeed, the physical properties of local materials interact with each other and integrate other variables such as cultural construction practices and traditional technologies (knowledge and expertise) to form a coherent construction set for humans, the environment, and the climate. Because maintaining the balance between the human body and its environment is one of the main requirements for health, safety, and comfort [15]. And the current development challenge is based on responsible energy consumption. The temperature and humidity present in the building can cause energy consumption, degradation of building materials, and a feeling of discomfort for humans [16]. The management of thermal comfort must meet several requirements, including technical requirements. ASHRAE defined Thermal comfort as that condition of mind which expresses satisfaction with the thermal environment and is assessed by subjective evaluation [17,18]. The study or the choice of material for a wall is important because [19] the wall thermal performance influences housing thermal comfort and energy consumption. Moussa, H.S., and al, shows that the number of hours of warm and humid thermal discomfort was impacted for stabilized CEB based masonry in comparison with cement-based masonry [20].

The nature of the building materials is a significant factor, whether natural or composite. To achieve sustainable and green technology in construction, more alternative methods were produced to replace the conventional construction

materials which lack concern on elements of sustainability especially on humans, economics, and the environment [2,8,21]. According to authors [10], Nere pod stabilization saves on 20 to 43% energy depending on the mixing rate compared to laterite and the decrement factor and the time lag are better when the wall thickness increases. It's in this context that this research, we highlight the compare the influence of wall in CSEB with fonio straw and Shea butter cake, cement blocks, cut laterite blocks, on the habitat thermal behaviour. Thus, it's planned to design a housing model to determine whether thermal comfort is achieved; that by varying building walls material and their thermophysical properties.

## 2. MATERIALS AND METHODS

### 2.1 Wall Thermal Performance

Building envelope participates in providing thermal comfort to users and in the optimal management building energy consumption [22]. For building envelope thermal performance study, several physical parameters are to be considered. It is important to define suitable descriptive indicators. Indeed, criteria allowing to evaluate the energy performance are defined, like Building annual energy performance and occupants thermal comfort [23]. In this study the main difference between different walls are the material, the component and the size. For this purpose, the thermal resistance of the evaluated wall are determined by following equation:

#### 2.1.1 Thermal resistance of each material component ( $R_T$ )

The thermal resistance (RT) characterizes the material ability to slow down heat transfer by conduction. It is calculated with the following equation:

$$R_T = \frac{e}{\lambda} \tag{1}$$

With:

- $R_T$ , in  $m^2.K/W$  Thermal resistance;
- $e$ , thickness in  $m$
- $\lambda$ , thermal conductivity in  $W/(m.K)$ .

#### 2.1.2 Wall global thermal resistance ( $R_{tp}$ )

It characterizes the sum of heat transfer by conduction within the material and surface heat exchange by convection and radiation.

$$R_{tp} = R_{si} + R_{se} + \Sigma(e/\lambda), \text{ in } m^2.K/W \tag{2}$$

Where **R<sub>si</sub>** and **R<sub>se</sub>** are respectively the walls internal and external thermal resistances.

They characterise the proportion of heat exchange that takes place at the surface of the wall by radiation and convection. It depends on the direction of the heat flow and the orientation of the wall. The following expressions can be applied:


$$\begin{aligned} R_{Si} &= 1/h_i \text{ et} \\ R_{Se} &= 1/h_e \end{aligned} \tag{3}$$

Where  $h_i$  and  $h_e$  represent respectively internal and external surface heat coefficient in  $W/(m^2.k)$ .

In the present study, they are identical for the different cases studied. So the comparison will focus on the  $\Sigma (e/\lambda)$  component of equation 2.

## 2.2 Modelling and Simulation Frameworks

The numerical study consists of the modelling of a building used for socio-economic housing in Ouagadougou in Burkina Faso and the simulation of its energy and hygrothermal behaviour. Indeed, It's subject of wall influence according to the type of construction material used. This influence will be established through the thermal parameters obtained such as temperature, relative humidity, and the necessary energy quantity to maintain habitat thermal comfort. The period considered for this study is the month of April, which is the hottest month in the dry tropical climate zone. This study is completely numerical and we have established a conceptual framework for a descriptive study of our working methodology based on [24]. Fig. 1 shows our methodology's main areas that will be described in the following paragraph.

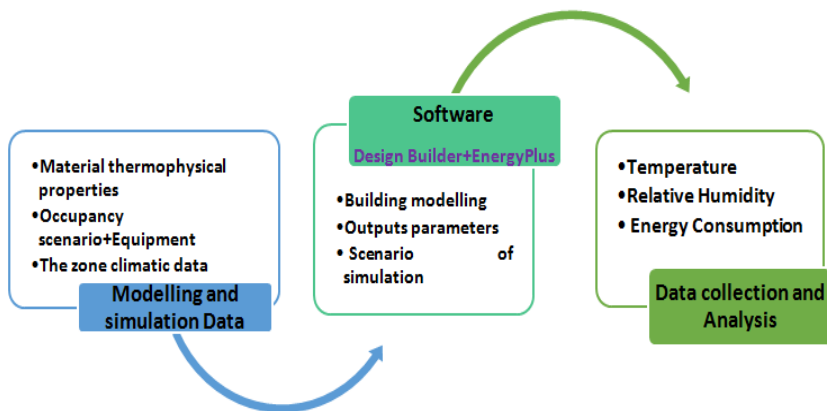



**Fig. 1. Study conceptual framework**

### 2.3 Building Description

Building constructed with local materials is nowadays of interest in the logic of sustainable development [13]. According to [25] the ultimate material efficiency aim is not to use lower materials quantity, but to reduce the impacts associated with their use. Our study aims at analyzing walls constructed with local composite materials (earth + natural cokes) impact on residential building thermal comfort and energy performances. To minimize annual energy consumption, a shorter-term objective is to design solids baselines on building envelopes (wall, floors, and roof) [26]. In search of energy efficiency, it's possible to investigate the choice of construction materials, building insulation, and the optimization of equipment operation. May the current development challenge be based on responsible energy consumption?

On an architectural level, the building to be assessed is a common standard villa type F3 used in the city of Ouagadougou and characterized by a living area of 56.77m<sup>2</sup> as designed in Fig. 2. For this purpose, the building will be considered in the dry tropical climatic conditions of the area of the Ouagadougou weather database file. The building description is shown in Fig. 2 below:

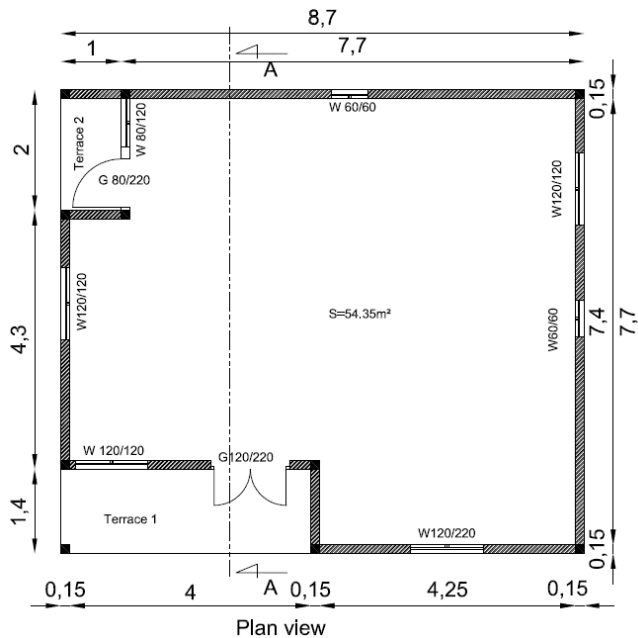

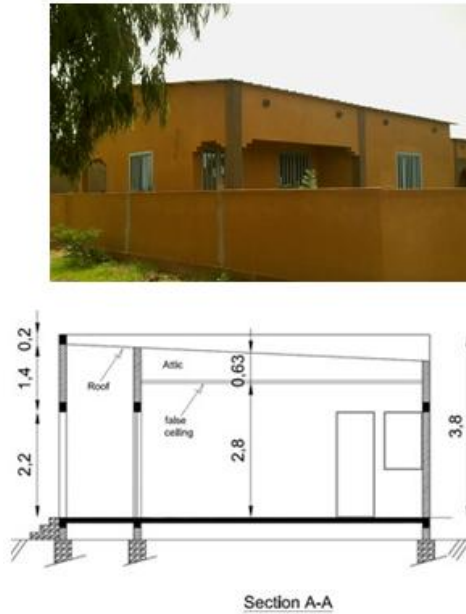

**Fig. 2. Building architectural plans**

Table 1 presents the properties of the construction materials used in this study.

**Table 1. Material thermo-physical properties [24,27] RT2000 and IEPF 2002**

N°	Material Description	$\lambda$ (W/m. K)	Cp (kJ/kg. K)	$\rho$ (kG/m <sup>3</sup> )	Thickness (cm)
1	Air gap(Attic)	0.192	1.00	1.218	62.5
2	Cement block	0,67	880	1250	15
3	Cut laterite block (BLT)	0.85	0.73	1850	15
4	CSEB -A13FF	0.504	1.967	1960	9
5	CSEB -A23FF	0.594	1.967	1904	9
6	Reinforced concrete paving	1.7	0.653	2400	10
7	Cement mortar (plaster)	0.87	1.05	2200	2.5
8	CEM-A13RL plaster	0.737	1.578	2008	2.5
9	False ceiling plaster	0.11	1.3	400	0.5
10	Floor tile	1.25	1.00	2000	0.7
11	Subfloor	1.21	1.00	1900	5
12	Single and clear glazing	0.96	0.837	2500	0.5
13	Isoplane door	0.12	2.51	593	2.5
14	Sheet metal	828	0.93	2700	0.07

The developed soil bricks can be used for affordable and sustainable housing construction across the world, particularly in developing countries [21,28,29].

Table 1 shows the properties of common construction material and local materials such as the CSEB-A13FF, CSEB-A23FF, and CEM-A13RL in Fig. 3.

These are local construction materials consisting of well define mixture of clay and agricultural cakes and bio-polymer and whose thermo-physical and mechanical properties are characterized by [24]. This study will investigate the influence of these composite materials on the habitat thermal behaviour and compare them with cement block and cut laterite blocks (BLT) walls.

## **2.4 Choice and Description of the Simulation Tools**

Building simulation software tools are mostly used by the building designers and engineers to explore various design alternatives under varying climatic conditions, internal gains, building envelope characteristics, building geometry, heating, ventilation and cooling (HVAC) system specifications, operation schedules, and control strategies, etc. [30].

In perspective to reach this study objective, the comparative approach is used by an analyzing process based on dynamic energy simulation with Design Builder tool integrated to Energy+ calculation engine [31] available in Sustainable Building Design Lab of Liege University. The building energy and environmental performances and thermal comfort need reliable dynamic thermal simulation tools [32]. And the interface Design Builder/Energy+ allows us to perform dynamic simulations on the thermal and energy behaviour of buildings, as well as to obtain results on energy loads, indoor thermal environment, and discomfort level. Emergent energy and environmental questions related to a building's thermal comfort and indoor air quality require accurate knowledge of temperatures and air movements inside buildings [26]. For this purpose, the modelled building is considered a single thermal zone.


## **2.5 Simulations Conditions**

The simulation conditions considered the occupancy scenario, the installed equipment operation, the input data, and thermal comfort physical parameters. Moreover, the life cycle analyses showed the importance of the operational phase in building energy balance concerning construction and end-of-life phases [33,34].

In the present study, the building energy and thermal dynamic simulation were done considering four (4) person occupancy scenario and a split system for air conditioning equipment. The required thermal comfort conditions are indoor temperature between 26°C and 29°C and average relative humidity (HR) % of 50%.

A total of four types of walls envelope materials were studied. The description of building walls components is presented in Table 2.



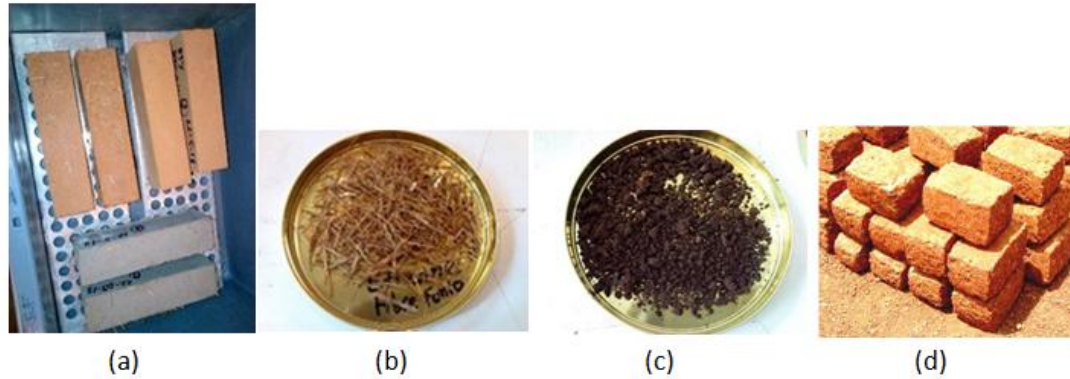

**Fig. 3. (a) CSEB of (b) fonio straw and (c) Shea butter cakes, (d): Cut laterite blocks**

The comparative study approach was chosen to evaluate the thermal and energy performance of the building constructed with walls in CSEB formulated by at the Laboratory of Construction Materials of Liege University in comparison to other common construction materials.

The wall's thermal properties have both great influences on wall temperature distribution and heat transfers from the wall [31]. The wall's nature-level adaptation is of particular interest in solar radiation management, creating a barrier between the inside and outside of a room that modifies the thermal exchanges. The walls envelope materials component, their thickness, color, coating, and thermo-physical properties are the main factors involved in their evaluation [15]. Three (03) types of building materials were selected: cement blocks and cut laterite blocks (BLT) commonly used and a CSEB composite material "earth + agricultural cakes and biopolymer" and the study concerned four (04) cases of walls envelope.

**Table 2. Wall envelope and construction materials descriptions for the case studied**

Designation	Base case	Case 1	Case 2	Case 3
Wall	Cement mortar plaster+Cement block+Cement mortar plaster (=20cm)	BLT (17.5cm)	CEM-A13RL+CSEB-A13FF + CEM-A13RL (19cm)	CEM-A13RL+CSEB-A23FF + CEM-A13RL (19cm)
Roof	Sheet tile (7/10 mm)			
Windows	Single clear glazing and metallic frame (5mm) and size 120cm*120 cm et 60cm*60 cm			
False ceiling	Plaster false ceiling (5 cm)			
Ground	Reinforce concrete paving+ cement mortar+ floor tile(=15.7cm)			

The characteristics of the roof, openings, and ground floor are kept identical for all studied cases. The only variation concerns the walls envelope, which by the construction materials used and the number of layers. The envelope material variants studied are described in Table 3 below.

**Table 3. Synthesis of wall variant layer modelled in Design Builder**

Variant	Wall layer description			
	Outer layer	Main layer	Inner layer	Total thickness(cm)
Base case	Cement mortar	Cement blocks	Cement mortar	20
Case 1	-	Cut laterite block	Cement mortar	17.5
Case 2	CEM-A13RL Mortar	A13FF	CEM-A13RL Mortar	19
Case 3	CEM-A13RL Mortar	A23FF	CEM-A13RL Mortar	19

This study aims to contribute to local building materials valuation, given that no one can progress by ignoring the richness of its heritage. And by developing a scientific understanding of traditional know-how we can help to develop new architectural solutions inspired by tradition [15]. The simulation outputs collected are the indoor discomfort hour's number, the air conditioning energy demand, the indoor, and the average operating temperature for twelve months. To do compare results, on focusses of April month. Indeed, in this region, the most difficult periods are the maxima of April and June, when a supplement of artificial air conditioning is inevitable [35] and April is taken from the hot period when temperatures are high and humidity low [36].

### 3. RESULTS

#### 3.1 Wall Construction Material Thermal Performance

The thermal resistance and heat flow of the walls are determining factors in the influence of the wall on the overall thermal behaviour of a building. These parameters for the three wall types are summarized in the Table 4 below:

**Table 4. Comparison of wall construction material thermal performance**

Envelope type	Wall component	RT of each component (m <sup>2</sup> .K/W)	RT of the wall (m <sup>2</sup> .K/W)	Up W/ (m <sup>2</sup> .K)	φ (kW)
<b>Cement blocks masonry</b>	Cement Mortar	0.0287	0.230	4.35	6.492
	Blocks	0.172			
	Cement Mortar	0.029			
<b>CSEB masonry</b>	Motar	0.034	0.323	3.10	4.312
	Blocks	0.255			
	Motar	0.034			
<b>Cut laterite blocks masonry</b>	Blocks	0.206	0.206	4.86	8.9


Table 4 shows that the thermal resistances and heat flows are better for the wall in earth-based in comparison to the other walls i.e. walls in cement blocks and cut laterite blocks. Indeed the gain in thermal flow for the wall in earth-based is respectively 33.58% and 70.67% in comparison to cement blocks wall and cut laterite blocks.

#### 3.2 Indoor Temperature Evolution during the Hot Period


Building thermal response depends on the design, chosen construction materials, and operating conditions. This study focuses on the

influence of construction materials for walls on housing indoor temperature evolution.


Below Figs. 4 to 7 give modelled building interior temperatures evolution profile for each case of wall envelope studied.

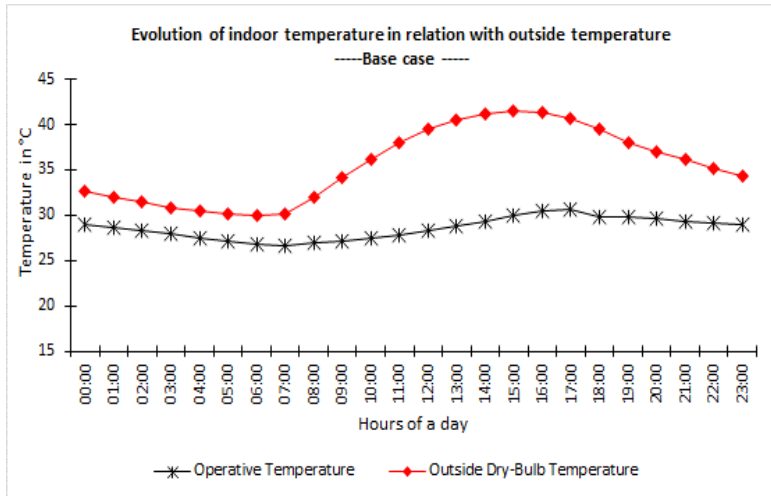


**Fig. 4. Indoor temperature evolution profiles in habitat with cement blocks wall (Base case)**

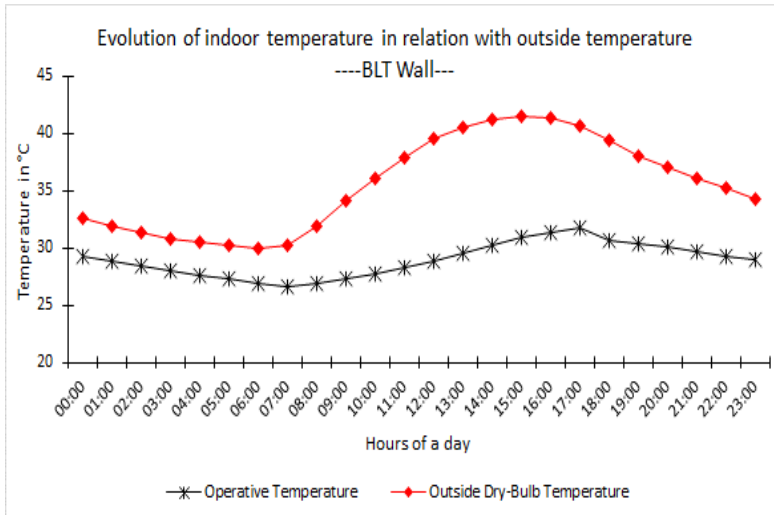

**Fig. 5. Indoor temperature evolution profiles in habitat with BLT Wall (Case 1)**

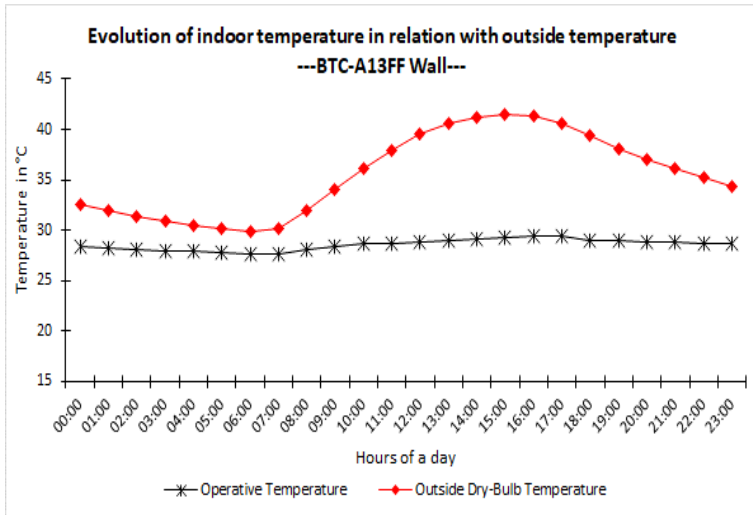


**Fig. 6. Indoor temperature evolution profiles in habitat with BTC-A13FF Wall (Case 2)**

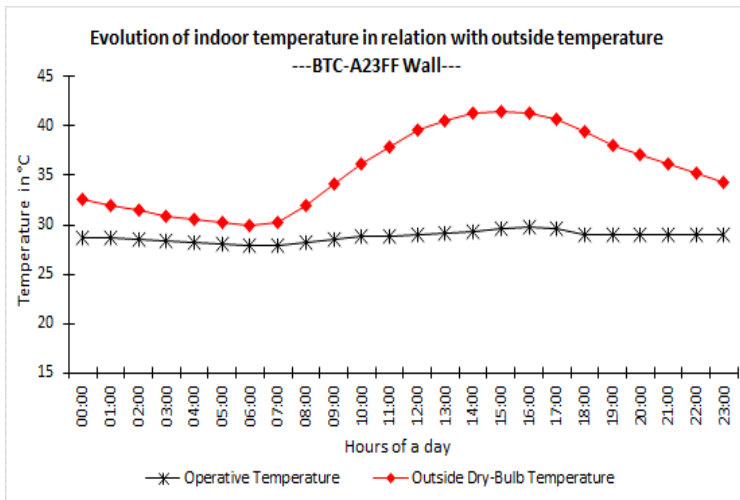


**Fig. 7. Indoor temperature evolution profiles in habitat with BTC-A23FF Wall (Case 3)**

Below Figs. 8 and 9 present indoor temperature evolution about ambient temperature respectively over 10 days and 24 hours during April month.

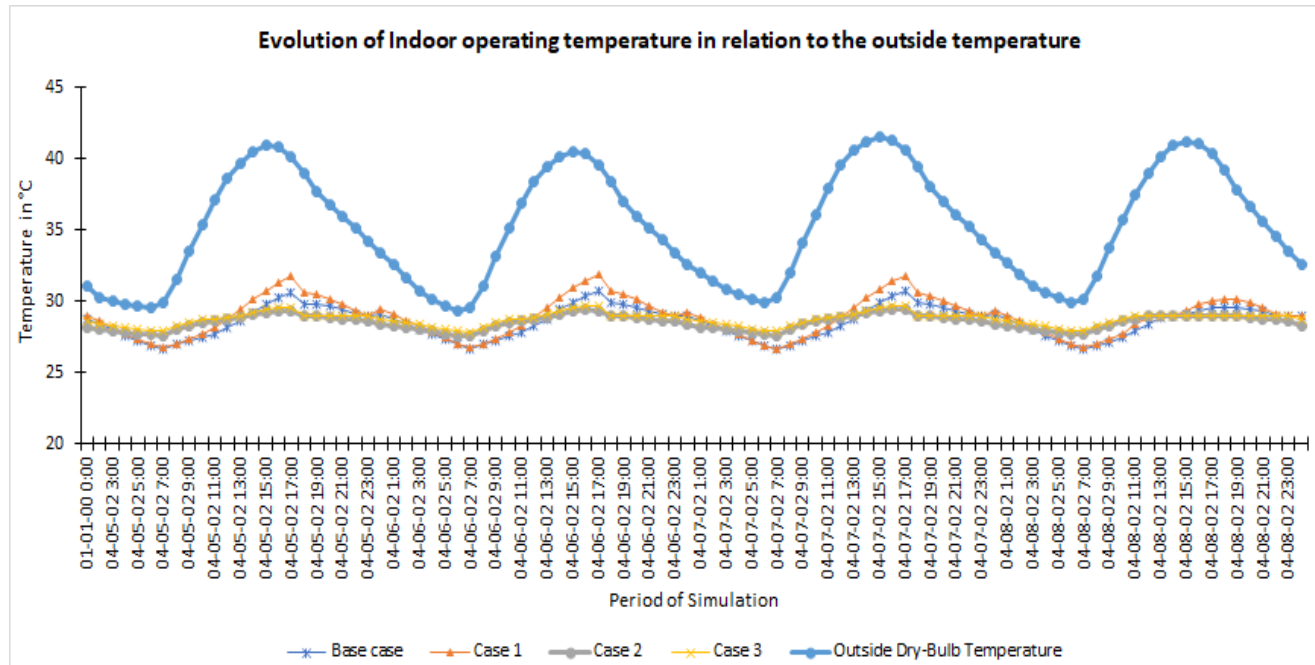

**Fig. 8. Comparison of Indoor temperature evolution in relation with external temperature for all wall cases studied (from 4-9<sup>th</sup> April)**

Fig. 8 presents the comparison of indoor temperature evolution profiles for walls cases studied and in relation with ambient temperature over 10 days during April month of reference year in dry tropical climate condition.

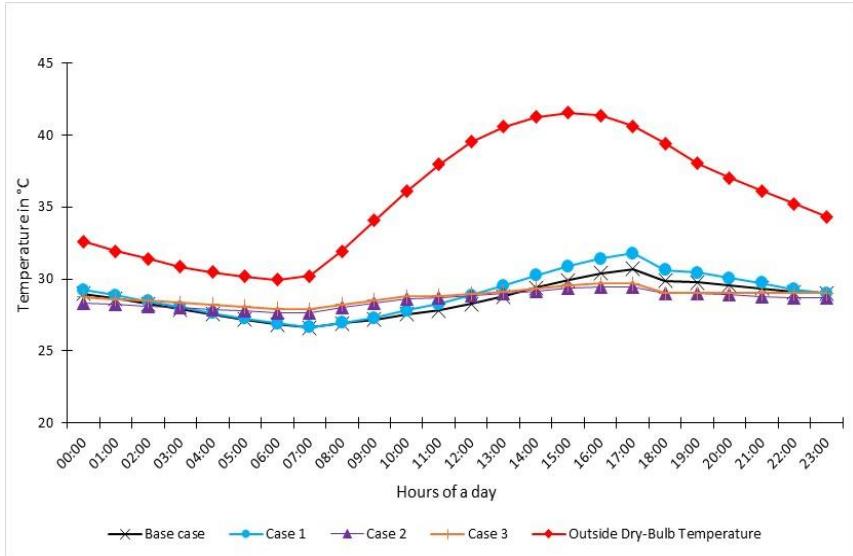

**Fig. 9. Indoor temperature evolution in relation with ambient temperature over 24 hours**

Fig. 9 presents the comparison of indoor temperature evolution profiles for the walls cases studied and about ambient temperature over 24 hours during the day of 7<sup>th</sup> April in dry tropical climate conditions.

The curves on all figures describe identical indoor temperature evolution profiles whatever the type of building wall construction materials used. The average indoor temperature is between 28.52°C to 28.91°C and is lower than ambient temperature. This indicates that all walls construction materials used allow for building indoor temperature peaks dumping during considered period, especially during heat period. Then, the average percentage of temperature dumping over the considered period is 23.28%, 21.67%, 23.32%, and 22.35% respectively for the base case, variants 1 to 3 studied.


### 3.3 Discomfort Hours Evaluation in Building

Thermal comfort is a complex notion defined as the occupant satisfaction sense and which depends on several physical and physiologic parameters. For physical parameters, temperature and relative humidity are used to appreciate and evaluate the level of thermal comfort according to the climatic conditions. The

simulation over the year allows us to evaluate the number of thermal discomfort hours as shown in below Fig. 10.


Fig. 10 shows the number of building's indoor discomfort hours as a function of the type of envelope wall. From this graph and depending on the wall construction material, the number of building thermal discomfort hours is higher when the envelope wall construction materials are cement blocks (Base case) or cut laterite blocks(Case 1) than Compressed stabilized earth blocks (Case 2 and 3).

Fig. 11 presents the building's indoor warm thermal discomfort hours decrease rate in the four cases studied. As shown in Fig. 11, the number of warm thermal discomfort hours is lower for walls in earth-based i.e. with CSEB-A13FF or CSEB-23FF, and coated with composite earth material (CEM-A13RL) masonry. These walls in earth-based reduce the number of warm discomfort hours in housing from 9.02% to 12.19% compared to walls in cement-based material.

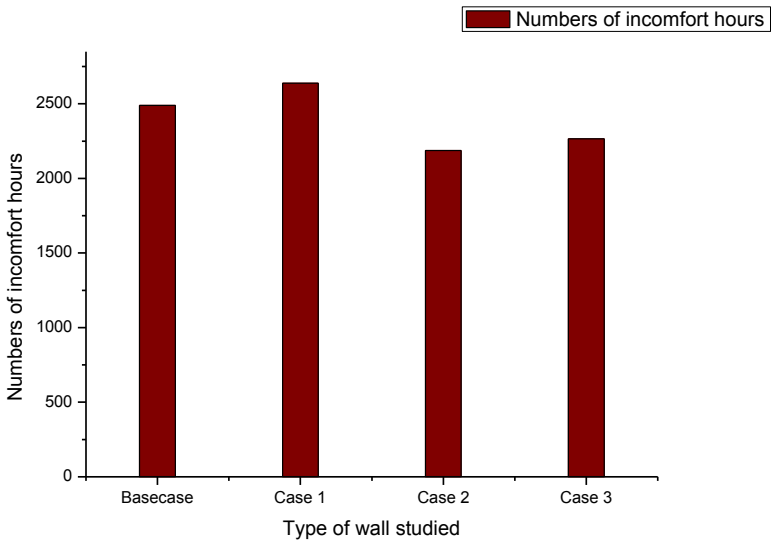

**Fig. 10. Building indoor discomfort hours about wall construction materials**




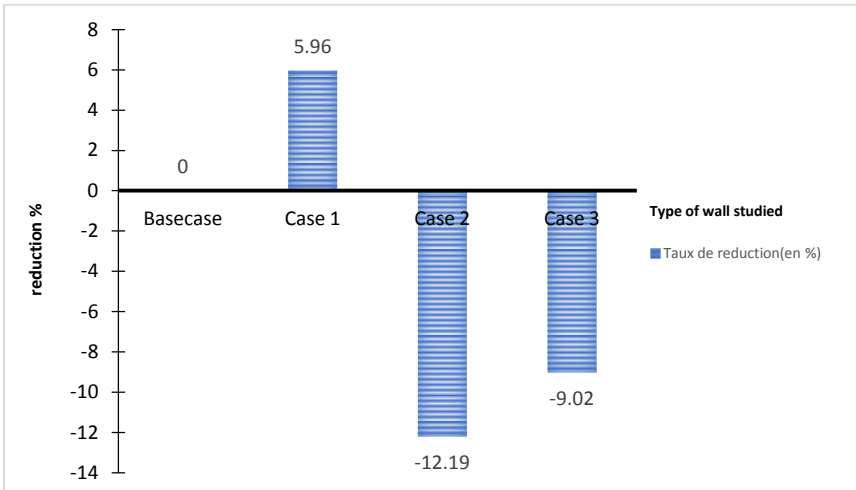

**Fig. 11. Building indoor discomfort hours decrease rate in relation with wall construction material**

### 3.4 Cooling Energy Requirement in Building

Fig. 12 presents the building air conditioning (AC) quantity requirement graph in the four cases of wall construction materials studied.

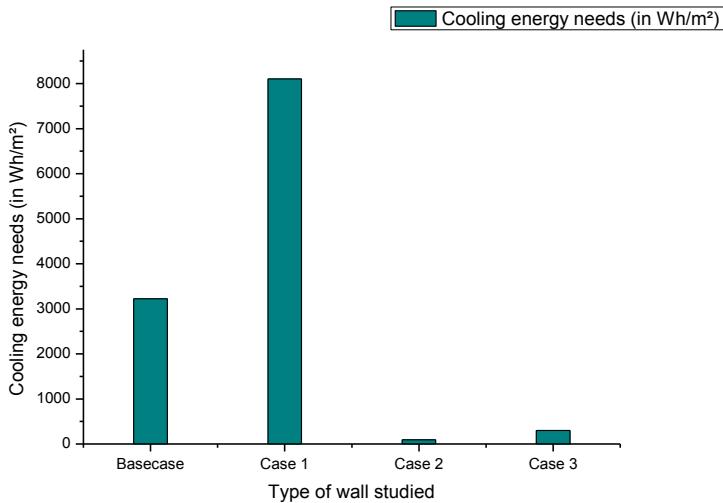

**Fig. 12. Building cooling energy needs in relation to wall construction materials**

As shown in Fig. 12 graph, the building cooling energy demand is lower in cases 2 and 3 which walls are constructed with CSEB-A13FF and CSEB-23FF and coated with composite earth material (CEM-A13RL). The cooling energy needs are estimated at 94.95wh/m<sup>2</sup>, 300.51Wh/m<sup>2</sup>, 3223.12Wh/m<sup>2</sup>, and 8104.56Wh/m<sup>2</sup> respectively for cases 2, 3, and base case and case 1.

## 4. DISCUSSION

### 4.1 Summary of Main Findings

The building thermal and energy behavior were studied in two stages by modelling the habitat on Design Builder and then the simulation of different cases of envelope wall by integrating Energy Plus. The simulation outputs collected are the indoor discomfort hour's number, the air conditioning energy demand, the indoor, and the average operating temperature. Table 5 summarizes the values obtained for each envelope wall variant studied.

**Table 5. Synthesis of energy and thermal simulation results**

Variant	Number of discomfort hours		Cooling energy needs		$T_{opm}$ (in °C)
	(in hour)	Decrease %	(in Wh/m <sup>2</sup> )	Decrease %	
Base case	2490	-	3223.12	-	25.95
Case 1	2638.50	+5.96	8104.56	+151.45	26.25
Case 2	2186.50	-12.19	94.95	-97.05	25.71
Case 3	2265.50	-09.02	300.51	-90.67	25.92

Table 5 shows that operative temperature (25.71°C-25.95°C), cooling energy needs (94.95 - 300.51 Wh/m<sup>2</sup>), and the discomfort hour's number (2186.50-2265.50 hours) are lower in building modelled with CSEB walls than cement or cut laterite blocks walls. Therefore, based on these three selected criteria, the Building thermal and energy behavior is better with walls variants 2 and 3 i.e. in wall in earth-based. By keeping housing other constant parameters, we noticed that the envelope construction materials choice is important in building energy and thermal comfort performance search.

The analysis of the results indicates an average reduction of 10.60% of the warm thermal discomfort hours and 93.86% in thermal loads with an average operating temperature between 25.71°C and 25.92°C when using CSEB to fonio straw with coatings of CEM with 3% Shea butter cakes. Moreover, the indoor temperatures are between 28.52°C and 28.91°C (Figs. 8 and 9), i.e. an average difference of 0.16°C to 0.39°C from variant 3 to the base case. These operating and indoor temperatures are below those of the building constructed either in cement or cut laterite blocks. This performance of building stabilized soil material was observed by [37] who find that the thermal performance coefficients Ubat and G are lower in earthen constructions (adobe, BTC, BLT) than in modern constructions

(cement block). However, the results obtained can be reinforced by complementary options in terms of roof type, building orientation, and openings.

This local eco-materials option permit therefore in line to meet having internal temperatures with the Ouagadougou building thermal comfort zone (26-30°C), obtained by [38] through the use of insulation materials such as cotton and straw coupled with BLT giving temperatures between 28.7°C to 30.5°C for cotton, and 29.8°C to 31°C for straw. Thus, the present study results increase the scientific knowledge on CSEB with natural local resources and their potential impacts on building's thermal and energetic performance. This could contribute to Burkina Faso and other UEMOA (West African Economic and Monetary Union) country governments for the integration political of building energy efficiency requirements code in their area [39]. Indeed, building with earth materials has many advantages, such as its availability and required thermo-physicals and thermal properties in habitat construction, cost reduction, and environmental impacts reduced by minimizing industrial processes [9].

#### **4.2 Strength and Limitations**

We studied the wall envelope influence on building thermal and energetic global behavior. The study results show that earth material improved with fonio straw and Shea butter cakes contribute to better thermal comfort et reduce energy consumption in the habitat. It appears that:

- the walls in Compressed earth blocks stabilized with fonio straw (CSEB-A13FF or CSEB-A23FF) and coated by composite shea butter cake and earth material (CEM-A13RL formulated by [24] offer good average interior and operating temperatures;
- the number of discomfort hours and the energy requirements for air conditioning is reduced;
- the choice of the type of envelope construction materials is very decisive in the search of the thermal comfort achievement;

These results contribute to the valuation of local building materials in the hot region but this study remains in a numerical study by simulation case and does not take into account:

- recent meteorological data of the study area ;
- separately the building different pieces.

#### **4.3 Implication on Practice and Research**

The results obtained show that the building industry can rely on the use of local building materials to address the duality of thermal comfort and energy consumption search the hot region context. For example, sustainability guidelines for energy and carbon emissions suggest that we need to halve our energy use from 2000 to 2050 [40,41]. In this context, it's essential to reduce

housing operating temperature and construction materials production energy used.

In the use of research prospects, we will be interested in:

- In-situ instrumentation of housing built with wall envelope in Compressed earth blocks stabilized with fonio straw (CSEB-A13FF or CSEB-A23FF) and coated by composite shea butter cake and earth material (CEM-A13RL) ;
- CSEB-A13FF/CSEB-A23 and CEM-A13RL adhesion characterization when used for composite wall envelope. The presence of the rendering is important and its hold on the wall structure must be perfect. For the rehabilitation of old houses, the coating of aerogel-based rendering considerably reduces energy consumption [42].
- In-situ CEM-A13RL coating durability and repellency characterization on an existing building in adverse weather conditions [43].

## 5. CONCLUSION

The best way for the construction industry is to explore the use of natural and industrial secondary resources to provide new materials for sustainable construction. The choice of building materials is determined by their properties, cost, and accessibility. This paper deals with the influence of the local materials for walls on housing behavior by numerical study. Then the comparative study concern three types of construction material for wall, that are compressed earth block, cut laterite blocks, and cement blocks. The results indicate that walls in Compressed earth blocks stabilized with agricultural cakes (fonio straw) and bio-polymer (Shea butter cake or cakes) give the housing advantageous thermal comfort and energy consumption compared to walls in cement or cut laterite blocks. More specifically, the main conclusion can be drawn:

- The wall in earth-based material (CSEB) offer the reduction by 10.60% of the warm thermal discomfort hours in housing;
- The wall in earth-based material (CSEB) offers a reduction by 93.86% in thermal loads with an average operating temperature between 25.71°C and 25.92°C.

Indeed, by using this wall in local composite material, the housing indoor temperature remains within the limits prescribed for dry tropical climates thermal comfort, with a significant reduction of discomfort hour's number and air conditioning energy requirements. Then, the compressed stabilized earth blocks of fonio straw and Shea butter cakes presents an environmentally sustainable alternative that avoids the use of energy-intensive during the building life cycle. This study highlights the influence of local eco-materials on housing thermal behavior and its contribution to building energy efficiency.

## **ACKNOWLEDGEMENT**

This study was conducted as part of the SERAMA program for Secondary Resources valuation for Sustainable Construction. This research was completely founded by the “Academie de Recherche et d’Enseignement Supérieur (ARES)” in Laboratory of Construction Materials (LMC) and in Sustainable Building Design Lab Liege University. The author would like to acknowledge the support of the Institute of Environmental Engineering and Sustainable Development (IGEDD) of the University Joseph KI-ZERBO during the project submission

## **COMPETING INTERESTS**

Authors have declared that no competing interests exist.

## **REFERENCES**

1. Marteinsson B. Materials and energy use in buildings. Proceedings of the 9th International Conference on Durability of Building Materials and Components. 2002;17-21.
2. Chen Austin M, Chung-Camargo K, Mora D. Review of Zero Energy Building Concept-Definition and Developments in Latin America: A Framework Definition for Application in Panama. *Energies*. 2021;14(5647):1-29.
3. Vukadinović A, Radosavljević J, Đorđević A, Petrović N. Effects of the geometry of residential buildings with a sunspace on their energy performance. *Facta universitatis-series: Architecture and Civil Engineering*. 2019;17(1):105-18.
4. Kouakou M-SLP, Kouamé AN, Doubi BIHG, Méité N, Kangah JT, Zokou EP, Konan LK, Andji-Yapi YJ. Characterization of Two Clay Raw Materials from Côte d’Ivoire with a View to Enhancing Them in Eco-Construction. *Journal of Minerals and Materials Characterization and Engineering*. 2022;10:198-208.
5. Kouakou M-SLP, Kouamé AN, Doubi BIHG, Méité N, Kangah JT, Zokou EP, Konan LK, Andji-Yapi YJ. Characterization of Two Clay Raw Materials from Côte d’Ivoire with a View to Enhancing Them in Eco-Construction. *Journal of Minerals and Materials Characterization and Engineering*. 2022;10:198-208.
6. Fréhel D. Bâtiments tertiaires à énergie positive: Analyse critique et perspectives pour 2020 et au delà,” Paris; 2013
7. Kang JE, Ahn KU, Park CS, Schuetze T. Assessment of passive vs. active strategies for a school building design. *Sustainability*. 2015 Nov;7(11):15136-51.
8. Vijayan DS, Mohan A, Revathy J, Parthiban D, Varatharajan R. Evaluation of the impact of thermal performance on various building bricks and blocks: A review. *Environmental Technology & Innovation*. 2021 Aug 1;23:101577.

9. Malbila E, Delvoie S, Toguyen D, Courard L, Attia S. Improving the Building Energy Efficiency and Thermal Comfort through the Design of Walls in Compressed Earth Blocks of Agricultural and Biopolymer Residues Masonry. *Current Journal of Applied Science and Technology*. 2022 Jan 1;40(45).
10. Imbga KB, Ouédraogo E, Sambou V, Kieno FP, Ouédraogo A, Bathiebo DJ. New Materials for Thermal Insulation in Rural Construction. *Current Journal of Applied Science and Technology*. 2018;29(4):1-0.
11. Zoma F, Yonli FH, Malbila E, Toguyeni DY, Hassel IB. Adding Hydrated Lime in a Material Made of Clayey Soil and Fibres: Formulation and Effects on Thermo-Mechanical Properties. *Journal of Minerals and Materials Characterization and Engineering*. 2020 May 28;8(03): 149.
12. Araya-Letelier G, Gonzalez-Calderon H, Kunze S, Burbano-Garcia C, Reidel U, Sandoval C, Bas F. Waste-based natural fiber reinforcement of adobe mixtures: Physical, mechanical, damage and durability performance assessment. *Journal of Cleaner Production*. 2020 Nov 10;273:122806.
13. El Nabouch R, Bui QB, Perrotin P, Plé O, Plassiard JP. Modélisation numérique de structures en pisé: analyses et recommandations. *InRencontres Universitaires de Génie Civil 2015* May 26.
14. Buitrago AA, Vinasco GM. Título: Muretes no estructurales en bloques de tierra comprimida (BTC) de cenizas volcánicas, como material alternativo para construcciones sostenibles Title: Non-structural walls in compressed earth blocks (BTC) of volcanic ash, as an alternative material for sustainable.
15. Chelghoum Z, Belhamri A. Analyse des propriétés thermiques des matériaux de construction utilisés dans la ville de Tamanrasset. *Sciences & Technologies D*. 2011;33:47-56.
16. Kazemi M, Boukhelkhal I, Kosinski P, Attia S. Heat and moisture transfer measurement protocols for building envelopes. *Sustainable Building Design Lab*; 2021 Aug 2.
17. ASHRAE, Thermal Environmental Conditions for Human Occupancy. ANSI/ASHRAE Standard 55, American Society of Heating, Refrigerating and Air-Conditioning Engineers. Atlanta; 2004.
18. Maamar H. Choice of Orientation and Construction Materials to Improve the Thermal Performance of Buildings.. University Abou-Bekr Belkaïd, Tlemcen; 2016.
19. Jin X, Zhang X, Cao Y, Wang G. Thermal performance evaluation of the wall using heat flux time lag and decrement factor. *Energy and Buildings*. 2012 Apr 1;47:369-74.
20. Moussa SH, Nshimiyimana P, Hema C, Zoungrana O, Messan A, Courard L. Comparative study of thermal comfort induced from masonry made of stabilized compressed earth block vs conventional cementitious material. *Journal of Minerals and Materials Characterization and Engineering*. 2019 Oct 22;7(385-403):385-403.
21. Abdullah ES, Mirasa AK, Asrah H, Lim CH. Review on interlocking compressed earth brick. *InIOP Conference Series: Earth and*

- Environmental Science 2020 Apr 1 (Vol. 476, No. 1, p. 012029). IOP Publishing.
22. Malbila E, Zoma F, Toguyeni DYK, Compaore C-v. M, Bathiebo DJ. Developing Double Walls System to Improve Building Energy Performances in Dry Tropical Climates,” IRA-International Journal of Applied Sciences. 2021;16(03):39-52.
  23. Gossard D, Bonte M, Lartigue B, Thellier F. Optimisation thermique de l’enveloppe de bâtiment en vue de maximiser sa performance énergétique. InCongres Francais de thermique (SFT), Bordeaux, France. 2012;536-542.
  24. Mabila E, Delvoie S, Toguyeni D, Attia S, Courard L. An Experimental Study on the Use of Fonio Straw and Shea Butter Residue for Improving the Thermophysical and Mechanical Properties of Compressed Earth Blocks. Journal of Minerals and Materials Characterization and Engineering. 2020 May 15;8(2):107-32.
  25. Lifset R, Eckelman M. Material efficiency in a multi-material world. Philosophical Transactions of the Royal Society A: Mathematical, Physical and Engineering Sciences. 2013 Mar 13;371(1986):20120002.
  26. Amara S, Benmoussat A, Benyoucef B, Nordell B. Evaluation des besoins énergétiques de chauffage et climatisation d’un bâtiment pour le site de Tlemcen. InJITH 2007 2007 Aug (p. 5p). ENSTIMAC.
  27. Toguyeni DY, Malbila E. Parametric Study by Dynamic Simulation of the Influence of the Air Infiltration Rate and the Convective Thermal Transfer Coefficient on the Thermal Behavior of Residential Buildings Built with Cut Lateritic Blocks. Journal of Energy and Power Engineering. 2018;12:177-85.
  28. Salih MMA. Behaviour and Design of Fibre Reinforced Soil Bricks. Aberdeen, Écosse; 2020.
  29. Salih MM, Osofero AI, Imbabi MS. Critical review of recent development in fiber reinforced adobe bricks for sustainable construction. Frontiers of Structural and Civil Engineering. 2020 Aug;14(4):839-54.
  30. Jannat N, Hussien A, Abdullah B, Cotgrave A. A comparative simulation study of the thermal performances of the building envelope wall materials in the tropics. Sustainability. 2020 Jan;12(12):4892.
  31. Malbila E, Delvoie S, Toguyen D, Courard L, Attia S. Improving the Building Energy Efficiency and Thermal Comfort through the Design of Walls in Compressed Earth Blocks of Agricultural and Biopolymer Residues Masonry. Current Journal of Applied Science and Technology. 2022 Jan 1;40(45).
  32. Munaretto F. Étude de l'influence de l'inertie thermique sur les performances énergétiques des bâtiments (Doctoral dissertation, Paris, ENMP).
  33. Polster B, Peuportier B, Sommereux IB, Pedregal PD, Gobin C, Durand E. Evaluation of the environmental quality of buildings towards a more environmentally conscious design. Solar Energy. 1996 Sep 1;57(3):219-30.
  34. B. Favre. Étude de stratégies de gestion énergétique des bâtiments par l'application de la programmation dynamique. Paris; 2013.

35. Coulibaly Y, Thiombiano G, Traore MY. Climat et Confort Thermique. Sud Sciences et Technologies. 1998;2:22-27.
36. Ouedraogo E, Coulibaly O, Ouedraogo A. Elaboration d'une année météorologique type de la ville de Ouagadougou pour l'étude des performances énergétiques des bâtiments. Journal of Renewable Energies. 2012 Mar 31;15(1):77-90.
37. Compaore A, Ouedraogo B, Guengane H, Malbila E, Bathiebo DJ. Role of local building materials on the energy behaviour of habitats in Ouagadougou. International Journal of Applied Science. 2017;8:63-72.
38. Tchouateu R. Etude et Developpement d'un éco habitat sahélien à haute efficacité énergétique; 2013.
39. UEMOA. Projet de code régional d'efficacité énergétique dans les bâtiments neufs de l'UEMOA; 2014.
40. Intergovernmental Panel on Climate Change. 2011 Working group III: mitigation of climate change, vol. 2011. Geneva, Switzerland: Intergovernmental Panel on Climate Change; 2011.
41. Gutowski TG, Sahni S, Allwood JM, Ashby MF, Worrell E. The energy required to produce materials: constraints on energy-intensity improvements, parameters of demand. Philosophical Transactions of the Royal Society A: Mathematical, Physical and Engineering Sciences. 2013 Mar 13;371(1986):20120003.
42. Ibrahim M. Improving the buildings envelopes energy performance using aerogel-based insulating mineral rendering (Doctoral dissertation, Ecole Nationale Supérieure des Mines de Paris).
43. Etienne Malbila ALJK, David YK, Toguyeni. Saïdou Bamogo. Thermophysical and Mechanical Characterization of Local Stabilized Materials Suitable for Buildings in Dry and Hot Climate. Journal of Materials Science & Surface Engineering. 2018;6(2):767-772.

---

© Copyright (2022): Author(s). The licensee is the publisher (Book Publisher International).

**DISCLAIMER**

This chapter is an extended version of the article published by the same author(s) in the following journal. Current Journal of Applied Science and Technology, 40(45): 7-22, 2021.

**Reviewers' Information**

- (1) Nazli H, Tehran University of Art, Iran.
- (2) Siti Hafsa Zulkarnain, University Teknologi MARA, Malaysia.