

Bond breaking of furan-maleimide adducts via a diradical sequential mechanism under an external mechanical force

Manuel Cardosa-Gutierrez,¹ Guillaume De Bo,² Anne-Sophie Duwez,¹ *Francoise Remacle¹

¹ UR Molecular Systems, Department of Chemistry, University of Liège, 4000 Liège, Belgium

² Department of Chemistry, University of Manchester, Manchester M13 9PL, UK

Abstract

Substituted furan-maleimide Diels-Alder adducts are bound by dynamical covalent bonds that make them particularly attractive mechanophores. Thermally activated [4+2] retro Diels-Alder (DA) reactions predominantly proceed via a concerted mechanism on the ground electronic state. We show that an asymmetric mechanical force along the anchoring bonds in both the *endo* and *exo* isomers of proximal dimethyl furan-maleimide adducts favors a sequential pathway. The switching from a concerted to a sequential mechanism occurs at external forces of ≈ 1 nN. The first bond rupture occurs for a projection of the pulling force on the scissile bond at ≈ 4.3 nN for the *exo* adduct and ≈ 3.8 nN for the *endo* one. The reaction is inhibited for external forces up to ≈ 3.4 nN for the *endo* adduct and 3.6 nN the *exo* one after which it is activated. In the activated region, at 4 nN, the rupture rate of the first bond for the *endo* adduct is computed to be ≈ 3 orders of magnitude larger than for *exo* one in qualitative agreement with recent sonication experiments [Z. Wang, S. L. Craig, *Chemical Communications* **2019**, 55, 12263-12266.] In the intermediate region of the path between the rupture of the first and the second bond, the lowest singlet state exhibits a diradical character for both adducts and is close in energy to a diradical triplet state. The computed values of spin-orbit coupling along the path are too small for inducing intersystem crossings. These findings open the way for the rational design of DA mechanophores for polymer science and photochemistry.

Corresponding author: fremacle@uliege.be

Introduction

Dynamic covalent bonds, like the archetypal furan–maleimide Diels–Alder (DA) adduct, are vastly used in synthetic chemistry and polymer science, and are now expanding into biology.^{1–3} Furan-maleimide adducts are characterized by dynamical covalent bonds that are more labile and slightly longer than typical carbon-carbon covalent ones. The dynamical covalent bonds of Diels-Alder (DA) adducts makes them attractive mechanophore when embedded in polymers and networks.^{4–11} The DA reactions on these adducts proceed via a low reaction barrier that leads to reversible reactions. In solution, the adducts need to be heated at high temperatures to break open.^{1, 12} The retro-DA reaction can also take place at room temperature when the adduct is sonicated, thus subjected to mechanical forces.^{5, 10, 11} There is however not yet a detailed understanding on the rupture mechanism of these adducts under tension, in particular on the concerted or sequential nature of the reaction path.¹³

Beyond stabilizing intermediates and shifting chemical equilibria, due to the vector character of the force, mechanochemical reactions can follow specific pathways yielding products that may differ from those of non-directional thermal activation in solution.^{4, 13–19} It was shown that the *cis* or *trans* anchoring of benzocyclobutene to a polymer chain controls the stereochemistry of the ring opening.^{20, 21} Under tension, the *cis* attachment leads to a disrotatory ring opening in violation of the Woodward-Hoffmann rules²² and yields the same product as the *trans* attachment. *Ab initio* steered molecular dynamics simulations on cyclobutene and the determination of the minimum energy pathway provided a mechanistic interpretation on the force modified potential energy surface.¹⁴ In *cis* and *trans* *gem*-difluorocyclopropane (gDFC), it was shown that under tension, the *trans* gDFC undergoes a Woodward-Hoffmann thermally forbidden conrotatory ring opening, and that both *cis* and *trans* gDFC open via a diradical intermediate that is stabilized under tension.²³ Upon releasing the tension, the diradical returns to the *cis* gDFC for which the barrier is smaller on the field free potential. The diradical character of the intermediate under tension was demonstrated by trapping it with a radical chromophore. Cyclobutane cores embedded in mechanophores were reported to open sequentially^{24–27} and shown to proceed via a diradical intermediate, the product stereochemistry being determined by whether or not the intermediate undergoes isomerization after the first bond rupture.^{28, 29} Diradical intermediates were also recently reported to play a role in the mechanochemical reactivity of vinyl-addition polynorbornene that contains norbornane units,³⁰ and in the release of CO by sonication activation of Norborn 2-en-7-one scaffold.³¹

Various [4+2] mechanophores have been investigated,¹⁹ among them furan-maleimide is a popular motive.^{5, 6, 9-11, 32-38} Furan-maleimide adducts embedded in a polymethyl acrylate (PMA) polymer were shown to selectively break under sonication.⁵ Stevenson and De Bo¹⁰ pointed to a regioselectivity of the rupture of furan-maleimide mechanophore embedded in PMA activated by sonication; the two proximal stereoisomers, where the anchoring of the polymer chain on the furan is on a carbon atom near neighbor to the furan/maleimide junction, being more labile than the distal ones where the anchoring is on the next near neighbor atom on the furan moiety. Wang et al¹¹ benchmarked the mechanical resistance to activation by sonication of the two proximal stereoisomers with respect to the ring opening of the *gem*-dichlorocyclopropane. They concluded that the *proximal-exo* adduct is mechanically less labile than the *proximal-endo* one. This stereoselectivity in the rupture under force follows the trend of thermal activation. It is corroborated by the differences in the computed force-free activation barriers and in the efficiency of the mechanochemical coupling to the polymer chain.

Motivated by these results^{10, 11} we theoretically investigated the mechanism of the [4+2] retro Diels-Alder (rDA) ring opening of the *proximal-endo*, P_{endo} , and *proximal-exo*, P_{exo} , dimethyl furan-maleimide adducts under tension. We report on a shift from a concerted mechanism at zero force to a sequential one at external pulling forces on the weakest scissile bond smaller than 1 nN due to the directionality of the force applied to the methyl groups used to model the tethering of the adduct into a polymer. We further show that the tension inhibits the bond rupture up to pulling forces of ≈ 3 nN before inducing a preferential activation of the P_{endo} stereoisomer in qualitative agreement with the experimental results of Wang et al.¹¹

On the ground electronic state at room temperature, thermally activated [4+2] retro Diels-Alder (rDA) reactions proceed most of the time via a concerted and stereospecific pathway involving a single concerted transition state at room temperature.^{39, 40} Activation energies of 25-30 kcal·mol⁻¹ for the concerted rupture of the two scissile bonds at room temperature confer them a dynamic character. *Endo* adducts are more reactive than *exo* ones because of their lower activation barriers.⁴¹⁻⁴³ A sequential mechanism involving diradicals or zwitterion species is also thermally possible, depending of the substitution of DA adducts.⁴⁴ Studies involving molecular dynamics showed that for some adducts at high temperature (>1000 K) and for substituted ones a small fraction of the trajectories involves two transition states (TS) and diradicals open shell singlet intermediates along the reaction path.⁴⁰ Photoactivation of DA adducts by UV pulse was shown to proceed via non concerted pathways through successive

bond cleavages, depending on the nature of the Conical Intersections (CoIn) leading back to the ground electronic state.⁴⁵⁻⁴⁸ Studies investigating activation by an external static electrical field also reported going through a sequential pathway involving zwitterionic intermediates.^{41,}

49

We show here that diradical intermediates can be stabilized under tension in the rDA of the substituted P_{endo} and P_{exo} furan-maleimide adducts where the methyl groups model the anchoring on the polymer chain and control the directionality of the external force. The two adducts and the four bonds of interest, the two scissile bonds, SB1 and SB2, and the CN and the CC anchoring bonds of the methyl groups are drawn in Figure 1. Because of the difference in the stereo character of P_{endo} and P_{exo} , at the force free equilibrium geometry, SB1 and SB2 are essentially of equal length in P_{endo} (1.57 Å) while in P_{exo} , SB1 is longer (1.58Å) than SB2 (1.56 Å).

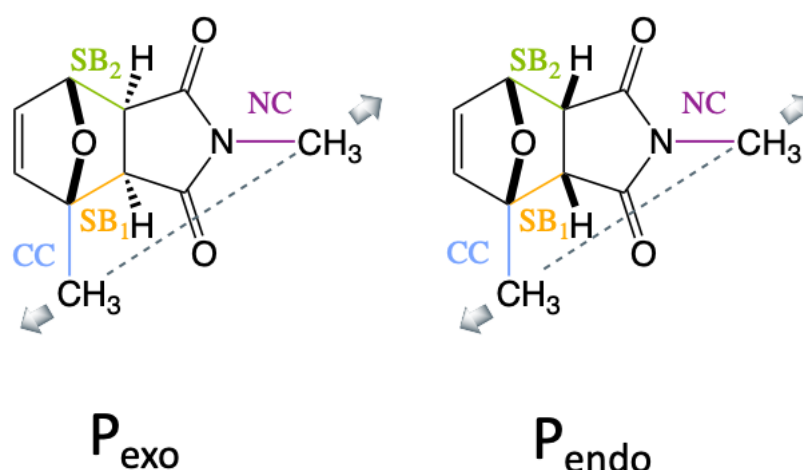


Figure 1. Stereochemistry of the P_{endo} and P_{exo} adducts, the labeling of the two scissile bonds, SB1 (orange) and SB2 (green) and of the two anchoring bonds, CC (blue) and NC (violet) and the direction of the stretching coordinate in dashes. The pulling coordinate has a larger projection on SB1 than on SB2.

Computational methods

The effect of the external force on the potential energy surface (PES) can be computed by an isometric or an isotensional approach.⁵⁰ The isometric method CoGEF (constrained geometries simulate external force)⁵¹ consists in a constrained geometry optimization where typically the constraint is the distance between the two atoms to which the pulling force is applied. This approach yields the most stable geometry of the system that satisfies a given value of the

constraint, and provides the energy and other molecular properties through electronic structure computations. In the isotensional method, the external force is explicitly added as a term in the expression of the nuclear gradient of the energy during the geometry optimization. Three approaches have been implemented, the force-modified-potential-energy surface (FMPES),¹⁴ the external force is explicitly included (EFEI)¹⁵ and the enforce geometry optimization (EGO).⁵² The isotensional approaches can be used to determine the reactant, transition state and activation energies on the FMPES and to carry out *ab initio* molecular dynamics under force.¹⁴ It was shown in ref. ⁵³ that at stationarity, the EFEI potential, $V_{EFEI}(\mathbf{F}_0)$, is the Legendre transform of the CoGEF potential $V_{CoGEF}(\mathbf{q}_0)$, so that the external force and the geometrical constraint can be considered conjugate variables: $V_{EFEI}(F_0) \equiv V_{CoGEF}(q_0) - F_0 q_0$.

The reaction mechanism was studied by the CoGEF isometric protocol, for the two adducts at the UDFT level with the wB97XD⁵⁴ functional and at the CAS-SCF (4,4) level with the 6-31G(d,p) basis set for the lowest singlet, S_0 , and triplet, T_0 , states. The mechanical coordinate is taken to be the distance between the two C atoms of the methyl anchoring groups (dashed line in Figure 1). For each relaxed geometry under force, the spin-orbit coupling between S_0 and T_0 was computed along the CoGEF path as well as the 4 lowest singlet and three lowest triplet states at the state average (SA) complete active space⁵⁵ CAS-SCF level. The CoGEF path computed at the CAS (4,4) level /6-31G(d,p) is consistent with that obtained at the UDFT level, see ESI for more details. The UDFT computations were carried out with the quantum chemistry software QChem⁵⁶ and the CAS-SCF computation with the MOLPRO quantum chemistry package.^{57, 58}

The TS were determined at the UDFT/wB97XD level scanning external pulling force values corresponding to the stretching coordinate.⁵⁹ Consistent force modified CoGEF paths and activation barriers were obtained with the PBE0DH⁶⁰ and the BH&HLYP⁶¹ functionals, Figure S2. These three functionals describe correctly the diradical species that appear when the pulling force induces the switch from a concerted to a sequential rupture mechanism, and give results consistent with the CAS-SCF level.

The computed values of the barrier for the rupture of the weakest bond SB1 using the UDFT/wB97XD/6-31G(d,p) in the gas phase at zero force are in good agreement with previously reported values in gas phase^{41, 42} or the M06-2X⁴⁹ functional in DMSO for unsubstituted adducts. They are systematically higher by ≈ 5 -6 kcal/mol than those reported values for similar furan-maleimide adducts using the B3LYP¹¹ functional in THF. A detailed comparison with previous results at zero force and computed values of the barriers using different functionals is provided in the Electronic Supplementary Information (ESI).

Since the value of the stretching coordinate at equilibrium at zero force, $R_{\text{pulling-0}}$, is different in the two stereoisomers, we report below the variation of the structural and energetic observables as a function of the pulling distortion, defined as $(R_{\text{pulling}} - R_{\text{pulling-0}})$ where R_{pulling} is the stretching distortion imposed in the CoGEF protocol.

Results and discussion

Switching from a concerted to a sequential mechanism under tension

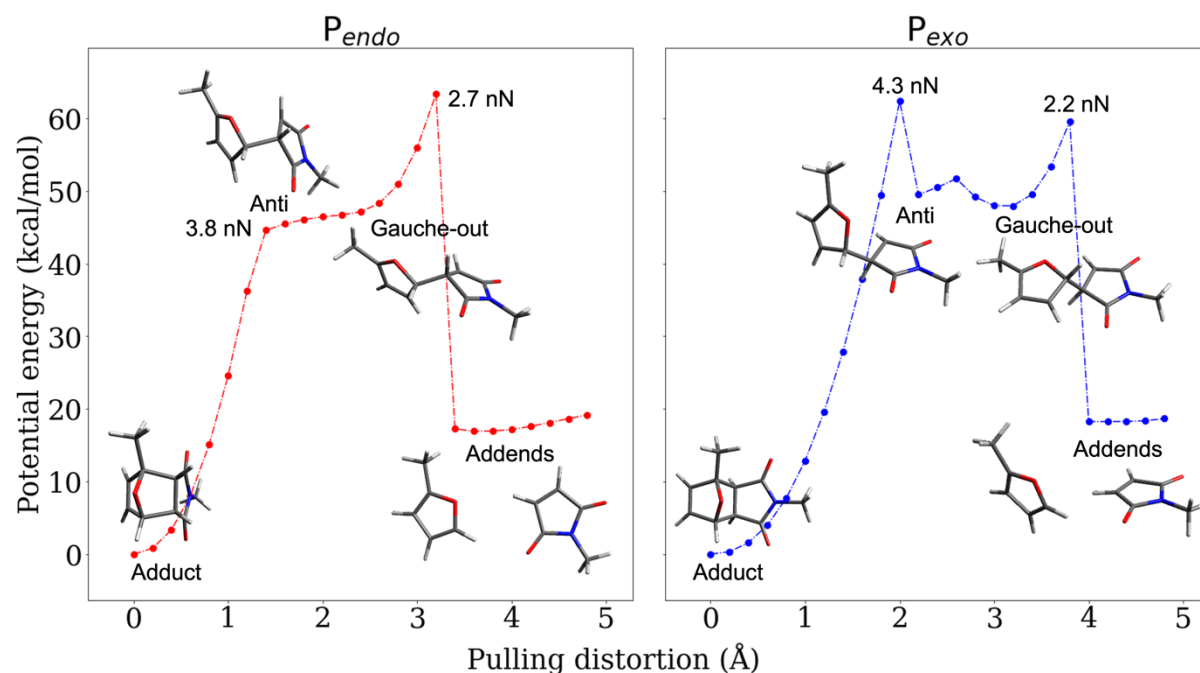


Figure 2. CoGEF UDFT wB97XD potential energy profiles for the P_{endo} (a) and P_{exo} (b) adducts as a function of the pulling distortion ($R_{\text{pulling}} - R_{\text{pulling-0}}$) as well as relaxed geometries under force for maxima and minima. The CoGEF path computed at the CAS(4,4) level is given in Figure S1 and the one computed with the PBE0DH and BH&HLYP functionals in figure S2. The relaxed geometries along the CoGEF paths computed at the DFT wB97XD and CAS(4,4) levels are given in the ESI.

The CoGEF UDFT/wB97XD potential energy profiles are reported as a function of the pulling distortion, $(R_{\text{pulling}} - R_{\text{pulling-0}})$, in Figures 2a and b for P_{endo} and P_{exo} respectively. Similar profiles are obtained at the CAS(4,4) level, see Figure S1. Both adducts undergo a sequential bond rupture. The energy curves exhibit two sharp rises separated by an intermediate region. The breaking of SB1 occurs at the end of the first sharp energy rise, while that of SB2 occurs at the end of the second one. This can be seen from the relaxed geometries under force reported as

insets in Figures 2a and b, and from the elongation of the bond lengths as a function of the pulling distortion plotted in Figure 3a. During the first energy rise, SB1 is elongated while SB2 remains essentially at its equilibrium value (Figure 3a). In this range, the projection of the pulling force on SB2 (Figure 3b) is smaller than on SB1 and not large enough for inducing bond breaking. The SB1 bond of P_{endo} ruptures for a projection of the pulling force of 3.8 nN, that is slightly smaller than the breaking projection of pulling force for P_{exo} (4.3 nN). These values are in good agreement with those reported in ref. ¹⁰. After the SB1 breaking, the projection of the pulling force (Figure 3b) on the two scissile bonds drops sharply to values close to zero. In the intermediate region between the two bond breakings, the energy profile of P_{endo} (Figure 2a) continues to rise with a much smaller slope, starting from an *anti-like* unstable endo rotamer that evolves to an unstable endo *gauche out* one just before the breaking of SB2. On the other hand, in P_{exo} the *anti* and *gauche out* rotamers correspond to minima (see Figure 2b), separated by a small rotation barrier of 3 kcal·mol⁻¹ which is overcome by a small value of the force of 0.2 nN as can be seen from Figure 3b. These intermediates have been reported previously for similar DA adducts for zero force reaction paths.^{40, 44, 48} Such a rotation around the unbroken bond has also been reported for the sequential ring opening of cyclobutane cores under tension.^{24-27, 29} The breaking of SB2 occurs after a second sharp rise in the projection of the pulling force for a smaller value for P_{exo} (2.2 nN) than for P_{endo} (2.7 nN), Figure 3b. Then the potential energy drops sharply to the dissociation asymptote.

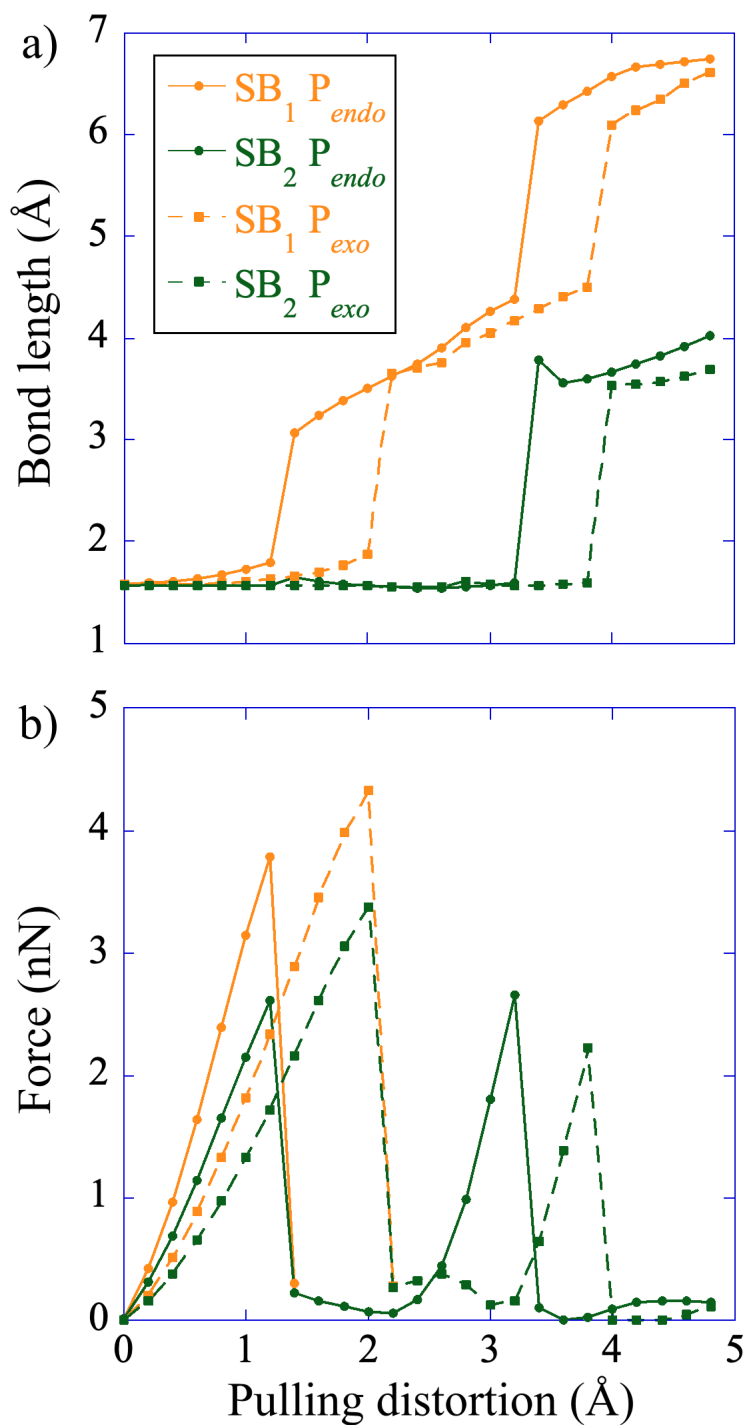


Figure 3. a) SB1 (orange) and SB2 (green) elongation plotted as a function of the pulling distortion for P_{endo} (full lines) and P_{exo} (dashes). b) Projection of the pulling force on SB1 and SB2 for the two adducts. The bond rupture and the maximum in the projection of the pulling force on the scissile bonds do not occur at the same value for P_{endo} and P_{exo} because of the difference in geometries of the two stereoisomers.

The results discussed above imply that there is a switching of the rupture mechanism from a concerted one to a sequential one at low values of the pulling force, before the rupture of the first scissile bond. In order to get further insights, we computed the transition state (TS) and the free energy of the activation barrier, ΔG_F^\ddagger , at 298 K, using the EFEI¹⁵ isotensional protocol at the same UDFT level from zero force up to values of the pulling force on SB1 approaching that of the rupture in the UDFT CoGEF path shown in Figure 3b. It is plotted in Figure 4.

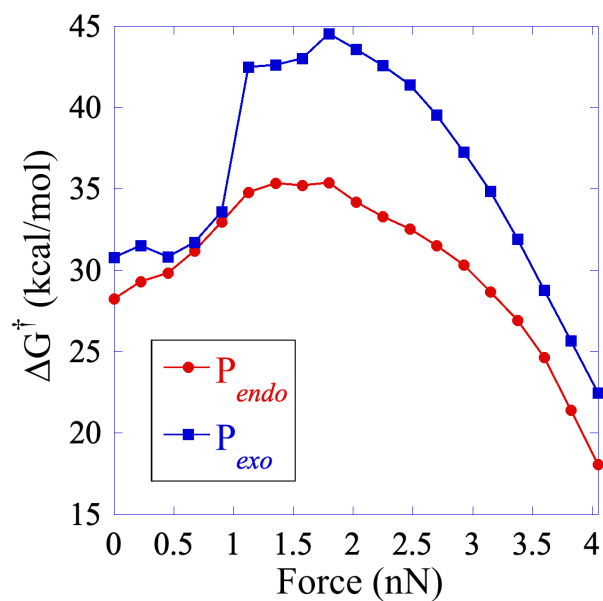


Figure 4. Free energy activation barrier computed using the EFEI protocol for values of the pulling force up to the rupture of the SB1 bond. P_{endo} is plotted in red with full circles and P_{exo} in blue with diamonds. The geometries of the reactant and the transition states are given in the SI.

At zero force, at 298 K, the free energy barrier is smaller for the P_{endo} adduct (28.2 kcal·mol⁻¹) than for the P_{exo} (30.8 kcal·mol⁻¹) which leads to a computed $\Delta(\Delta G^\ddagger)$ between P_{exo} and P_{endo} of 2.6 kcal/mol. For both adducts, as the pulling force increases, the activation barrier first increases, which means that rupture is inhibited, then is going through a plateau, before sharply decreasing up to the rupture of the SB1 bond, see figure 4. The maximum of the activation barrier occurs for both P_{endo} and P_{exo} at 1.8 nN. The barrier is higher for P_{exo} (44.5 kcal·mol⁻¹) than for P_{endo} (35.4 kcal·mol⁻¹). At pulling forces larger than 3.4 nN, the rupture of SB1 is activated in P_{endo} compared to the zero-force barrier. For P_{exo} , activation occurs for a pulling force larger than 3.8 nN (Figure 4). Above 3.5 nN, the computed $\Delta(\Delta G^\ddagger)$, decays sharply, but remains higher for P_{exo} , which makes P_{endo} adduct more labile, in agreement with the experimental results of Wang et al.¹¹ At 4 nN, just before rupture of SB1, the computed barrier

is 18 kcal/mol for P_{endo} (rate constant of 0.36 s^{-1} (lifetime of 2.8 s)) while it is 22.5 kcal/mol (rate constant of $2.1 \cdot 10^{-4}\text{ s}^{-1}$ (lifetime of 77 min)) for P_{exo} , see Figure S3 and the ESI for more details. The crossover from a concerted mechanism to a sequential one occurs before the first bond rupture at pulling forces $\approx 1\text{ nN}$ (1.1 nN for P_{exo} and 0.9 nN for P_{endo}). It coincides with the inflexion point of the pulling force on SB1. Above 1nN, the sequential mechanism is favored over the concerted one and it dominates for forces above 3nN.

Diradical species in the sequential mechanism

The electronic structure of S_0 is very similar for both adducts along the CAS (4,4) CoGEF path. The main configurations correspond to a diradicalar open shell singlet in the intermediate region between the two bond ruptures, see ESI for details and Figure S4 that shows the coefficients of the S_0 state on the electronic configurations as a function of the pulling distortion.

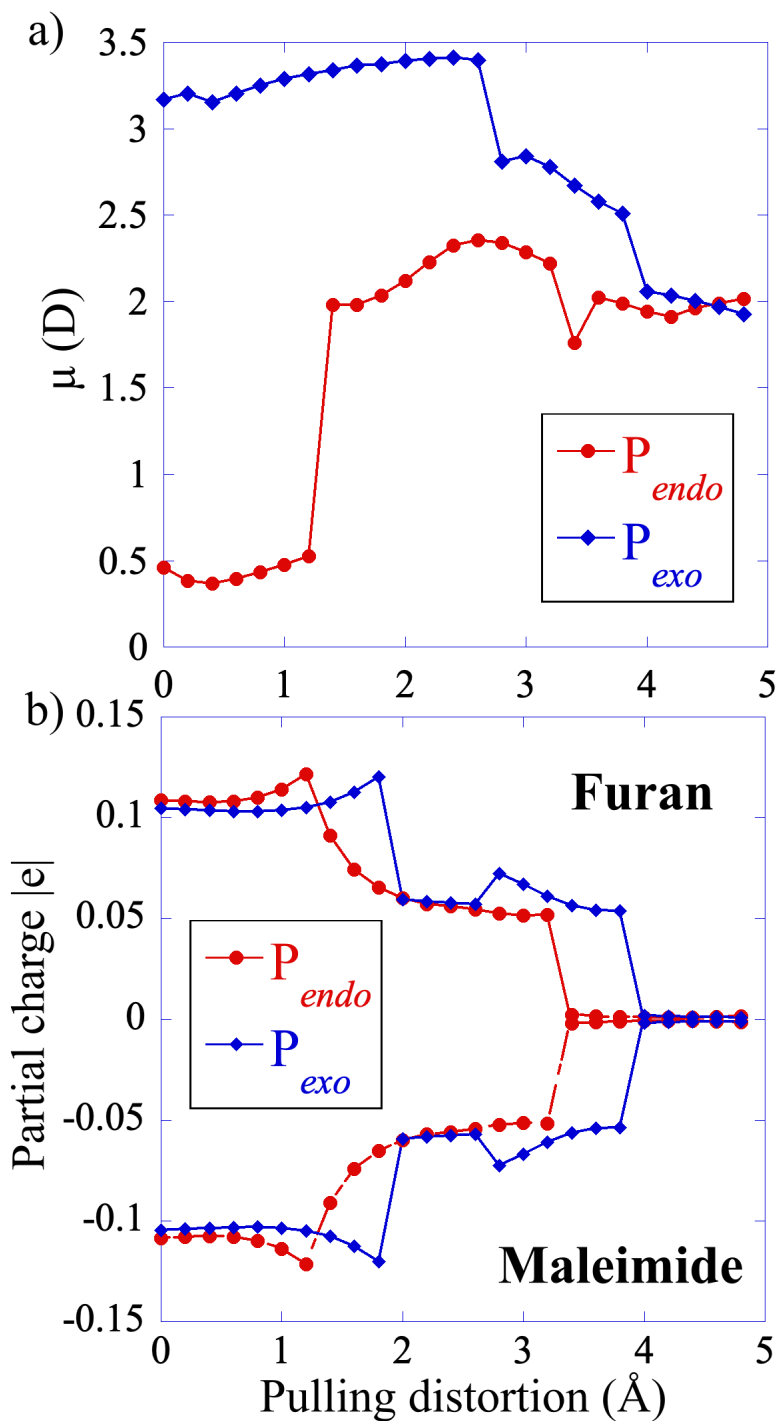


Figure 5. a) Permanent dipole of the two adducts along the CAS(4,4) CoGEF path for P_{endo} (red-filled circles) and P_{exo} (blue-diamonds). b) Computed partial charge on the furan and maleimide addends along the CAS CoGEF path.

At zero force, the value of the permanent dipole moment of the P_{endo} is very small (0.5 D). It increases to 2.5 D in the intermediate region, after the first bond rupture, because the pulling distortion increases the extension of the P_{endo} adduct and makes it comparable to that of the

P_{exo} , Figure 5. The geometry of the P_{exo} is more extended geometry at zero force because of its stereo character and the dipole moment is larger, 3 D, than that of the P_{endo} adduct. It slightly decreases in the intermediate region to 2 D. The partial positive and negative charges on the two addends are small at zero force ((furan (donor), +0.1 |e| and maleimide (acceptor), -0.1 |e|) and decrease in the intermediate region along the CoGEF path confirming the diradical character of S_0 in the intermediate region.

For both adducts, the lowest triplet state, T_0 , becomes close in energy with S_0 in the intermediate region with energy differences of the order of 0.05 eV (Figure 6). The weight of the $|2aa0\rangle$ configuration in the intermediate region is 93% (Figure S6). In the case of P_{endo} , the triplet state energy becomes lower than that of S_0 at the beginning of the intermediate region, for distortion in the range of 1.8 to 2.4 Å (see Figure S7 for a plot of the S_0/T_0 energy difference). The spin-orbit coupling remains extremely small, of the order of 10^{-5} eV for both adducts throughout the intermediate region (see Table S1), which makes intersystem crossing unlikely along the minimum energy path under force. However, the S_0/T_0 minimum energy crossing occurs in the vicinity of second bond rupture for both adducts, see Figure S8. Therefore, one could observe spin-orbit transitions using steered molecular dynamics^{14, 29} which will be the subject of future work. The first excited singlet state S_1 which has also a diradical character in the intermediate region, is much higher in energy along the minimum path, with a S_0/S_1 energy difference larger than 3 eV.

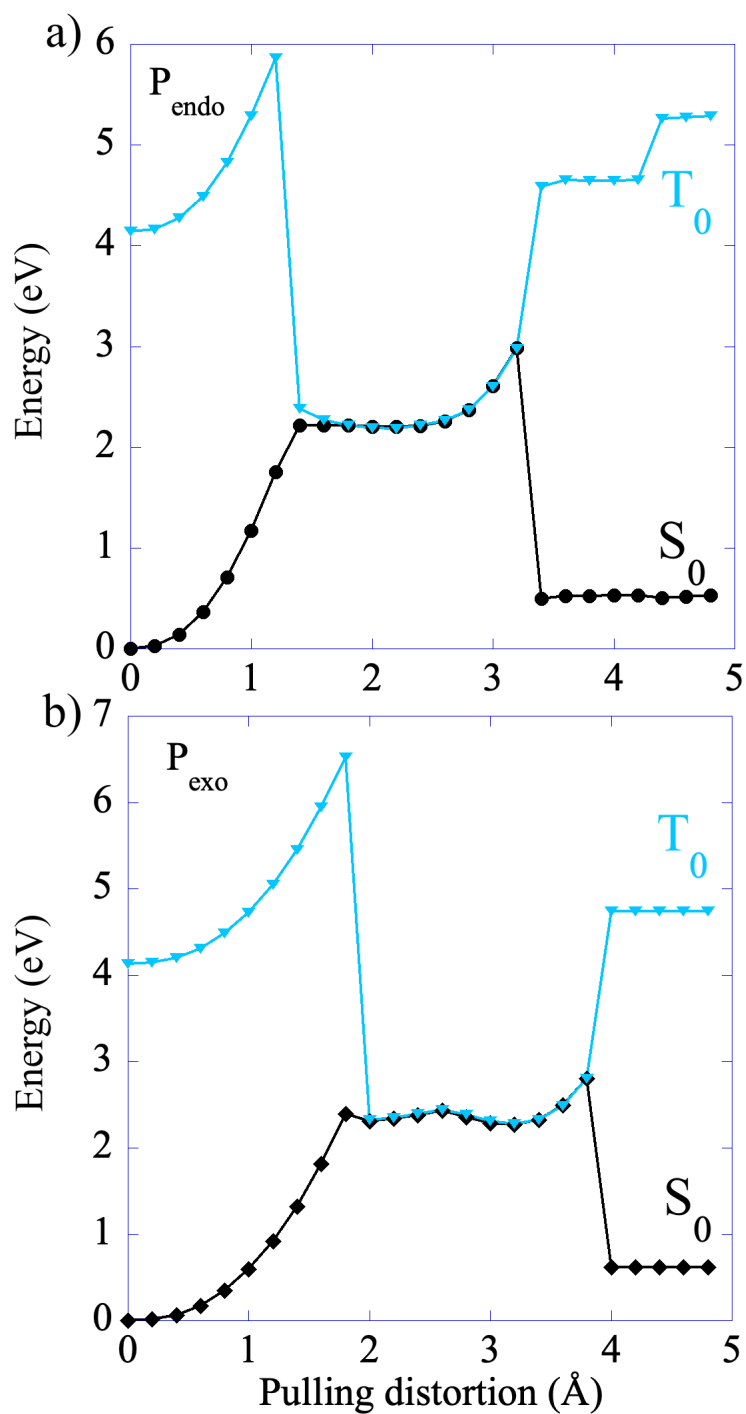


Figure 6. Energy profiles of the singlet S_0 and the lowest triplet T_0 along the CAS(4,4)-CoGEF path. The energy of the T_0 state is computed at the relaxed geometry of S_0 . The values of the spin-orbit coupling are reported in Table S1 of the ESI. The S_0/T_0 energy differences are plotted in Figure S6 and the minimum energy intersystem crossing (MEIC) geometries in Figure S7. Files of geometries of the S_0 state along the CoGEF path as well as at the MEIC are given in the ESI.

Conclusions

Our computations uncover a rich and complex electronic and structural reorganization of the P_{endo} and P_{exo} adducts along the stretching mechanical path. The directionality of the force as dictated by the carbon atoms of the two methyl substituents that model the anchoring into the polymer leads to an uneven activation of the two scissile bonds. This in turn induces a switch from a concerted mechanism at zero pulling force to a sequential one for force larger than 1 nN along the minimum energy path. As the external force increases, the reaction is first inhibited and then activated. Pulling forces on the most activated scissile bond larger than 3.4 nN (P_{endo}) and 3.6 nN (P_{exo}) lead to a faster rupture rate constant than at zero force. The values of the pulling force leading to the switch of mechanism and to the bond rupture for the reactant state of P_{endo} and P_{exo} are very close. However, the response P_{endo} occurs systematically at slightly lower forces than those computed for P_{exo} . The free energy activation barrier of P_{endo} for the first bond breaking is systematically lower by 7 to 3 kcal·mol⁻¹ as the external force increases which explains the more labile character of P_{endo} under tension observed experimentally.¹¹

In the intermediate region between the two sequential bond ruptures, the singlet ground state has a diradical character and adopts an extended geometry for both adducts. In this region, the triplet state becomes very close in energy to S_0 but the spin-orbit coupling remains too small to induce an intercrossing transition along the minimum energy path. However, the minimum energy crossing between T_0 and S_0 occurs in the vicinity of the second bond rupture along the P_{exo} adduct minimum energy path.

Diradical intermediates resulting from an activation by an external mechanical force have been identified experimentally in the case of ring opening of cyclopropanes²³ and in the sequential opening of [2+2] cyclobutane mechanophores.^{24, 25, 29, 62-64} Our results suggest that diradical intermediates are also formed in the mechanically activated sequential cycloreversion of [4+2] furan-maleimide DA adducts due to the directionality of the pulling force. The effect of the mechanical force is to modify the level structure of the various singlet and triplet states in the intermediate region, inducing several conical intersections within the singlet and triplet manifolds, as well as intersystem singlet-triplet crossings for geometries close to those of the minimum energy path. In particular, the mechanical force stabilizes the diradical intermediates on the lowest singlet and triplet states and does not induce the formation of a zwitterion, as has been reported in the case of an activation by a static electric field^{41, 49} or for substituted addends,⁴⁴ which leads to a larger charge separation. After the first bond rupture, in the case of the P_{exo} adduct, small forces of less than 1 nN along the minimum path induce an isomerization

of the diradical intermediate from an *anti* to a *gauche out* stereoisomer, which are separated by a small rotational barrier of 3 kcal/mol. Such internal rotations have been reported for DA adducts undergoing a sequential cycloreversion at zero force^{40, 44, 48}, and also observed the opening of cyclobutane under mechanical force.^{24, 25, 29, 62-64}

The presence of several crossings between electronic states in the vicinity of the minimum energy path as well as the fact that the rotational barriers between stereoisomers of the diradical intermediate can be overcome by small external forces could lead to different adducts upon ring closure when the force is relaxed.⁴⁴ The switching to a sequential mechanism under force and the predicted production of intermediate diradicals could be potentially observed experimentally with the help of a radical trap,²³ and the eventual formation of alternative adducts confirmed by spectroscopy.

Single-molecule force spectroscopy (SMFS) has contributed to further developments in mechanochemistry^{4, 65} by enabling the mechanical activation of covalent bonds,⁶⁶⁻⁶⁸ with applications in irreversible bond scission,^{17, 69-77} and opening of mechanophores.^{17, 26, 78-83} Our results offer new perspectives for investigating DA mechanophores by SMFS, in particular the force-clamp characterization of a reversible partial opening by breaking the weakest bond of the adduct only and the investigation of the effect of a photoexcitation of the mechanophore by UV light under force. A recent study indeed reports the involvement of fluorescent radical species in the SMFS spectroscopy of a tetraaryl succinonitrile mechanophore.⁸⁴ In a broader perspective, our results are also relevant for the photochemistry of DA adducts.^{46, 47} They provide insights on the regions of the potential energy surfaces involved in a sequential bond rupture as well as on the relevant conical intersections and spin-orbit intersystem crossings between excited states along the sequential reaction path that could be probed using the ultrashort few femtosecond optical pulses that became recently available.⁸⁵

Electronic Supplementary Information

The Electronic Supplementary Information provides a detailed description of computational methods and results for the thermodynamics and kinetics analysis and of the electronic structure methodology. Zip files provide the geometries of both adducts along the CoGEF path computed at the DFT and CAS(4,4) levels, the geometries of the reactant and transition states computed at the DFT level and the geometries at minimum energy intersystem crossing computed at the CAS(4,4) level.

Data availability statement: Data for this paper, including optimized geometries for COGEF path and EFEI and minimum energy intersystem crossings are available at ZENODO at <https://doi.org/10.5281/zenodo.7473211>.

Author contributions

M.C.-G. carried out the computations. All authors designed the research, analyzed the results and wrote the ms.

Acknowledgments

The work of M.C.-G., A.S.D. and F.R. is supported by the action of concerted research MECHANOCHEM (ARC 19/23-20, ULiege). Computational resources have been provided by the Consortium des Equipements de Calcul Intensif (CECI), funded by the F.R.S.-FNRS under Grant # 2.5020.11. G.D.B. is a Royal Society University Research Fellow.

Conflict of interest

The authors declare no conflict of interest.

References

- (1). S. Kotha and S. Banerjee, *RSC Adv.*, 2013, **3**, 7642-7666.
- (2). Z. P. Zhang, M. Z. Rong and M. Q. Zhang, *Prog. Poly. Sci.*, 2018, **80**, 39-93.
- (3). P. Chakma and D. Konkolewicz, *Angewandte Chemie International Edition*, 2019, **58**, 9682-9695.
- (4). R. Boulatov, ed., *Polymer Mechanochemistry*, Springer, Cham, 2015.
- (5). H.-Y. Duan, Y.-X. Wang, L.-J. Wang, Y.-Q. Min, X.-H. Zhang and B.-Y. Du, *Macromolecules*, 2017, **50**, 1353-1361.
- (6). B. Lyu, W. Cha, T. Mao, Y. Wu, H. Qian, Y. Zhou, X. Chen, S. Zhang, L. Liu, G. Yang, Z. Lu, Q. Zhu and H. Ma, *ACS Appl. Mater. Interfaces*, 2015, **7**, 6254-6259.
- (7). X. Hu, M. E. McFadden, R. W. Barber and M. J. Robb, *J Am Chem Soc*, 2018, **140**, 14073-14077.
- (8). J. Kida, K. Imato, R. Goseki, D. Aoki, M. Morimoto and H. Otsuka, *Nat Commun*, 2018, **9**, 3504.
- (9). Y. Min, S. Huang, Y. Wang, Z. Zhang, B. Du, X. Zhang and Z. Fan, *Macromolecules*, 2015, **48**, 316-322.
- (10). R. Stevenson and G. De Bo, *J. Am. Chem. Soc.*, 2017, **139**, 16768-16771.
- (11). Z. Wang and S. L. Craig, *Chem. Comm.*, 2019, **55**, 12263-12266.
- (12). A. Gandini, *Prog. Poly. Sci.*, 2013, **38**, 1-29.
- (13). S. Akbulatov and R. Boulatov, *ChemPhysChem*, 2017, **18**, 1422-1450.
- (14). M. T. Ong, J. Leiding, H. Tao, A. M. Virshup and T. J. Martínez, *J. Am. Chem. Soc.*, 2009, **131**, 6377-6379.
- (15). J. Ribas-Arino, M. Shiga and D. Marx, *Angew. Chem.*, 2009, **48**, 4190-4193.
- (16). D. A. Davis, A. Hamilton, J. Yang, L. D. Cremer, D. Van Gough, S. L. Potisek, M. T. Ong, P. V. Braun, T. J. Martínez, S. R. White, J. S. Moore and N. R. Sottos, *Nature*, 2009, **459**, 68-72.
- (17). J. Wang, T. B. Kouznetsova, Z. Niu, M. T. Ong, H. M. Klukovich, A. L. Rheingold, T. J. Martinez and S. L. Craig, *Nat. Chem.*, 2015, **7**, 323-327.
- (18). R. Nixon and G. De Bo, *Nat. Chem.*, 2020, **12**, 826-831.
- (19). E. Izak-Nau, D. Campagna, C. Baumann and R. Göstl, *Polymer Chemistry*, 2020, **11**, 2274-2299.
- (20). C. R. Hickenboth, J. S. Moore, S. R. White, N. R. Sottos, J. Baudry and S. R. Wilson, *Nature*, 2007, **446**, 423-427.
- (21). C. L. Brown, B. H. Bowser, J. Meisner, T. B. Kouznetsova, S. Seritan, T. J. Martinez and S. L. Craig, *J. Am. Chem. Soc.*, 2021, **143**, 3846-3855.

- (22). R. B. Woodward and R. Hoffmann, *Angew. Chem.*, 1969.
- (23). J. M. Lenhardt, M. T. Ong, R. Choe, C. R. Evenhuis, T. J. Martinez and S. L. Craig, *Science*, 2010, **329**, 1057.
- (24). M. J. Kryger, M. T. Ong, S. A. Odom, N. R. Sottos, S. R. White, T. J. Martinez and J. S. Moore, *J. Am. Chem. Soc.*, 2010, **132**, 4558-4559.
- (25). Z. S. Kean, Z. Niu, G. B. Hewage, A. L. Rheingold and S. L. Craig, *J. Am. Chem. Soc.*, 2013, **135**, 13598-13604.
- (26). Z. Chen, J. A. M. Mercer, X. Zhu, J. A. H. Romaniuk, R. Pfattner, L. Cegelski, T. J. Martinez, N. Z. Burns and Y. Xia, *Science*, 2017, **357**, 475-479.
- (27). M. Horst, J. Yang, J. Meisner, T. B. Kouznetsova, T. J. Martínez, S. L. Craig and Y. Xia, *J. Am. Chem. Soc.*, 2021, **143**, 12328-12334.
- (28). Z. Chen, X. Zhu, J. Yang, J. A. M. Mercer, N. Z. Burns, T. J. Martinez and Y. Xia, *Nat. Chem.*, 2020, **12**, 302-309.
- (29). Y. Liu, S. Holm, J. Meisner, Y. Jia, Q. Wu, J. Woods Toby, J. Martinez Todd and S. Moore Jeffrey, *Science*, 2021, **373**, 208-212.
- (30). D. C. Lee, V. K. Kensy, C. R. Maroon, B. K. Long and A. J. Boydston, *Angewandte Chemie*, 2019, **131**, 5695-5698.
- (31). Y. Sun, W. J. Neary, Z. P. Burke, H. Qian, L. Zhu and J. S. Moore, *J. Am. Chem. Soc.*, 2022, **144**, 1125-1129.
- (32). T. Zeng, X. Hu and M. J. Robb, *Chem. Comm.*, 2021, **57**, 11173-11176.
- (33). M. Zhang and G. De Bo, *J. Am. Chem. Soc.*, 2020, **142**, 5029-5033.
- (34). M. Zhang and G. De Bo, *J. Am. Chem. Soc.*, 2018, **140**, 12724-12727.
- (35). R. Stevenson, M. Zhang and G. De Bo, *Polymer Chemistry*, 2020, **11**, 2864-2868.
- (36). X. Hu, T. Zeng, C. C. Husic and M. J. Robb, *ACS Central Science*, 2021, **7**, 1216-1224.
- (37). X. Hu, T. Zeng, C. C. Husic and M. J. Robb, *J. Am. Chem. Soc.*, 2019, **141**, 15018-15023.
- (38). L. C. Wu and G. De Bo, *Synlett*, 2022, **33**, st-2022-r0064-c.
- (39). R. C. Cioc, M. Crockatt, J. C. van der Waal and P. C. A. Bruijninx, *Angew. Chem.*, 2022, **61**, e202114720.
- (40). K. Black, P. Liu, L. Xu, C. Doubleday and K. N. Houk, *Proc. Natl. Acad. Sci. U.S.A.*, 2012, **109**, 12860.
- (41). R. Meir, H. Chen, W. Lai and S. Shaik, *ChemPhysChem*, 2010, **11**, 301-310.
- (42). L. Rulišek, P. Šebek, Z. Havlas, R. Hrabal, P. Čapek and A. Svatoš, *J. Org. Chem.*, 2005, **70**, 6295-6302.
- (43). A. Ogawa and H. Fujimoto, *Tetrahedron Lett.*, 2002, **43**, 2055-2057.
- (44). J. Sauer and R. Sustmann, *Angew. Chem.*, 1980, **19**, 779-807.
- (45). S. De Feyter, E. W. G. Diau, A. A. Scala and A. H. Zewail, *Chem. Phys. Lett.*, 1999, **303**, 249-260.
- (46). E. W. G. Diau, S. De Feyter and A. H. Zewail, *Chem. Phys. Lett.*, 1999, **304**, 134-144.
- (47). B. A. Horn, J. L. Herek and A. H. Zewail, *J. Am. Chem. Soc.*, 1996, **118**, 8755-8756.
- (48). S. Wilsey, K. N. Houk and A. H. Zewail, *J. Am. Chem. Soc.*, 1999, **121**, 5772-5786.
- (49). C. Yang, Z. Liu, Y. Li, S. Zhou, C. Lu, Y. Guo, M. Ramirez, Q. Zhang, Y. Li, Z. Liu, K. N. Houk, D. Zhang and X. Guo, *Sci. Adv.*, 2021, **7**, eabf0689.
- (50). T. Stauch and A. Dreuw, *Chemical Reviews*, 2016, **116**, 14137-14180.
- (51). M. K. Beyer, *J. Chem. Phys.*, 2000, **112**, 7307-7312.
- (52). K. Wolinski and J. Baker, *Mol. Phys.*, 2009, **107**, 2403-2417.
- (53). J. Ribas-Arino, M. Shiga and D. Marx, *J. Am. Chem. Soc.*, 2010, **132**, 10609-10614.
- (54). J.-D. Chai and M. Head-Gordon, *Phys. Chem. Chem. Phys.*, 2008, **10**, 6615-6620.
- (55). P. J. Knowles and H.-J. Werner, *Chem. Phys. Lett.*, 1985, **115**, 259-267.
- (56). Y. Shao, Z. Gan, E. Epifanovsky, A. T. B. Gilbert, M. Wormit, J. Kussmann, A. W. Lange, A. Behn, J. Deng, X. Feng, D. Ghosh, M. Goldey, P. R. Horn, L. D. Jacobson, I. Kaliman, R.

Z. Khaliullin, T. Kuś, A. Landau, J. Liu, E. I. Proynov, Y. M. Rhee, R. M. Richard, M. A. Rohrdanz, R. P. Steele, E. J. Sundstrom, H. L. Woodcock, P. M. Zimmerman, D. Zuev, B. Albrecht, E. Alguire, B. Austin, G. J. O. Beran, Y. A. Bernard, E. Berquist, K. Brandhorst, K. B. Bravaya, S. T. Brown, D. Casanova, C.-M. Chang, Y. Chen, S. H. Chien, K. D. Closser, D. L. Crittenden, M. Diedenhofen, R. A. DiStasio, H. Do, A. D. Dutoi, R. G. Edgar, S. Fatehi, L. Fusti-Molnar, A. Ghysels, A. Golubeva-Zadorozhnaya, J. Gomes, M. W. D. Hanson-Heine, P. H. P. Harbach, A. W. Hauser, E. G. Hohenstein, Z. C. Holden, T.-C. Jagau, H. Ji, B. Kaduk, K. Khistyayev, J. Kim, J. Kim, R. A. King, P. Klunzinger, D. Kosenkov, T. Kowalczyk, C. M. Krauter, K. U. Lao, A. D. Laurent, K. V. Lawler, S. V. Levchenko, C. Y. Lin, F. Liu, E. Livshits, R. C. Lochan, A. Luenser, P. Manohar, S. F. Manzer, S.-P. Mao, N. Mardirossian, A. V. Marenich, S. A. Maurer, N. J. Mayhall, E. Neuscamman, C. M. Oana, R. Olivares-Amaya, D. P. O'Neill, J. A. Parkhill, T. M. Perrine, R. Peverati, A. Prociuk, D. R. Rehn, E. Rosta, N. J. Russ, S. M. Sharada, S. Sharma, D. W. Small, A. Sodt, T. Stein, D. Stück, Y.-C. Su, A. J. W. Thom, T. Tsuchimochi, V. Vanovschi, L. Vogt, O. Vydrov, T. Wang, M. A. Watson, J. Wenzel, A. White, C. F. Williams, J. Yang, S. Yeganeh, S. R. Yost, Z.-Q. You, I. Y. Zhang, X. Zhang, Y. Zhao, B. R. Brooks, G. K. L. Chan, D. M. Chipman, C. J. Cramer, W. A. Goddard, M. S. Gordon, W. J. Hehre, A. Klamt, H. F. Schaefer, M. W. Schmidt, C. D. Sherrill, D. G. Truhlar, A. Warshel, X. Xu, A. Aspuru-Guzik, R. Baer, A. T. Bell, N. A. Besley, J.-D. Chai, A. Dreuw, B. D. Dunietz, T. R. Furlani, S. R. Gwaltney, C.-P. Hsu, Y. Jung, J. Kong, D. S. Lambrecht, W. Liang, C. Ochsenfeld, V. A. Rassolov, L. V. Slipchenko, J. E. Subotnik, T. Van Voorhis, J. M. Herbert, A. I. Krylov, P. M. W. Gill and M. Head-Gordon, *Mol. Phys.*, 2015, **113**, 184-215.

(57). H.-J. Werner, P. J. Knowles, F. R. Manby, J. A. Black, K. Doll, A. Heßelmann, D. Kats, A. Köhn, T. Korona, D. A. Kreplin, Q. Ma, T. F. Miller, A. Mitrushchenkov, K. A. Peterson, I. Polyak, G. Rauhut and M. Sibaev, *J. Chem. Phys.*, 2020, **152**, 144107.

(58). H.-J. Werner, P. J. Knowles, G. Knizia, F. R. Manby and M. Schütz, *Wiley Interdiscip. Rev. Comput. Mol. Sci.*, 2012, **2**, 242-253.

(59). J. M. Seminario, *Int. J. Quantum Chem.*, 1996, **60**, 1271-1277.

(60). E. Brémond and C. Adamo, *J. Chem. Phys.*, 2011, **135**, 024106.

(61). A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 1372-1377.

(62). M. J. Kryger, A. M. Munareto and J. S. Moore, *J. Am. Chem. Soc.*, 2011, **133**, 18992-18998.

(63). H. M. Klukovich, Z. S. Kean, S. T. Iacono and S. L. Craig, *J. Am. Chem. Soc.*, 2011, **133**, 17882-17888.

(64). J. Wang, T. B. Kouznetsova, R. Boulatov and S. L. Craig, *Nat. Commu.*, 2016, **7**, 13433.

(65). S. Garcia-Manes and A. E. M. Beedle, *Nat. Chem.*, 2017, **1**.

(66). A.-S. Duwez, S. Cuenot, C. Jérôme, S. Gabriel, R. Jérôme, S. Rapino and F. Zerbetto, *Nat. Nanotechnol.*, 2006, **1**, 122-125.

(67). M. K. Beyer and H. Clausen-Schaumann, *Chemical Reviews*, 2005, **105**, 2921-2948.

(68). F. R. Kersey, W. C. Yount and S. L. Craig, *J. Am. Chem. Soc.*, 2006, **128**, 3886-3887.

(69). A. P. Wiita, S. R. K. Ainavarapu, H. H. Huang and J. M. Fernandez, *Proc. Natl. Acad. Sci. USA*, 2006, **103**, 7222-7227.

(70). P. Zheng, G. M. Arantes, M. J. Field and H. Li, *Nat. Commu.*, 2015, **6**, 7569.

(71). S. Akbulatov, Y. Tian, Z. Huang, T. J. Kucharski, Q.-Z. Yang and R. Boulatov, *Science*, 2017, **357**, 299-303.

(72). M. Grandbois, *Science*, 1999, **283**, 1727-1730.

(73). P. Zheng and H. Li, *J. Am. Chem. Soc.*, 2011, **133**, 6791-6798.

(74). S. W. Schmidt, P. Filippov, A. Kersch, M. K. Beyer and H. Clausen-Schaumann, *ACS Nano*, 2012, **6**, 1314-1321.

(75). A. E. M. Beedle, A. Lezamiz, G. Stirnemann and S. Garcia-Manyes, *Nat. Commu.*, 2015, **6**, 7894.

- (76). M. F. Pill, A. L. L. East, D. Marx, M. K. Beyer and H. Clausen-Schaumann, *Angew. Chem.*, 2019, **58**, 9787-9790.
- (77). D. Schütze, K. Holz, J. Müller, M. K. Beyer, U. Lüning and B. Hartke, *Angew. Chem.*, 2015, **54**, 2556-2559.
- (78). M. M. Hansmann, R. L. Melen, M. Rudolph, F. Rominger, H. Wadepohl, D. W. Stephan and A. S. K. Hashmi, *J. Am. Chem. Soc.*, 2015, **137**, 15469-15477.
- (79). P. A. May and J. S. Moore, *Chem. Rev. Soc.*, 2013, **42**, 7497.
- (80). J. Li, C. Nagamani and J. S. Moore, *Acc. Chem. Res.*, 2015, **48**, 2181-2190.
- (81). H. M. Klukovich, Z. S. Kean, A. L. B. Ramirez, J. M. Lenhardt, J. Lin, X. Hu and S. L. Craig, *J. Am. Chem. Soc.*, 2012, **134**, 9577-9580.
- (82). M. F. Pill, K. Holz, N. Preußke, F. Berger, H. Clausen-Schaumann, U. Lüning and M. K. Beyer, *Chem. Eur. J.*, 2016, **22**, 12034-12039.
- (83). H. Li and G. C. Walker, *ACS Nano*, 2017, **11**, 28-30.
- (84). M. van Galen, J. P. Kaniraj, B. Albada and J. Sprakel, *J. Phys. Chem. C*, 2022, **126**, 1215-1221.
- (85). M. Nisoli, P. Decleva, F. Calegari, A. Palacios and F. Martín, *Chem. Rev.*, 2017, **117**, 10760-10825.