



SMM 27 Conference
Torino 8 – 11 September 2025
<https://smm27.polito.it>
smm27@polito.it

Conference Chairs: Carlo Appino and Carlo Ragusa

This is the template to submit your abstracts to the SMM27 Conference. Please fill the mandatory metadata in the table below, then type your abstract in the next page. Send us by e-mail at smm27@polito.it this whole document, both in docx and in pdf format.

Full name	Abhishek Naik	Please type here the presenting author's full name.
e-mail address	a.naik@uliege.be	Please type here the presenting author's e-mail address.
Abstract title	Surface artificial grooving and engraving for magnetic anisotropy texture patterning	Please type here the abstract title. It must be the same as the one in the next page.
Full list of authors	Abhishek Naik; Nicolas Lejeune; Cyril Delforge; Alejandro V. Silhanek; Emile Fourneau	Please type here the full list of authors co-signing the abstract. It must be the same as the one in the next page. Use semicolons (;) as separators.
Scientific topic	Magnetostriction, anisotropy, magnetocaloric properties	Pick the topic where your abstract best fits into. Refer to the web site.
Keywords	Anisotropy; thin films; nanolithography; AFM nanomachining	Please specify at least one keyword describing your abstract. In case of more than one keyword, use semicolons (;) as separators.
Preferred presentation method	Oral	Please specify either oral or poster.

Surface artificial grooving and engraving for magnetic anisotropy texture patterning

Abhishek Naik¹, Nicolas Lejeune², Cyril Delforge³, Alejandro V. Silhanek⁴, Emile Fourneau⁵

^a *Experimental Physics of Nanostructured Materials, Department of Physics, Université de Liège, B-4000 Sart Tilman, Belgium.*

In this work, we investigate the induction of in-plane uniaxial magnetic anisotropy in permalloy thin films through Surface Artificial Grooving and Engraving (SAGE), a technique that involves the controlled nanoscale scratching of the film surface using atomic force nanolithography. This process generates a well-ordered groove array resulting in a strong uniaxial anisotropy with the easy axis aligned along the groove direction. The strength of this anisotropy is found to increase for small period and deep engraving. This approach is applied to patterned Py structures, enabling the mastering of domain arrangement and domain-wall motion. In particular, we demonstrate the control of vortex-state chirality in ferromagnetic disks and the direction of spin wave propagation in corrugated permalloy waveguides.

1. Introduction

Uniaxial magnetic anisotropy can be induced in permalloy through substrate corrugation, as previously demonstrated in corrugated Si systems [1]. This finding motivated further exploration of anisotropy control at the micron scale through direct structuring of the ferromagnet itself. Here, we present a method for tailoring magnetic anisotropy using the Surface Artificial Grooving and Engraving (SAGE) technique, where the periodicity and depth of grooves dictate the anisotropy strength. Beyond the control of anisotropy, this approach enables the manipulation of domain walls, tuning the magnetic disk chirality [2] and the excitation of zero-field spin waves [3]. The technique further opens pathways for engineering multidomain magnetic architectures and guiding spin wave propagation in corrugated ferromagnetic media [4].

2. Results and discussion

A series of 30 nm-thick, 25 μm -wide square permalloy samples were patterned using atomic force nanolithography, employing the SAGE technique. Corrugations were introduced across the entire structure, with systematically varied depth and periodicity to investigate their impact on the magnetization reversal mechanism. The coercive field was found to scale linearly with groove depth, while an increase in periodicity resulted in an inverse relationship with coercivity. These findings highlight the tunability of magnetic anisotropy through controlled nanoscale structuring.

A further extension of this concept was applied to local corrugation in a Py waveguide to investigate its impact on spin wave propagation. The findings revealed that the structured waveguide supported zero-field spin wave propagation with an enhanced amplitude compared to its non-corrugated counterpart. Additionally, it was observed that local corrugation played a crucial role in controlling the vortex chirality in ferromagnetic disks, enabling switching between chiral states under an applied field. Furthermore, the introduction of corrugation enabled the tuning of magnetoresistance in magneto-resistive Py stripes, resulting in an improved linear response in MR devices and offering an alternative approach to the traditional barber pole configuration [5].

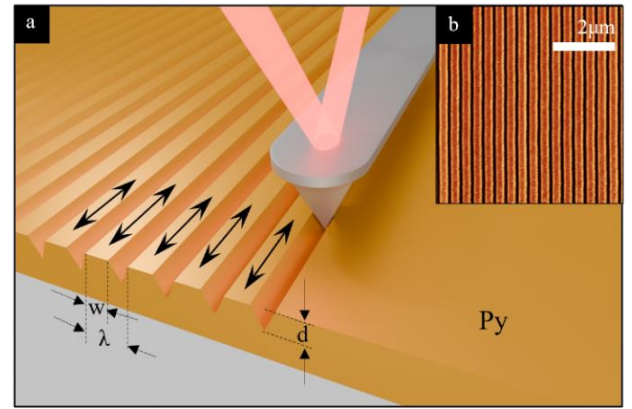


Figure 1: (a) Schematic representation of the SAGE technique via atomic force nanolithography. (b) Atomic Force Microscopy image of a SAGE-patterned region.

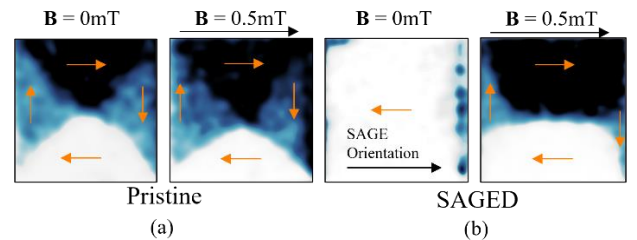


Figure 2: (a) MOKE images of a pristine 30 nm thick Py square in the remanent state (left) and under a 0.5 mT applied field (right). (b) MOKE images of a SAGED Py square (with SAGE orientation along the indicated direction) in the remanent state (left) and under a 0.5 mT field (right) highlighting the emergence of uniaxial anisotropy. The orange arrows in the samples indicate the direction of magnetization ($\mathbf{M}$).

References

- [1] M. O. Liedke et al., Phys. Rev. B **87**, 024424 (2013).
- [2] M. Y. Im et al., Nat. Commun. **5**, 5620 (2014).
- [3] I. Turčan et al., Appl. Phys. Lett. **118**, 092405 (2021).
- [4] J. Klíma et al, Appl. Phys. Lett. **124**, 112404 (2024).
- [5] Kuijk et al., IEEE Trans. Magn. **11**, 1215-1217 (1975).

Acknowledgments: The authors acknowledge the financial support from the Fonds de la recherche Scientifique - FNRS, under the grants Weave-PDR T.0208.23 and CDR J.0199.25. N.L. et C.D. acknowledge support from F.R.S.-FNRS (Research Fellowships FRiA). The work of E. Fourneau has been financially supported by the FWO and F.R.S.-FNRS under the Excellence of Science (EOS) project O.0028.22.